

# Fast-growing native tree species to the secondary forest of East Kalimantan, Indonesia: Physicochemical properties of woody materials for bioelectricity feedstocks

*by Yuliansyah Yuliansyah*

---

**Submission date:** 29-Mar-2023 09:44AM (UTC+0700)

**Submission ID:** 2049606929

**File name:** st\_Kalimantan,\_Indonesia\_Physicochemical\_properties\_of\_woody.pdf (909.25K)

**Word count:** 6515

**Character count:** 34583

## Fast-growing native tree species to the secondary forest of East Kalimantan, Indonesia: Physicochemical properties of woody materials for bioelectricity feedstocks

YULIANSYAH<sup>1</sup>, MUHAMMAD TAUFIQ HAQIQI<sup>1</sup>, KRISNA ADIB SETIAWAN<sup>1</sup>, AGUS SETIAWAN<sup>1</sup>, PRISTIANGGA DWI SAPUTRA<sup>1</sup>, HERI SUKMA IQBAL ROMADLON<sup>1</sup>, AHMAD MUKHDOR<sup>1</sup>, RICO RAMADHAN<sup>2</sup>, RUDIANTO AMIRTA<sup>1,\*</sup>

<sup>1</sup>Faculty of Forestry, Universitas Mulawarman, Jl. Penajam, Kampus Gn. Kelua, Samarinda 75123, East Kalimantan, Indonesia.

Tel./Fax.: +62-541-748683. \*email: ramirta@fahutan.unmul.ac.id

<sup>2</sup>Department of Chemistry, Faculty of Science and Technology, Universitas Airlangga, Jl. Dr. Ir. Soekarno, Mulyorejo, Surabaya 60115, East Java, Indonesia

Manuscript received: 13 May 2022. Revision accepted: 17 June 2022.

**Abstract.** Yuliansyah, Haqiqi MT, Setiawan KA, Setiawan A, Saputra PD, Romadlon HSI, Mukhdor A, Ramadhan R, Amirta R. 2022. Fast-growing native tree species to the secondary forest of East Kalimantan, Indonesia: Physicochemical properties of woody materials for bioelectricity feedstocks. *Biodiversitas* 23: 3379-3386. The conversion of woody biomass into electricity through a thermochemical process has recently attracted significant attention worldwide to promote green energy production. It provides a low-cost and straightforward operation promising for developing rural areas, especially with limited transportation access. In East Kalimantan Province, almost all remote areas are surrounded by forests with high tree species diversity, which is the potential to be utilized for sustainable feedstocks in electric power plants. This study pointed out the energy potential produced from woody biomass of selected fast-growing tree species native to East Kalimantan secondary tropical forest: *Elaeocarpus ferrugineus* (Jacq.) Steud., *Ficus aurata* (Miq.) Miq., *Fordia splendidissima* (Blume ex Miq.) Buijsen, *Lindera lucida* (Blume) Boerl., *Mallotus paniculatus* (Lam.) Mull. Arg. and *Schima wallichii* (DC). Their wood physicochemical properties were firstly investigated. Furthermore, each species' wood quality for solid energy purposes was presented as the fuel value index (FVI). The results revealed that the change from greenwood into wood chip effectively removed the moisture content, thus improving efficiency to achieve higher energy potency. Our findings showed that the highest energy potency was obtained from the wood chip of *F. splendidissima* (3.61 MWh/ton), followed by *S. wallichii* (2.98 MWh/ton). A similar pattern was also found in FVI determination showing that the wood chip of *S. splendidissima* had the greatest value (8970). Therefore, we observed that the high quality of *S. splendidissima* compared to other selected fast-growing species indicates its high suitability for further large-scale crop plantation to supply wood chips for biomass-based electricity generation.

**Keywords:** Electricity, fast-growing, native species, secondary forest, woody biomass

### INTRODUCTION

The exploitation of fossil fuels has significantly increased the degradation of natural resources and the environment. Its combustion corresponding to generating electricity constantly accelerates the global warming potential. According to the report from the International Energy Agency, energy production from fossil fuels sectors is responsible for more than 80% of released carbon dioxide (CO<sub>2</sub>) in the atmosphere, or it is estimated to exceed two-thirds of total greenhouse gas (GHC) emission (Ram et al. 2018; Cardoso et al. 2019). Although the Paris Agreement in 2015 implicitly called for shifting away from the domination of fossil fuels, the human population and industrialization are continuously growing, creating a significant challenge on how to mitigate climate change and reduce those harmful GHC effects (Karmaker et al. 2020; Rempnand Gupta 2020). The United Nations (UN), through the Climate Action Summit in New York in 2019, has set a global plan to achieve net-zero emissions by 2050 (Mutezo and Mulopo 2021). Therefore, many countries

have committed to addressing a transition from fossil fuels to renewable energy by implementing a legal policy (Molayudego et al. 2017; Moya et al. 2019; Rincon et al. 2019).

The usage of renewable energy has gained a lot of attention (Nugraha et al. 2020). Among all resources, biomass has been considered the most appreciated renewable energy globally, with a proportion of 12.4% of the total energy consumption (Wang et al. 2020). Energy production from biomass is expected to meet global energy demands in the future (Bilgili et al. 2017). It offers various advantages over other renewable sources, such as better energy properties and less CO<sub>2</sub> emission (Liu et al. 2014; Tenorio et al. 2015). Woody biomass harvested from the forest is also one of the promising feedstocks to produce clean energy because it contains quite low sulfur and nitrogen (Hupa et al. 2017; Lee et al. 2021). Since almost all remote areas in Indonesia are covered by forests with limited transportation access, the approach to using its biomass will be adequate to overcome the electricity

limitation in those rural areas. Moreover, it will improve economic growth by providing micro or small-scale electricity with a simple and cheaper process. When the wood is burned during the combustion stage, the CO<sub>2</sub> emission can be easily absorbed by available forest plant species through photosynthesis. The net cycle of CO<sub>2</sub> is always in balance, and this phenomenon is known as neutral carbon (Mäkipää et al. 2015; Proto et al. 2021). It will potentially lead to a zero-emission power system (Mori et al. 2022). Excellent performance of biomass-based electricity has been reported earlier (González et al. 2015). Furthermore, it has also been successfully developed in many countries in the world, such as in Brazil (Ferreira 2018), Finland (Majava et al. 2022), Ghana (Präger et al. 2019), India (Narnaware and Panwar 2022), Japan (Battuvshin et al. 2020), Portugal (da Costa et al. 2020), Spain (Aguado et al. 2022), and United States (Broughel 2019).

East Kalimantan province was one of Indonesia's most considerable bioenergy potentials due to its high availability of wood biomass resources from the forest (Mangunsong et al. 2017). The high diversity of biomass plant species distributed in the tropical rain forest of East Kalimantan was also reported as the essential biodiversity value in Indonesia for many endemic species compared to other places on the earth (Pio and D'Cruz 2005). However, the wood harvested from its forest resources was still dominated by the Dipterocarpaceae family, commonly used for furniture and construction purposes. Although it had promising calorific values, it was considered a low-growing tree species that was not desirable for sustainable energy crops (Yuliansyah et al. 2016). On the other hand, fast-growing tree species planted on forest plantations, such as *Acacia mangium*, *Anthocephalus cadamba*, *Eucalyptus pellita*, *Gmelina arborea*, and *Paraserianthes falcataria*, are have been reported to possess low heating value (Amirta et al. 2016; Haqiqi et al. 2022). Therefore, finding suitable plant species having high wood calorific value combined with their fast-growing ability to obtain high biomass yield for energy-electricity production is recently growing (Haqiqi et al. 2018).

The investigation of native species can be an important step in searching for suitable plant biomass species to be cultivated as energy crops in some remote areas. In East Kalimantan Province, many local fast-growing species are characterized as non-commercial species, even known as species with high adaptability to grow well in their origin ecosystem. They are mainly found in plant communities at secondary forest succession. Commonly used as firewood by local people, those species still have less attention for further large-scale utilization, especially in energy production. These species will promise future plantation of short-rotation wood crops to provide sustainable raw materials with a faster-growing ability. However, further wood physicochemical analysis was necessary to meet an ideal energy crop requirement. This study reported comparing wood physicochemical properties of selected fast-growing tree species native to the East Kalimantan forest to be used as feedstocks in electricity production.

## MATERIALS AND METHODS

### Study area

Wood biomass materials and leaf samples from some fast-growing native species were collected at the secondary forest of Mulawarman University Educational Forest (KHDTK Fahutan UNMUL, Samarinda), Samarinda City, East Kalimantan Province, Indonesia (0°25'10"S-0°25'10"E and, 117°14'00"E-117°14'14"E, 300 ha).

### Biomass plant species

Medium trees with 6-8 cm diameter recognized as native fast-growing species naturally grown on secondary tropical rain forests in East Kalimantan were pointed out. Identification through leaf herbarium specimens of each species was deposited at the Laboratory of Forest Dendrology and Ecology, Faculty of Forestry, Mulawarman University, Samarinda, Indonesia. In this study, six species were identified, namely *Elaeocarpus ferrugineus* (Jacq.) Steud., *Ficus aurata* (Miq.) Miq., *Fordia splendidissima* (Blume ex Miq.) Buijsen, *Lindera lucida* (Blume) Boerl., *Mallotus paniculatus* (Lam.) Mull.Arg. and *Schima wallichii* (DC). They belong to different family groups, including Elaeocarpaceae, Moraceae, Fabaceae, Lauraceae, Euphorbiaceae and Theaceae, respectively. All woody biomass samples were collected in September 2021. They were debarked to analyze the dry bark-wood ratio, then converted into wood chips before proceeding to laboratory analysis.

### Determination of wood physicochemical properties and energy potency

The total moisture and proximate compositions of wood materials were carried out according to ASTM D 7582-12 method. The lost weight of the samples after reaching the constant weight in a hot air oven at 105°C was calculated to determine the moisture content. For proximate analysis, the samples were dried and grounded into smaller sizes (±60 mesh). The measurements consisted of two steps in a furnace. The first step was done by heating from 300-575°C for 3 hours. The weight loss was measured and noted as a volatile matter (VM) substance. Then, the temperature was increased to reach 950°C for 2 hours to heat the remaining samples. After cooling down to room temperature, the residual weight was measured in ash content while the lost weight was fixed carbon (FC).

The ultimate compositions of wood biomass including carbon (C), hydrogen (H), and oxygen (O) were estimated based on the following Equation (Parikh et al. 2007):

$$C (\%) = (0.637 \times FC) + (0.455 \times VM) \quad (1)$$

$$H (\%) = (0.052 \times FC) + (0.062 \times VM) \quad (2)$$

$$O (\%) = (0.304 \times FC) + (0.476 \times VM) \quad (3)$$

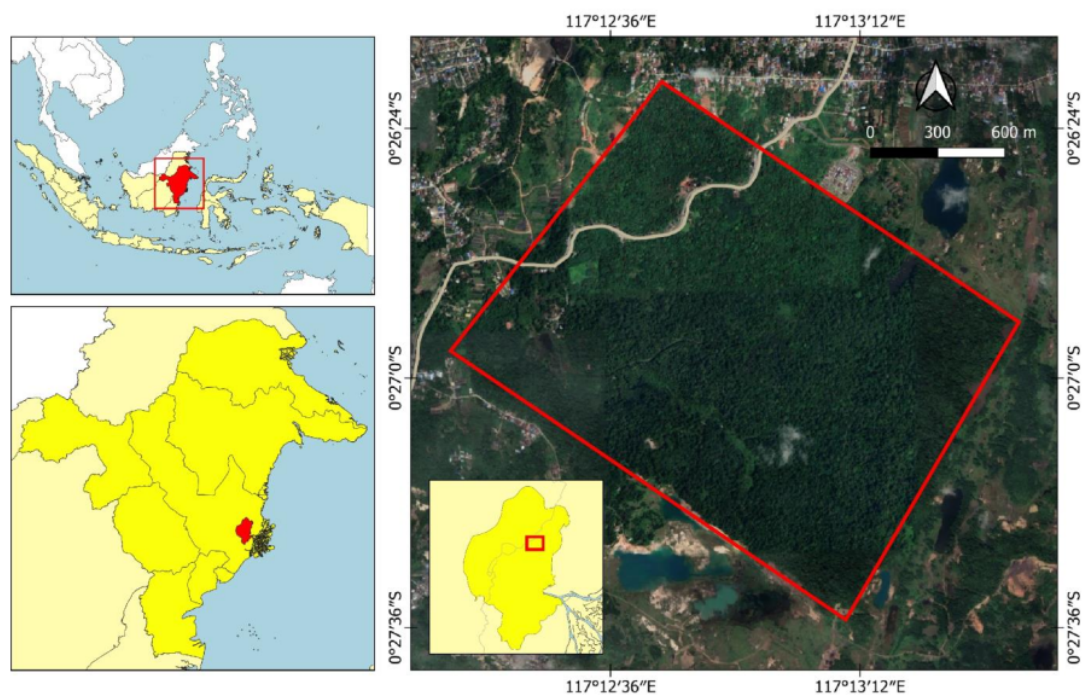


**Figure 1.** Research location conducted at Mulawarman University educational forest, Samarinda City, East Kalimantan Province, Indonesia ( $0^{\circ}25'10''$  LS -  $0^{\circ}25'10''$  LS and  $117^{\circ}14'00''$  BT- $117^{\circ}14'14''$  BT).

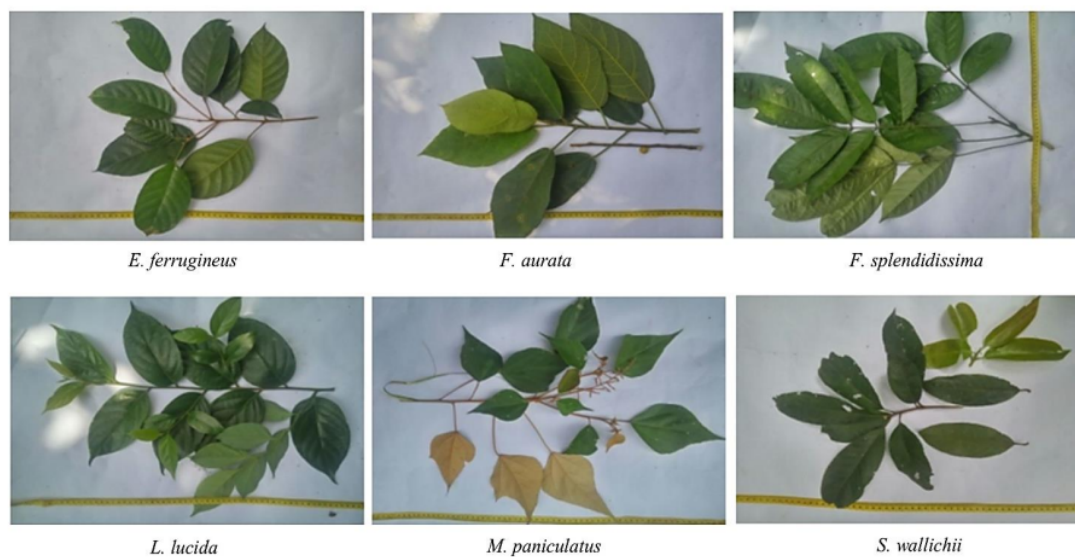


**Figure 2.** Fresh leaf shape varieties of some fast-growing native tree species were collected from the secondary forest of Mulawarman University educational forest, Samarinda City, East Kalimantan Province, Indonesia

Measurement of wood density ( $\text{kg/m}^3$ ) was conducted by drying the wood samples at  $105^\circ\text{C}$  following Edwards et al. (2014). The wood calorific value ( $\text{MJ/kg}$ ) was accomplished in a bomb calorimeter according to the standard from EN-ISO 15400:2011, followed by the calculation of energy-electricity potency according to Francescato et al. (2008). Those measurements were classified into greenwood and wood chips. Furthermore, the fuel value index (FVI) was calculated using the equation as follows (Jain and Singh 1999):

$$\text{FVI} = (\text{Calorific value} \times \text{density}) / (\text{ash} \times \text{moisture}) \quad (4)$$

## RESULTS AND DISCUSSION

### Plant biomass species

Generally, tropical forest areas provide better environmental conditions for plants to produce sustainable biomass with high yields. This condition will lead to its potential wide-range application in biomass-based conversion technology, such as electricity generation. However, a previous study demonstrated that forest biomass species with high energy content were commonly produced from low-growing species (Amirta et al. 2016). In large-scale electricity production, utilization of the low-growing species in energy feedstocks requires a slow harvest cycle period with a high-cost operation. Therefore, this study assessed woody materials obtained from selected fast-growing species, including *E. ferrugineus*, *F. aurata*, *F. splendidissima*, *L. lucida*, *M. paniculatus*, and *S. wallichii* for the purpose of energy-electricity feedstock. Those species are abundant and native to the secondary forest of East Kalimantan, in which the local people traditionally used their wood as firewood for cooking activities. Nevertheless, literature describing those plant species for further industrial application is still rare. The measurement of bark and wood proportion of each species was summarized in Table 1. It was noticeable that three species, including *E. ferrugineus*, *F. aurata*, and *F. splendidissima*, had the lowest bark-wood ratio (0.7). The highest bark proportion was obtained from *S. wallichii*, followed by *M. paniculatus* and *L. lucida*, with the value of 12.95%, 11.22%, and 7.80%, respectively. It has been reported earlier that the stem bark of *E. ferrugineus* was the potential for treating malaria-like symptoms (Ismail et al. 2015). On the other hand, *S. wallichii* bark could be

utilized as an antimicrobial agent (Dewanjee et al. 2008). Hence, these interesting properties could potentially enhance their application for both energy feedstocks and natural medicine products. Since the stem bark produces a high quantity of ash (Pérez et al. 2008), its removal from wood when used for energy production through thermochemical conversion is necessary.

### Wood physicochemical properties

Moisture content, density, and chip capacity of woody materials examined from some selected native tree species were summarized in Table 2. It has been previously reported that the percentage of wood moisture content depends on the plant species, season, and storage condition (Mancini and Rinnan 2021). In green conditions, the highest wood moisture content was obtained from *S. wallichii* (59.25%), while the lowest moisture content could be found in *F. splendidissima* (40.37%). The conversion of the wood into chip form evidently reduced their moisture content. As shown in Table 2, all wood chips revealed a lower moisture percentage than green wood conditions. It was found that the average moisture content of wood chips was 9.58%. It seems that wood chip form could easily evaporate the amount of water. Surprisingly, this situation could also be benefited considerably increase the achieved calorific value due to the water loss phenomenon (Figure 3A). According to the measurement of wood density, it was found that the highest wood density was obtained from *F. splendidissima* ( $760 \text{ kg/m}^3$ ). The second and third largest were found in *E. ferrugineus* ( $575 \text{ kg/m}^3$ ) and *S. wallichii* ( $536 \text{ kg/m}^3$ ) wood, respectively. The average wood density value from all species used in this study was  $507 \text{ kg/m}^3$ . Meanwhile, their form changed into wood chips that needed a high storage capacity. It was found that the average value of wood chips of all species was  $201 \text{ kg per m}^3$  of storage area. The high wood density contributed to increasing the efficiency of wood chip storage. As observed from *F. splendidissima*, its wood chip ( $300 \text{ kg/m}^3$ ) was the most efficient storage capacity among all woody materials used. Especially for a large-scale operation, the high density of wood chips potentially contributes to low energy production costs (Bahadori et al. 2014). In contrast, low wood density affects the fast burning of the reactor, high transport costs, and high storage capacity (de Oliveira et al. 2013).

4

**Table 1.** Wood and bark ratio of some fast-growing tree species native to the secondary forest of East Kalimantan, Indonesia

| Plant species            |             | Bark proportion  | Wood proportion  | Bark-wood ratio |
|--------------------------|-------------|------------------|------------------|-----------------|
| Latin name               | Local name  | (%)              | (%)              |                 |
| <i>E. ferrugineus</i>    | Belau       | $6.37 \pm 0.59$  | $93.63 \pm 0.59$ | $0.07 \pm 0.01$ |
| <i>F. aurata</i>         | Kayu ara    | $6.65 \pm 0.25$  | $93.35 \pm 0.25$ | $0.07 \pm 0.00$ |
| <i>F. splendidissima</i> | Makumpit    | $6.70 \pm 0.93$  | $93.30 \pm 0.93$ | $0.07 \pm 0.01$ |
| <i>L. lucida</i>         | Madang      | $7.80 \pm 0.55$  | $92.20 \pm 0.55$ | $0.08 \pm 0.01$ |
| <i>M. paniculatus</i>    | Balik angin | $11.22 \pm 0.45$ | $88.78 \pm 0.45$ | $0.13 \pm 0.01$ |
| <i>S. wallichii</i>      | Puspa       | $12.95 \pm 0.68$ | $87.06 \pm 0.68$ | $0.15 \pm 0.01$ |
| Average                  |             | $8.62 \pm 2.79$  | $91.39 \pm 2.79$ | $0.10 \pm 0.10$ |

**Table 2.** Moisture content, wood density, and chip capacity of some fast-growing tree species native to the secondary forest of East Kalimantan, Indonesia

| Plant species            |             | Moisture content (%) |             | Wood density (kg/m <sup>3</sup> ) | Chip capacity (kg/m <sup>3</sup> ) |
|--------------------------|-------------|----------------------|-------------|-----------------------------------|------------------------------------|
| Latin name               | Local name  | Greenwood            | wood Chip   |                                   |                                    |
| <i>E. ferrugineus</i>    | Belau       | 49.77 ± 1.59         | 9.34 ± 0.03 | 575 ± 25.78                       | 227 ± 10.18                        |
| <i>F. aurata</i>         | Kayu ara    | 56.90 ± 0.63         | 9.62 ± 0.03 | 487 ± 23.19                       | 192 ± 9.15                         |
| <i>F. splendidissima</i> | Makumpit    | 40.37 ± 0.19         | 9.81 ± 0.01 | 760 ± 22.69                       | 300 ± 8.94                         |
| <i>L. lucida</i>         | Madang      | 50.64 ± 1.05         | 9.64 ± 0.05 | 354 ± 14.86                       | 140 ± 5.86                         |
| <i>M. paniculatus</i>    | Balik angin | 52.85 ± 0.28         | 9.52 ± 0.03 | 331 ± 11.21                       | 131 ± 4.42                         |
| <i>S. wallichii</i>      | Puspa       | 59.25 ± 1.83         | 9.53 ± 0.01 | 536 ± 18.99                       | 211 ± 7.49                         |
| Average                  |             | 51.63 ± 6.61         | 9.58 ± 0.15 | 507 ± 157.7                       | 200 ± 62.6                         |

**Table 3.** Proximate and ultimate analysis of some fast-growing tree species native to the secondary forest of East Kalimantan, Indonesia

| Plant species            | Ash (%)     | Fixed carbon (%) | Volatile matter (%) | Carbon (%)   | Hydrogen (%) | Oxygen (%)   | H/C ratio   |
|--------------------------|-------------|------------------|---------------------|--------------|--------------|--------------|-------------|
| <i>E. ferrugineus</i>    | 2.29 ± 0.03 | 14.23 ± 0.18     | 74.14 ± 0.14        | 42.80 ± 0.18 | 5.34 ± 0.01  | 39.62 ± 0.12 | 0.12 ± 0.00 |
| <i>F. aurata</i>         | 2.30 ± 0.02 | 13.53 ± 0.16     | 75.55 ± 0.17        | 42.54 ± 0.17 | 5.33 ± 0.01  | 39.60 ± 0.13 | 0.13 ± 0.00 |
| <i>F. splendidissima</i> | 1.62 ± 0.04 | 13.85 ± 0.13     | 74.72 ± 0.13        | 42.82 ± 0.14 | 5.35 ± 0.02  | 37.78 ± 0.10 | 0.12 ± 0.00 |
| <i>L. lucida</i>         | 1.71 ± 0.02 | 14.82 ± 0.21     | 73.83 ± 0.21        | 43.03 ± 0.04 | 5.35 ± 0.01  | 39.62 ± 0.04 | 0.12 ± 0.00 |
| <i>M. paniculatus</i>    | 2.69 ± 0.01 | 13.36 ± 0.10     | 74.43 ± 0.16        | 42.38 ± 0.13 | 5.31 ± 0.01  | 39.49 ± 0.10 | 0.13 ± 0.00 |
| <i>S. wallichii</i>      | 1.64 ± 0.05 | 12.96 ± 0.16     | 75.87 ± 0.09        | 42.78 ± 0.14 | 5.38 ± 0.01  | 40.05 ± 0.09 | 0.13 ± 0.00 |
| Average                  | 2.04 ± 0.44 | 13.79 ± 0.66     | 74.76 ± 0.80        | 42.72 ± 0.44 | 5.34 ± 0.66  | 39.70 ± 0.80 | 0.13 ± 0.00 |

Various laboratory tests were carried out for proximate and ultimate analysis. The proximate analysis includes ash, fixed carbon, and volatile matter (Table 3). These parameters strongly affected the performance of combustion, pyrolysis, and gasification of wood biomass in the thermochemical conversion process (Tursunov and Abduganiev 2020). Ash content of all woody materials showed less than 5%, which demonstrated their high potency utilized for raw materials of energy production. The low value of ash residue (<5%) resulting from the combustion process has a positive impact on increasing the efficiency stage and avoiding damage to the electricity reactor (Shao et al. 2011). Nimmanterdwong et al. (2021) stated that the ash in biomass is directly related to the mineral and inorganic elements absorbed by plants from the ground via the root cells, while its percentage differently depends on the soil properties, rocks, chemical treatment, and available metal contents. The volatile matters of all woody materials in this study were in the range of 73.83 - 75.87%, whereas the fixed carbons were in the range of 12.96 - 14.82%. It has been reported that the heat decomposition of cellulose and hemicellulose in biomass is the source of volatile matter. In contrast, lignin is a char source due to its richness in carbon atoms (Vega et al. 2019). The ultimate compositions, including C (carbon), H (hydrogen), and O (oxygen), were presented in Table 3. This investigation is essential to determine the theoretical air-fuel ratio in the thermochemical system and predict the released pollution (Telmo et al. 2010). The average value of C, H, and O was 42.72%, 5.35%, and 39.70%, respectively. It was clearly observed that all woody materials contained C higher than O, indicating its high suitability used as the energy feedstock since high C content will increase the obtained calorific value. Moreover, the C content, with a value of more than 40% in this study, was in line with that of the C content of various

tropical woods (Amirta et al. 2016; Amirta et al. 2019; Yuliansyah et al. 2019; Mukhdlor et al. 2021). Ratio of H/C was also assessed since a higher value could contribute to improving energy efficiency and decreasing released emissions during combustion (Gopalakrishnan et al. 2019). The average H/C ratio of the six-plant studied was 0.13. This value was comparable with sawdust previously reported by García et al. (2012). More importantly, these findings demonstrated that all fast-growing species selected in this study possessed better H/C ratio than those of other tropical fast-growing woody species, such as *Bridelia tomentosa*, *Fagraea racemosa*, *Piper aduncum*, *Trema orientalis*, and *Vernonia arborea* (Amirta et al. 2016).

#### Wood quality for energy feedstock

The investigation of the fuelwood quality of native species is presented in Figure 3. The important parameters were calorific value, wood chip conversion value, energy-electricity potency, and fuel value index. According to Figure 3A, the conversion of green wood (original solid form) into wood chip form significantly enhanced the average calorific value up to 0.5-fold. It was calculated that the average calorific value of all examined woods in the green form (7.92 MJ/kg) increased to 17.01 MJ/kg at the wood chip condition. We found that those results were in line with decreasing the amount of moisture content on wood samples when converted into wood chips (51.63% to 9.58%) (Table 2). It has also been reported by Deboni et al. (2020) that lower moisture content is considered one of the factors that significantly influence the increased calorific value of woody biomass as a reliable energy source. The high proportion of moisture content in fuelwood could result in delayed ignition and devolatilization (Lu et al. 2008). Although this work promised high energy content, the wood chip form consequently required a larger storage

area (29 per ton of wood chip biomass than the greenwood form, as shown in Figure 3B).

In order to compare the suitability of woody materials from selected native species, further measurement of energy potency in MWh per ton biomass was performed (Figure 3C). The results showed that *F. splendidissima* exhibited the highest energy potency in both greenwood (2.21 MWh/ton) and wood chip (3.61 MWh/ton) forms. Although *S. wallichii* and *F. aurata* possessed high calorific values (Figure 3A), *F. splendidissima* had higher energy-electricity potency than those species due to its high wood density (760 kg/m<sup>3</sup>). Interestingly, even though *F. splendidissima* is considered fast-growing species, this species was classified as high wood density (< 600 kg/m<sup>3</sup>), whereas *S. wallichii* and *F. aurata* were characterized as medium wood density (400 - 600 kg/m<sup>3</sup>). Having a similar pattern with calorific value results, the energy potency of all woody materials to generate electricity demonstrated significantly enhanced value after converting into wood chips due to the moisture removal. Our previous study shows fast-growing species in the lowland community forest, such as *Gmelina arborea*, *Anthocephalus cadamba*, *Acacia mangium*, and *Paraserianthes falcata*, had relatively low energy potency (1.37 - 1.70 MWh/ton) (Amirta et al. 2016). Another study also reported that fast-growing and shrub species found in the tropical swamp-peat forest of Kutai Kartanegara in East Kalimantan generated low energy potency: *Kleinhovia hospita* (1.76 MWh/ton), *Cananga odorata* (1.36 MWh/ton), and

*Octomeles sumatrana* (1.17 MWh/ton) (Amirta et al. 2019). However, our findings in this study indicated that fast-growing species native to the secondary forest in East Kalimantan, especially *F. splendidissima*, could produce woody materials with superior energy capacity for electricity production.

The bioenergy potential of each fast-growing native species was represented by Fuel Value Index (FVI) (Figure 3D). The FVI is an essential assessment for screening desirable biomass species for solid fuel (Samal et al. 2021). This measurement was also used by Niemczyk et al. (2018) to rank the quality of 10 poplar cultivars in northern Poland. The FVI was calculated using combinations of some influencing factors, including ash content, moisture content, calorific value, and wood density. This study found that wood chips containing low moisture content increased the FVI result from each wood tested. The average FVI of the wood chip, which had a value of 5267, was significantly higher than that of the greenwood condition, with an average value of 698. The greatest FVI was obtained from *F. splendidissima* (8970), followed by *S. wallichii* and *F. ferrugineus* with the value of 7502 and 4958, respectively. A high FVI value of wood biomass was observed because of low ash content, low moisture content, and high density (Pérez et al. 2014). We concluded that the wood chip revealed lower moisture content compared to the original form (green condition), indicating its high suitability to produce sustainable green energy.

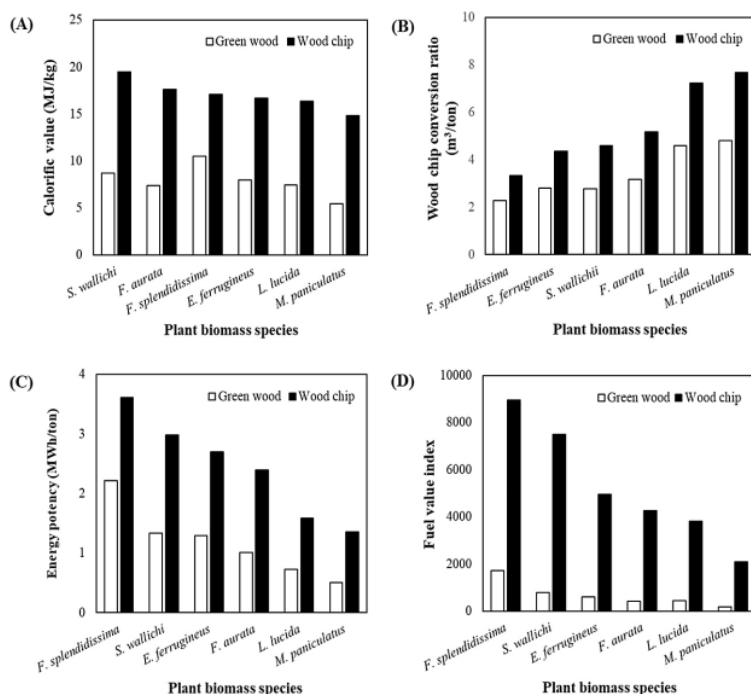


**Figure 3.** Analysis of some fast-growing tree species native to the secondary forest of East Kalimantan, Indonesia, for electricity feedstock: Wood calorific value (A), wood chip conversion ratio (B), energy potency (C), and fuel value index (D)

Finally, all woody materials obtained from fast-growing native species in the secondary forest of East Kalimantan were suitable for electricity feedstock due to the low ash content and a high proportion of carbon. When each wood biomass was converted into wood chip form, their efficiency in energy feedstocks (calorific value, storage capacity, energy-electricity potency, and FVI) was gradually increased since this form was able to remove moisture effectively. In contrast, the greenwood showed inefficient use since it might take longer to dry; thus, the cost of energy production will also increase. Among all biomass tested, the wood chip of *F. splendissima* exhibited the most appropriate properties for electricity feedstock due to its high energy potency (3.61 MWh/ton) with desired FVI value (8970). Furthermore, the high adaptability in the local ecosystem combined with its high wood density and fast-growing ability will be the promising characteristics that allow *F. splendissima* to be one of the ideal crops for energy feedstocks in the future. In general, this study successfully demonstrated the physicochemical properties of selected fast-growing native species in the tropical secondary forest in East Kalimantan, Indonesia, to generate electricity in rural communities, especially to develop the economic sector in this province.

#### ACKNOWLEDGEMENTS

The current study was financially supported by the Project Implementation Unit of Islamic Development Bank - PIU IsDB (Grant No. 402/UN17.45/DL/2021 for YI, TG, and MTH), and the research funding for lecturers and students from the Faculty of Forestry, Mulawarman University (For YI 2022)

#### REFERENCES

- Aguado R, Vera D, Jurado F, Beltrán G. 2022. An integrated gasification plant for electric power generation from wet biomass: toward a sustainable production in the olive oil industry. *Biomass Convers Biorefin*. DOI: 10.1007/s13399-021-02231-0.
- Amirta R, Haqiqi MT, Saparwadi Septia E, Mujiasih D, Setiawan KA, Sekedang MA, Yuliansyah, Wijaya A, Setiyono B, Suwinarti W. 2019. Searching for potential wood biomass for green energy feedstock: A study in tropical swamp-peat forest of Kutai Kertanegara, Indonesia. *Biodiversitas* 20 (6): 1516-1523. DOI: 10.13057/biodiv/d200605.
- Amirta R, Yuliansyah, Angi EM, Ananto BR, Setiyono B, Haqiqi MT, Septiana HA, Londong M, Oktavianto RN. 2016. Plant diversity and energy potency of community forest in East Kalimantan, Indonesia: Searching for fast-growing wood species for energy production. *Nusantara Biosci* 8 (1): 22-31. DOI:10.13057/nusbiosci/n080106.
- Bahadori A, Zahedi G, Zendejboudi S, Jamili A. 2014. Estimation of the effect of biomass moisture content on the direct combustion of sugarcane bagasse in boilers. *Intl J Sustain Energy* 33: 349-356. DOI:10.1080/14786451.2012.748766.
- Battuvshin B, Matsuoka Y, Shirasawa H, Toyama K, Hayashi U, Aruga K. 2020. Supply potential and annual availability of timber and forest biomass resources for energy considering inter-prefectural trade in Japan. *Land Use Policy* 97: 104780. DOI:10.1016/j.landusepol.2020.104780.
- Bilgic F, Koçak E, Bulut Ü, Kuşkaya S. 2017. Can biomass energy be an efficient policy tool for sustainable development? *Renew Sustain Energy Rev* 71: 830-845. DOI: 10.1016/j.rser.2016.12.109.
- Broushel AE. 2019. Impact of state policies on generating capacity for production of electricity and combined heat and power from forest biomass in the United States. *Renew Energy* 134: 1163-1172. DOI: 10.1016/j.renene.2018.09.058.
- Carvalho J, Silva V, Eusébio D. 2019. Techno-economic analysis of a biomass gasification power plant dealing with forestry residues blends for electricity production in Portugal. *J Clean Prod* 212: 741-753. DOI: 10.1016/j.jclepro.2018.12.054.
- da Costa TP, Quinteiro P, Arroja L, Dias AC. 2020. Environmental comparison of forest biomass residues application in Portugal: Electricity, heat, and biofuel. *Renew Sustain Energy Rev* 134: 110302. DOI:10.1016/j.rser.2020.110302.
- de Oliveira JL, da Silva JN, Pereira EG, Filho DO, Carvalho DR. 2013. Characterization and mapping of waste from coffee and eucalyptus production in Brazil for thermochemical conversion of energy via gasification. *Renew Sustain Energy Rev* 21: 52-58. DOI:10.1016/j.rser.2012.12.025.
- DeBorja TL, Simioni FJ, do Rosário JDA, Costa VJ. 2020. Quality of biomass from old wood waste deposits in Southern Brazil. *Biomass Bioenergy* 143: 105841. DOI: 10.1016/j.biombioe.2020.105841.
- Dewanjee S, Maiti A, Majumdar R, Majumdar A, Mandal SC. 2008. Evaluation of antimicrobial activity of hydroalcoholic extract *Schima wallichii* bark. *Pharmacologyonline* 1: 523-528.
- Edwards LE, Newby AF, Gilliam CH, Fain GB, Sibley JL, Murphy, AM. 2014. Evaluation of eastern redcedar substrate in the production of four annual species. *J Environ Hort* 32 (3): 167-173.
- Ferreira LRA, Otto RB, Silva FP, De Souza SNM, De Souza SS, Junior OA. 2018. Review of the energy potential of the residual biomass for distributed generation in Brazil. *Renew Sustain Energy Rev* 94: 440-455. DOI: 10.1016/j.rser.2018.06.034.
- Franciscato F, Antonini E, Bergomi LZ. 2008. *Wood Fuels Handbook: Production, Quality Requirements, Trading*. Legnaro, Italy.
- García R, Pizarro C, Lavín AG, Bueno JL. 2012. Characterization of agricultural biomass wastes for energy use. *Bioresour Technol* 103 (1): 249-258. DOI: 10.1016/j.biortech.2011.10.004.
- González A, Riba JR, Puig R, Navarro P. 2015. Review of micro-and pilot-scale technologies to produce electricity and heat from Mediterranean forests' wood chips. *Renew Sustain Energy Rev* 43: 143-155. DOI:10.1016/j.rser.2014.11.013.
- Gopalakrishnan B, Khanna N, Das D. 2019. Dark-fermentative hydrogen production. In: *Biohydrogen*. Elsevier. DOI: 10.1016/B978-0-444-64203-5.00004-6.
- Haqiqi MT, Hudaya D, Septiana HA, Ramadhan R Yuliansyah, Suwinarti W, Amirta R. 2022. Analysis of the ultimate wood composition of a forest plantation species, *Eucalyptus pellita*, to estimate its bioelectricity potency. *Biodiversitas* 23 (5): 2389-2394. DOI: 10.13057/biodiv/d230516.
- Haqiqi MT, Yuliansyah, Suwinarti W, Amirta R. 2018. Response surface methodology to simplify calculation of wood energy potency from tropical short rotation coppice species. *IOP Conf Ser: Earth Environ Sci*. DOI: 10.1088/1755-1315/144/1/012041.
- Hupa M, Karlström O, Vainio E. 2017. Biomass combustion technology development-It is all about chemical details. *Proc Combust Inst* 36 (1): 113-134. DOI: 10.1016/j.proci.2016.06.152.
- Ismail I, Linatoc AC, Mohamed M, Tokiman L. 2015. Documentation of medicinal plants traditionally used by the jakun people of endaurompin (peta) for treatments of malaria-like symptoms. *Jurnal Teknologi* 77 (31): 63-69. [Indonesian]
- Jain RK, Singh B. 1999. Fuelwood characteristics of selected indigenous tree species from central India. *Bioresour Technol* 68: 305-308. DOI: 10.1016/S0960-8524(98)00173-4.
- Karmaker AK, Rahman MM, Hossain MA, Ahmed MR. 2020. Exploration and corrective measures of greenhouse gas emission from fossil fuel power stations for Bangladesh. *J Clean Prod* 244: 118645. DOI: 10.1016/j.jclepro.2019.118645.
- Lee BH, Sh L, Lee DG, Jeon CH. 2021. Effect of torrefaction and ashless process on combustion and NOx emission behaviors of woody and herbaceous biomass. *Biomass Bioenergy* 151: 106133. DOI: 10.1016/j.biombioe.2021.106133.

- Liu Y, Xu Y, Zhang F, Yun J, Shen Z. 2014. The impact of biofuel plantation on biodiversity: a review. *Chinese Sci Bull* 59 (34): 4639-4651. DOI: 10.1007/s11434-014-0639-1.
- Lu G, Yan Y, Cornwell S, Whitehouse M, Riley G. 2008. Impact of co-firing coal and biomass on flame characteristics and stability. *Fuel* 87: 1133-1140. DOI: 10.1016/j.fuel.2007.07.005.
- Majava A, Vaden T, Toivanen T, Järvensivu P, Lähde V, Eronen JT. 2022. Sectoral low-carbon roadmaps and the role of forest biomass in Finland's carbon neutrality 2035 target. *Energy Strategy Rev* 41: 100836. DOI: 10.1016/j.esr.2022.100836.
- Mäkipää R, Linkosalo T, Komarov A, Mäkelä A. 2015. Mitigation of climate change with biomass harvesting in Norway spruce stands: are harvesting practices carbon neutral? *Canadian J For Res* 45 (2): 217-225. DOI:10.1139/cjfr-2014-0120.
- Mancini M, Rinnan Å. 2021. Near infrared technique as a tool for the rapid assessment of waste wood quality for energy applications. *Renew Energy* 177: 113-123. DOI: 10.1016/j.renene.2021.05.137.
- Mola-Yudego B, Arevalo J, Díaz-Yáñez O, Dimitriou I, Freshwater E, Haapala A, Khanam T, Selkimäki M. 2017. Reviewing wood biomass potentials for energy in Europe: the role of forests and fast-growing plantations. *Biofuels* 8 (4): 401-410. DOI: 10.1080/17597269.2016.1271627.
- Mori S, Sumner J, Bouvet J, Simms NJ. 2022. Fireside and steamside performance in biomass power plant. *Mater High Temp* 39 (2): 106-121. DOI:10.1080/09603409.2021.2019657.
- Moya R, Tenorio C, Oporto G. 2019. Short rotation wood crops in Latin America: A review on status and potential uses as biofuel. *Energies* 12 (4): 705. DOI:10.3390/en12040705.
- Mukhdlor A, Haqiqi MT, Tirkaamiana MT, Suwinarti W, Amirta R. 2021. Assessment of wood biomass productivity from *Anthocephalus macrophyllus* forest plantation. *Adv Biol Sci Res*. DOI: 10.2991/abstr.k.210408.005.
- Mutezo G, Mulopo J. 2021. A review of Africa's transition from fossil fuels to renewable energy using circular economy principles. *Renew Sustain Energy Rev* 137: 110609. DOI: 10.1016/j.rser.2020.110609.
- Narnaware SL, Panwar NL. 2022. Biomass gasification for climate change mitigation and policy framework in India: A review. *Bioresour Technol Rep* 17: 100892. DOI:10.1016/j.biteb.2021.100892.
- Niemczyk M, Kaliszewski A, Jewiarz M, Wrobel M, Mudryk K. 2018. Productivity and biomass characteristics of selected poplar (*Populus spp.*) cultivars under the climatic conditions of northern Poland. *Biomass Bioenergy*, 111: 46-51. DOI: 10.1016/j.biombioe.2018.02.002.
- Nimmanterdwong P, Chalermisinsuan B, Piumsombon P. 2021. Prediction of lignocellulosic biomass structural components from ultimate/proximate analysis. *Energy* 222: 119945. DOI: 10.1016/j.energy.2021.119945.
- Nugraha HW, Djajakirana G, Anwar S, Santosa DA. 2020. Producing renewable electricity through a microbial fuel cell in the rice field. *Biodiversitas* 21 (9): 4139-4146. DOI: 10.13057/biodiv/d210927.
- Parikh L, Channiwala SA, Ghosal GK. 2007. A correlation for calculating elemental composition from proximate analysis of biomass materials. *Fuel* 86: 1710-1719. DOI:10.1016/j.fuel.2006.12.029.
- Pérez S, Renedo CJ, Ortiz A, Delgado F, Fernández I. 2014. Energy potential of native shrub species in northern Spain. *Renew Energy* 62: 79-83. DOI: 10.1016/j.renene.2013.06.048.
- Pérez S, Renedo CJ, Ortiz A, Manáña M. 2008. Energy potential of waste from 10 forest species in the North of Spain (Cantabria). *Bioresour Technol* 99: 6339-6345. DOI: 10.1016/j.biortech.2007.12.014.
- Pio D, D'Cruz R. 2005. Borneo's Lost World: Newly Discovered Species on Borneo. WWF, Jakarta.
- Präger F, Paczkowski S, Sailer G, Derkyi NSA, Pelz S. 2019. Biomass sources for a sustainable energy supply in Ghana-A case study for Sunyani. *Renew Sustain Energy Rev* 107: 413-424. DOI: 10.1016/j.rser.2019.03.016.
- Proto AR, Palma A, Paris E, Papandrea SF, Vincenti B, Carnevale M, Guerriero E, Bonofiglio R, Gallucci F. 2021. Assessment of wood chip combustion and emission behavior of different agricultural biomasses. *Fuel* 289: 119758. DOI:10.1016/j.fuel.2020.119758.
- Ram M, Child M, Aghahosseini A, Bogdanov D, Lohrmann A, Breyer C. 2018. A comparative analysis of electricity generation costs from renewable, fossil fuel, and nuclear sources in G20 countries for the period 2015-2030. *J Clean Prod* 199: 687-704. DOI: 10.1016/j.jclepro.2018.07.159.
- Rempel A, Gupta J. 2020. Conflicting commitments? Examining pension funds, fossil fuel assets, and climate policy in the organisation for economic co-operation and development (OECD). *Energy Res Soc Sci* 69: 101736. DOI: 10.1016/j.erss.2020.101736.
- Rincon L, Puri M, Kojakovic A, Maltsoğlu I. 2019. The contribution of sustainable bioenergy to renewable electricity generation in Turkey: Evidence based policy from an integrated energy and agriculture approach. *Energy Pol* 130: 69-88. DOI: 10.1016/j.enpol.2019.03.024.
- Samal B, Vanapalli KR, Dubey BK, Bhattacharya J, Chandra S, Medha I. 2021. Influence of process parameters on thermal characteristics of char from co-pyrolysis of eucalyptus biomass and polystyrene: Its prospects as a solid fuel. *Energy* 232: 121050. DOI:10.1016/j.energy.2021.12.1050.
- Shao Y, Xu C, Zhu J, Preto F, Wang J, Li H, Badour C. 2011. Ash deposition in co-firing three-fuel blends consisting of woody biomass, peat, and lignite in a pilot-scale fluidized-bed reactor. *Energy Fuels* 25 (7): 2841-2849. DOI: 10.1021/ef2002603.
- Simangunsong BCH, Sitanggang VJ, Manurung EGT, Rahmadi A, Moore GA, Aye L, Tambunan AH. 2017. Potential forest biomass resource as feedstock for bioenergy and its economic value in Indonesia. *For Policy Econ* 81: 10-17. DOI: 10.1016/j.forpol.2017.03.022.
- Telmo C, Lousada J, Moreira N. 2010. Proximate analysis, backwards stepwise regression between gross calorific value, ultimate and chemical analysis of wood. *Bioresour Technol* 101 (11): 3808-3815. DOI:10.1016/j.biortech.2010.01.021.
- Tenorio C, Moya R, Filho MT, Valaert J. 2015. Quality of pellets made from agricultural and forestry crops in Costa Rican tropical climates. *Bioresources* 10 (1): 482-498.
- Tursunov O, Abduganiev N. 2020. A comprehensive study on municipal solid waste characteristics for green energy recovery in Urt-Chirchik: A case study of Tashkent region. *Mater Today: Proc* 25: 67-71. DOI: 10.1016/j.matpr.2019.11.108.
- Vega LY, López L, Valdés CF, Chejne F. 2019. Assessment of energy potential of wood industry wastes through thermochemical conversions. *Waste Manag* 87: 108-118. DOI: 10.1016/j.wasman.2019.01.048.
- Wang Z, Bui Q, Zhang B, Pham TLH. 2020. Biomass energy production and its impacts on the ecological footprint: An investigation of the G7 countries. *Sci Total Environ* 743: 140741. DOI:10.1016/j.scitotenv.2020.140741.
- Yuliansyah, Amirta R. 2016. Physico-chemical properties and energy potency of wood waste biomass from logging activities to generate electricity in East Kalimantan, Indonesia. AIP Conference Proceeding. DOI: 10.1063/1.4958476.
- Yuliansyah, Haqiqi MT, Septia E, Mujiastih D, Helmi AS, Setiawan KA, Setiyono B, Angi EM, Saparwadi, Sari NM, Kusuma IW, Rujehan, Suwinarti W, Amirta R. 2019. Diversity of plant species growing during fallow period of shifting cultivation and potential of its biomass for sustainable energy production in Mahakam Ulu, East Kalimantan, Indonesia. *Biodiversitas* 20 (8): 2236-2242. DOI: 10.13057/biodiv/d200818.

# Fast-growing native tree species to the secondary forest of East Kalimantan, Indonesia: Physicochemical properties of woody materials for bioelectricity feedstocks

## ORIGINALITY REPORT

13%

SIMILARITY INDEX

11%

INTERNET SOURCES

9%

PUBLICATIONS

6%

STUDENT PAPERS

## PRIMARY SOURCES

1

[link.springer.com](https://link.springer.com)

Internet Source

1%

2

Submitted to SDM Universitas Gadjah Mada

Student Paper

1%

3

[agronomy.emu.ee](https://agronomy.emu.ee)

Internet Source

1%

4

[politanisamarinda.ac.id](https://politanisamarinda.ac.id)

Internet Source

1%

5

[www.frontiersin.org](https://www.frontiersin.org)

Internet Source

1%

6

[pure.ulster.ac.uk](https://pure.ulster.ac.uk)

Internet Source

1%

7

Submitted to Universitas Airlangga

Student Paper

1%

8

Dorin Maier. "The use of wood waste from construction and demolition to produce sustainable bioenergy—a bibliometric review"

1%

of the literature", International Journal of  
Energy Research, 2022

Publication

9

Submitted to Program Pascasarjana  
Universitas Negeri Yogyakarta

Student Paper

1 %

10

Submitted to RMIT University

Student Paper

<1 %

11

Anika Seppelt, Juan Alberto Molina Valero,  
César Pérez-Cruzado, Nieves Barros.

"Thermodynamic characterization of LF, H,  
and mineral soil layers from oak forest  
ecosystems: Exploring the role of proximate  
analysis", Environmental Research, 2023

Publication

<1 %

12

core.ac.uk

Internet Source

<1 %

13

report.ipcc.ch

Internet Source

<1 %

14

João Cardoso, Valter Silva, Daniela Eusébio.

"Techno-economic analysis of a biomass  
gasification power plant dealing with forestry  
residues blends for electricity production in  
Portugal", Journal of Cleaner Production, 2019

Publication

<1 %

15

biodiversitas.mipa.uns.ac.id

Internet Source

<1 %

|    |                                                                                                                                                                                                                                                                                                         |      |
|----|---------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------|------|
| 16 | <a href="http://www.medecc.org">www.medecc.org</a><br>Internet Source                                                                                                                                                                                                                                   | <1 % |
| 17 | <a href="http://www.tandfonline.com">www.tandfonline.com</a><br>Internet Source                                                                                                                                                                                                                         | <1 % |
| 18 | Submitted to Universitas Pendidikan Indonesia<br>Student Paper                                                                                                                                                                                                                                          | <1 % |
| 19 | Hariteja Nandimandalam, Veera Gnaneswar Gude, Mohammad Marufuzzaman.<br>"Environmental impact assessment of biomass supported electricity generation for sustainable rural energy systems - A case study of Grenada County, Mississippi, USA",<br>Science of The Total Environment, 2022<br>Publication | <1 % |
| 20 | <a href="http://worldwidescience.org">worldwidescience.org</a><br>Internet Source                                                                                                                                                                                                                       | <1 % |
| 21 | Huimin Liu, Yicheng Wang, Silan Zhao, Hongyun Hu, Chengyang Cao, Aijun Li, Yun Yu, Hong Yao. "Review on the Current Status of the Co-combustion Technology of Organic Solid Waste (OSW) and Coal in China", Energy & Fuels, 2020<br>Publication                                                         | <1 % |
| 22 | Zhaohua Wang, Quocviet Bui, Bin Zhang, Thi Le Hoa Pham. "Biomass energy production and its impacts on the ecological footprint: An                                                                                                                                                                      | <1 % |

# investigation of the G7 countries", Science of The Total Environment, 2020

Publication

23

[biosains.mipa.uns.ac.id](https://biosains.mipa.uns.ac.id)

Internet Source

<1 %

24

Galina Chebotareva, Wadim Strielkowski, Dalia Streimikiene. "Risk assessment in renewable energy projects: A case of Russia", Journal of Cleaner Production, 2020

Publication

<1 %

25

Okey Francis Obi, Kingsley Chukwudi Okongwu. "Characterization of fuel briquettes made from a blend of rice husk and palm oil mill sludge", Biomass Conversion and Biorefinery, 2016

Publication

<1 %

26

[beyond-coal.eu](https://beyond-coal.eu)

Internet Source

<1 %

27

[lutpub.lut.fi](https://lutpub.lut.fi)

Internet Source

<1 %

28

[pubmed.ncbi.nlm.nih.gov](https://pubmed.ncbi.nlm.nih.gov)

Internet Source

<1 %

29

[www.ncbi.nlm.nih.gov](https://www.ncbi.nlm.nih.gov)

Internet Source

<1 %

---

Exclude quotes      On

Exclude matches

< 10 words

Exclude bibliography      On