

Bionanomaterial from agricultural waste and its application

by Enih Rosamah

Submission date: 02-Aug-2021 01:40PM (UTC+0700)

Submission ID: 1626867486

File name: Bionanomaterial_from_agricultural_waste_and_its_application.pdf (25.21M)

Word count: 19790

Character count: 112078

Bionanomaterial from agricultural waste and its application

3

Rudi Dungani¹, Abdul Khalil H.P.S.², Nurjaman A. Sri Aprilia³, Ihak Sumardi¹, Pingkan Aditiawati¹, Atmawi Darwis¹, Tati Karliati¹, Aminudin Sulaeman¹, Enih Rosamah⁴ and Medyan Riza³

¹Institut Teknologi Bandung, Bandung, West Java, Indonesia ²University of Science, Malaysia, Penang, Malaysia ³Syiah Kuala University, Banda Aceh, Indonesia

⁴Mulawarman University, Samarinda, East Kalimantan, Indonesia

3.1 Introduction

Agricultural biomass refers to all the organic materials that are produced as by-products from agriculture activities, such as leaves, straws, husks, hulls, shells, and animal waste. Huge amounts of biomass are generated as by-products of agricultural (and wood) harvesting and processing activities every year, particularly in developing countries.

Agricultural biomass is the most abundant biomass found in nature. Its content in primary waste is about 30% [1], in forest biomass 40%–50% [2], secondary waste 65%–70% [3], and in industrial crops more than 90% [4]. Globally, biomass waste is produced and unutilized in million metric tonnes annually [5]. Of this enormous production, biomass waste is only a minor fraction of total biomass use for various applications in large-scale industries and community-level enterprises. Approximately 10% of agricultural biomass waste is converted to raw biomaterial to provide future materials to obtain products with higher performance [6]. Santhi et al. [7] investigated the sustainability and advancement in utilization of oil palm biomass for value-added products. They showed that only 10% of oil palm biomass is used as an alternative raw material for various applications such as reinforcing agents in composite materials, animal feed, fertilizer, chemical derivatives, and other applications.

In addition to the harvested crop itself, large quantities of wastes are generated in agricultural production systems. Industrial crops of kenaf, jute, abaca, ramie and other crops, and fruits such as coconut and oil palm generate considerable amounts of waste. These wastes constitute a major part of total annual production of biomass agricultural wastes and are an important source of biomaterial for industrial purposes.

Agricultural biomass is the most abundant resource and one that is also renewable. However, utilization of agricultural biomass has been based on the paradigm of a fossil resource-based society, and thus, it is critically important to establish a sustainable production and utilization system for agriculture resources, especially those in tropical regions where resources and biodiversity are plentiful. Therefore, it is becoming more and more important to establish sustainable and recycling-based societies dependent on renewable resources; otherwise, humankind cannot survive.

In addition, establishment of basic science and technology dealing with lignocellulosic materials, including agricultural waste, is indispensable to promotion of the composite industries of Southeastern Asian countries.

Plenty of waste is produced due to the increased activity in the modern agricultural sector, representing a tremendous threat to the environment. Meanwhile, a declining supply of raw material is cause for concern and in this context the natural fiber can be seen as a good alternative material for local timber industries to produce value-added products, such as biocomposites. Utilization of natural fiber, especially agricultural waste fiber, needs further development as a long-term strategy to develop the tremendous wealth of natural plant fiber that is currently underutilized. Agriculture waste can be obtained from plants such as oil palm, bagasse, corn stalks, coir, bamboo, pineapple, banana, as well as rice husk, and is extracted from different parts of the plant (stem, leaf, seed, fruit, stalk, and grass/reed) [8].

The renewable and biodegradable properties of cellulose found in agricultural waste offer biorefinery functions as cellulose fiber. Cellulose fiber itself is made from biomass-derived fiber that has been defibrated to the size level of several hundredths of a micron and smaller until nanometer-sized. Cellulose fibers exhibit a unique structural hierarchy derived from their biological origin. They are composed of nanofiber assemblies with a diameter that ranges from 2 to 20 nm, and a length of more than a few micrometers. Cellulose nanofibers (CNFs) have been proven to be a promising material for many fields, including high gas barrier packaging material, filter material, electronic devices, food, cosmetics, medicine, biocomposites, and health care, due to their morphology and physical properties.

Recent research on nanocellulose production uses cereal by-products such as wheat straw, soy hulls, soybean straw, sorghum fibers, and rice straw, as well as other crop residues such as cassava bagasse, banana stem, pineapple leaves, sugarcane bagasse, corn stalks, cornhusk, oil palm biomass, grape hulls, and orange bagasse. This biomass, the abundance of which is residue produced by agricultural industry, serves as the best biomaterial to obtain CNF. Study by Changsarn et al. [9] reported that CNF resulting from biomass presents a larger crystalline region and a higher specific surface area. These results suggested that this bionanomaterial is important for the development of nanocomposites for their applications. Furthermore, Lavoine et al. [10] and Durán et al. [11] considered that nanocomposites with CNF as filler enhance the barrier properties used for food packing.

On the other hand, the extremely rapid development of nanomaterials from biomass and the use of nanoparticles have received much attention as a viable alternative for the development of metal nanoparticles. Many attempts have been made to manufacture bionanoparticles, such as Adam et al. [12], Hata et al. [13], Dungani et al. [14], and Rosamah et al. [15]. They suggested that the potential of nanoparticles for filler/reinforcement in polymer composites is seen as highly promising, because bionanoparticles have marvelous and complex structures that are important in understanding their chemical applications.

In this chapter, first we will discuss the fundamental properties of different agriculture wastes as future materials. We will also concentrate our discussion on

technologies to produce bionanomaterials, and their use in polymer nanocomposites. After that, types of bionanomaterials such as nanocellulose and nanoparticles will be highlighted. At the end, some points regarding production of nanocomposites and their applications for various purposes will be discussed.

3.2 Overview of waste as green potential from biomass

Biomass is an essential part of the renewable portfolio; unlike other sources of renewables, it can be used as biomaterial for various biocomposite products [16–20]. The biomass itself is derived from three principal sources: agricultural products, forestry waste, and biogenic waste. In general agricultural products consist of oil- and sugar-containing plants; forestry products consist of wood, bark, branches, and stumps; while biogenic waste is derived from the agricultural, commercial, and household sectors. Furthermore, these sources of biomass exist in three forms: gaseous, solid, and liquid.

Recent advances in biomass waste development, conversion process technologies, and their products offer significant opportunities for an exploration and development of improved materials from these renewable resources. The major conversion technologies, such as twining, decortication, and tuxying, convert biomass waste to materials and their products such as biocomposites, pulp and paper, automotive, medical, packaging, construction, aerospace, marine, electronics, pharmaceutical, and biomass energy production [21].

Rapid increase in volume and types of agricultural biomass waste, as a result of intensive agriculture in the wake of population growth and improved living standards, is becoming a burgeoning problem. Furthermore, this waste is of high value with respect to material and energy recovery. Billions of tons of agro products are produced each year, of which the waste has potential for biomaterial resources (e.g., fibers). Assuming that 40% of the production is available as waste [23] and at least 10% of the waste by weight can be obtained as fiber, millions of metric tons of fibers are available every year and the amount will increase annually. Table 3.2 shows the annual biomass-based natural fiber production from various sources.

Since the biocomposites market is growing rapidly, it becomes urgent to design superior strength biocomposites to exploit in particular applications. These wastes could be potential resources for reinforcing materials in biocomposite applications. The utilization of such resources will not only provide sustainable and less expensive material but will also contribute to waste disposal management as well as overcoming environmental problems. However, the agricultural waste fiber is classified as non-wood fiber moderate quality [4]. In addition, its lack of good interfacial adhesion and hydrophilic nature have made its usage difficult [26]. Therefore, good understanding of the fundamental properties of agricultural waste fiber including its modification technologies are indispensable. Several treatment and modification processes can be applied to change its hydrophilic nature to hydrophobic in order to overcome the above-mentioned problems [27].

Table 3.1 Cellulosic biomass waste conversion to materials and their products

Biomass waste	Products
Pineapple leaves, sugarcane residues	Animal feed, industrial absorbents, additives for beverages and biocomposites
Wheat straw	Wheat straw PP pelletized feedstock, fertilizer, biocomposites
Rice husk	Silica, metal finishing, water soluble oil and synthetic lubricant
Sugarcane bagasse	Lumber materials, biocomposites, paper and packaging materials, paper wares
Abaca leaves	Fiber craft, cordage, textile and fabrics, pulp, and specialty papers
Coconut husk	Coconut fiber rope and twine, brooms and brushes, doormats, rugs, mattresses and upholstery, often in rubberized coir pads
Sugar mill boiler ash from bagasse	Filtration materials and absorbent products
Oil palm fruit residues	Biodegradable packaging materials, construction, pulp and paper, automotive components
Kenaf fibers, jute fiber	Soundproofing systems, thermal insulators, automotive components, electronics, pharmaceutical
Abaca leaves	Abaca leaf sheath, aerospace, marine, and electronics
Coconut coir	Coconut twines
Banana stem	Banana fiber, biocomposites, pulp and paper
Flax	Biodegradable bags and covers, energy sports equipment

3.3 Fundamental properties of various agriculture waste

Most basic of all in selecting agricultural waste is the characteristics of the fibers, i.e., the various properties by which a fiber may be evaluated. Physical, mechanical, and chemical properties of various agricultural waste-based fiber were examined to assess their suitability for various future applications. These fundamental properties will not only help in opening up a new avenue for these fibers, but also emphasize the importance of natural fibers from agricultural waste as future biomaterial. The following summarizes the properties of agricultural waste-based fiber and gives the specifics of these properties for each fiber source.

3.3.1 Types of agriculture waste

When managed on a sustainable basis, biomaterials available in primary products from industrial crop and agriculture wastes form an abundant, local, and environmentally

Table 3.2 Annual production of biomass-based natural fibers and sources

Fiber source	World production (10 ³ Tons)	Origin
Bamboo	10,000	Stem
Oil palm fruit	23,500	Fruit
Sugarcane bagasse	75,000	Stem
Banana	200	Fruit
Coir	100	Stem
Wood	1,750,000	Stem
Pineapple	1200	Leaf
Rice straw	28,900	Stem
Rice husk	26,750	Fruit/grain
Jute	2500	Stem
Kenaf	770	Stem
Flax	810	Stem
Sisal	380	Stem
Abaca	70	Stem
Kapok	100	Stem

Sources: From Taj SM, Munawar A, Khan SU. Natural fiber-reinforced polymer composites. Proc Pak Acad Sci 2007;44(2):129–44 [22]; John MJ, Thomas S. Biofibres and biocomposites. Carbohydr Polym 2008;71(3):343–64 [23]; Hambali E, Thahar E, Komarudin A. The potential of oil palm and rice biomass as bioenergy feedstock. In: 17th Biomass Asia Workshop; 2010 [24]; Faruk O, Bledzki AK, Fink HP, Sain M. Biocomposites reinforced with natural fibers: 2000–2010. Prog Polym Sci 2012;37(11):1552–96 [25].

friendly source of raw materials. In addition, the use of agricultural waste biomaterials for component material of composites contributes to income and employment in developing countries [28]. The ambitious policy developments combined with other associated benefits has led to a large increase in the use of agricultural biomaterials for biocomposite products in many countries (European, Australia, and American) [23].

There are many different types of biomaterials based on agricultural biomass. Industrial crops are crops that have the potential to yield a wide range of products. Crops produce filamentous matter from the bast tissue or other parts of plants, and are processed to be used for industrial purposes. There are a number of different industries and products including bioenergy [29], industrial oil and starch [30], fiber [31], and rubber and related compounds [32]. Primary wastes are obtained directly from the agriculture operations, whereas secondary wastes are obtained as by-products of the industrial processes associated with agriculture products. Other sources of agricultural-based biomaterials include kenaf, jute, and tertiary wastes, which consist mainly of the palm oil industry. Forest biomass consists of woody materials generated by industrial processes (timber industries in particular) such as wood chips, bark,

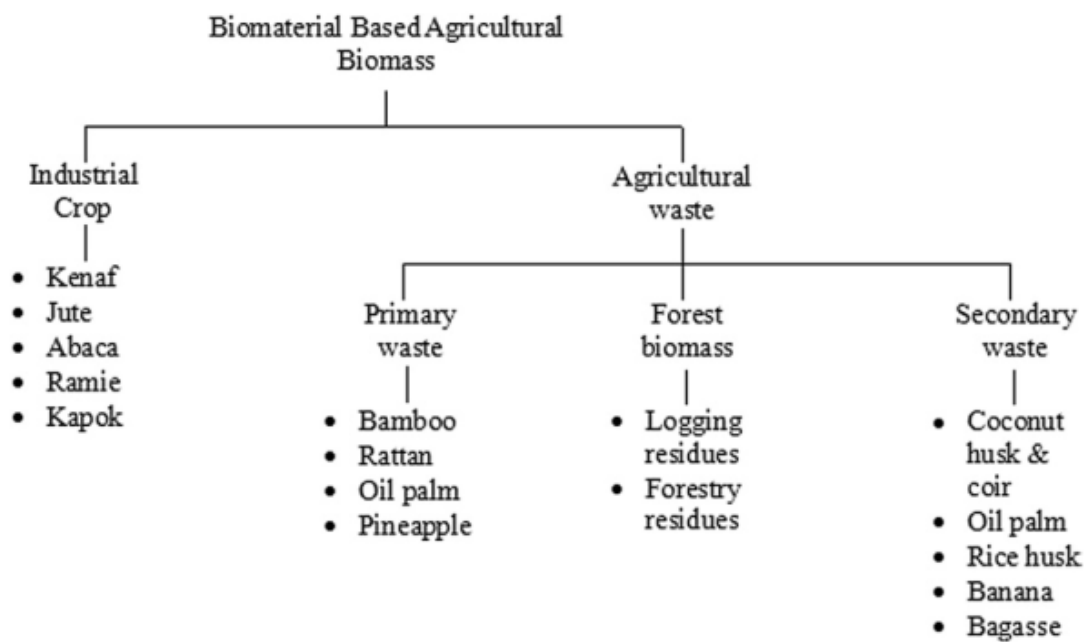


Figure 3.1 Classification of biomaterial-based agricultural biomass.

sawdust, shavings, chips, etc., or directly by logging residue (tree tops, branches, small stems, and deadwood). The use of forest biomass from forestry residues such as wood chips, bark, sawdust, timber slash, and mill scrap for biomaterial contributes to raw material of biocomposites such as particleboard, oriented strand board, and fiberboard [33,34].

At present, the largest share of biomaterial from agriculture comes from secondary wastes from the agricultural industries, namely, the coconut, coir, and oil palm industries. In this context, the use of industrial crop production is not enough for biomaterials; in secondary wastes, it represents a great potential source of raw material to increase the use of agricultural biomass for various applications, independent of the large industrial processes [18,19,35]. Finally, biomass, which includes plant species and agricultural waste, is another source of biomaterial, and its contribution to the sustainability of raw materials is expected to increase in the future [36]. The classification of agricultural biomass as biomaterial for biocomposite components according to their origin is presented in Fig. 3.1.

Type of agriculture waste includes residues from fruit, leaf, seed shells, grass, stalks or trunk, bast and straw, and waste wood. Fig. 3.2 shows the classification of agricultural waste forms based on conversion of cellulosic biomass waste to biomaterials and their products. The figure illustrates the great potential of agricultural waste for conversion to a variety of biomaterials.

3.3.2 Structure and chemical composition

This part deals with the structure and chemical composition of biomass-based natural fibers. Natural fibers' cell structures are basically the same, consisting of a primary

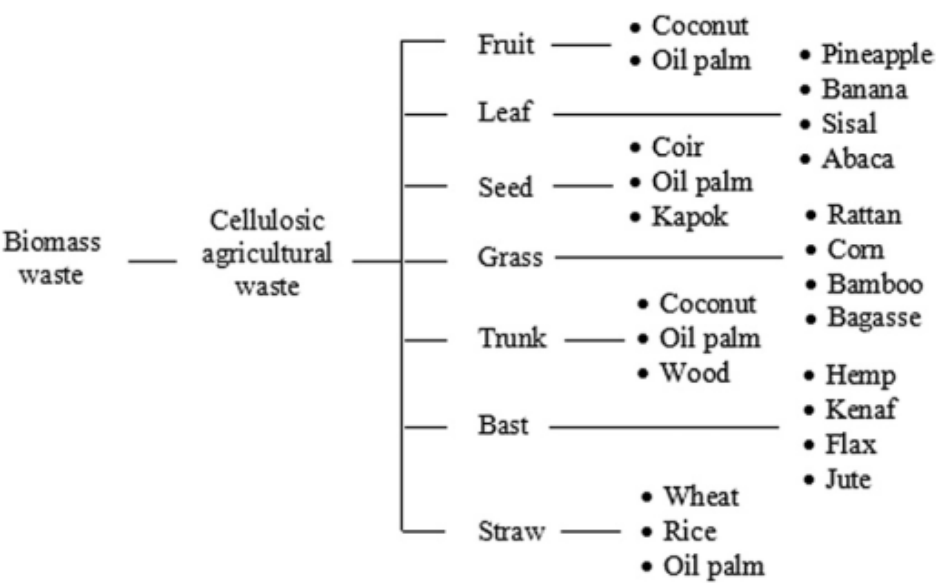


Figure 3.2 Classification of agricultural waste as a biomaterial.

and secondary cell wall, lumen, and middle lamella [37]. The secondary wall consists of three layers (S1, S2, and S3) and determines the mechanical properties of the fibers [38]. Each fiber bundle contains individual fiber cells or filaments, and is made of cellulose and hemicellulose, bonded together by lignin or pectin. Cellulose is a skeletal component in all plants and these polymers are organized in a cellular hierarchical structure. The primary structural component of cellulose cell walls contains many polar hydroxyl groups, which allow them to interact with adjacent molecules to form fibers. The fibers are structurally strong and resistant to chemical attack, so biomass products are widely used in various applications. Hemicellulose is similar in structure to cellulose, and is believed to be a compatibilizer between cellulose and lignin [39]. Lignin polymers are often found in most cell structures in association with cellulose; it is primarily hydrocarbon in nature and makes up a major portion of insoluble fiber.

The importance of biomaterials' fiber dimensions (length, width, thickness, and lumen width) on the physical and mechanical properties of products is well documented. Basiji et al. [40] have shown that, under certain conditions, impact strength and modulus of rupture in wood–plastic (polypropylene, PP) composites depends strongly on fiber length, whereas Singh and Samanta [41] report that increase in raw material fiber length enhances the mechanical properties of the natural fiber-reinforced composites. Using image analysis, Fidelis et al. [42] also found that the highest mechanical performance with tensile strength and Young's modulus in sisal and jute fibers could be accounted for by size of the cell walls and the real area of the fibers. Ghasemi et al. [43] have also suggested that the fiber cell wall thickness is an important parameter for biomass fibers to have excellent mechanical properties.

The revealing of cell structure and chemical composition of cellulosic fibers is important for assessing the suitability of various biomass fiber raw materials and ultimately can be useful in various applications of new biomaterials. In an extensive

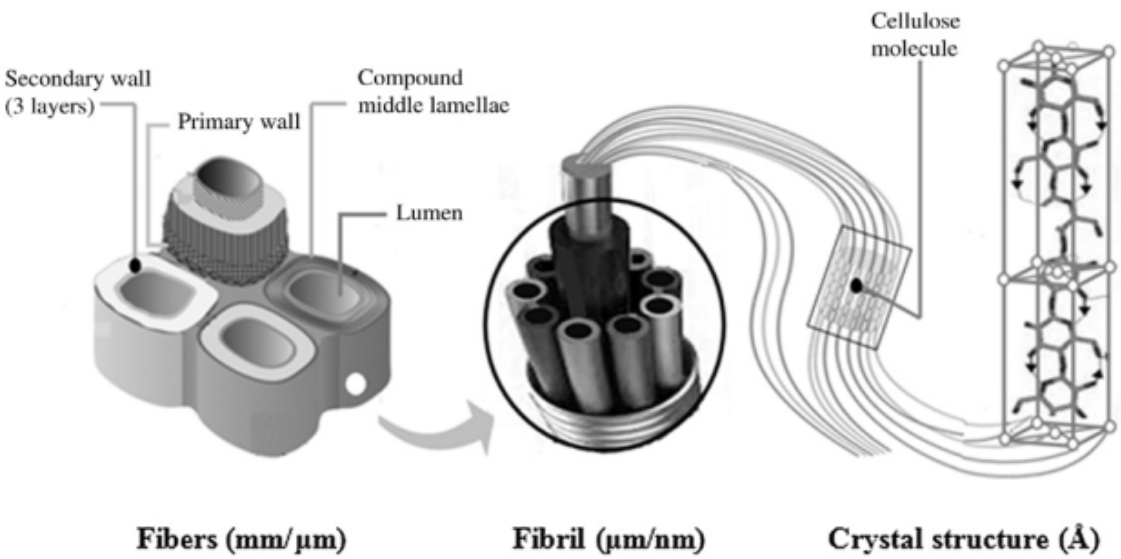


Figure 3.3 Model of cell structure of biomass-based natural fibers.

review of the literature, Abdul Khalil et al. [44] stressed that fibers have a wide range of variations in their properties, depending on various sources such as soil, genotype, climate, and agronomic practice. Moreover, Dittenber and Gangarao [45] investigated various factors affecting the fiber quality, such as plant growth, harvesting stage, and fiber extraction process. Norton et al. [46] suggested that chemical composition and cell structure of biomass fibers could be caused by soil component.

According to Rowell et al. [47], differences in cell structure in the biomass fiber will result in differences in physical properties. They reported that the physical properties of biomass fiber will be different because of differences in its morphology. A detailed overview of the morphological structure of biomass fiber by scanning electron microscopy (SEM) observation in this chapter will be useful to others in investigating fiber type [6].

Extraction is the process that separates the major components of biomass and converts it into fiber, lignin, and sugars for others to process into value-added products. This process separates the primary constituents of cellulosic biomass into three components (cellulose, hemicellulose, and lignin). This continuous process employs a cellulose extraction technique that removes lignin, resulting in a solid fraction containing a relatively pure cellulose or fiber.

Due to their main chemical composition, biomass fibers are also called [20]ulose or lignocellulosic fibers. Those constituents are scattered throughout the cell wall, which consists of a primary and secondary wall. The portion of these chemicals in the cell wall layer is affected by the fiber origin, climate condition during cultivation, and the extraction method [46,48], and influences the fiber properties chemically and physically [49,50].

The bagasse fiber bundles shown in Fig. 3.4 were mechanically separated from sugarcane stem residue. Fig. 3.4 shows the surface roughness from the raw fiber state. According to Hemmasi et al. [51], Satyanarayana et al. [52], and Driemeier et al. [53], the diameter of bagasse fibers ranges from 10.10 to 34.21 μm. The cell wall thickness

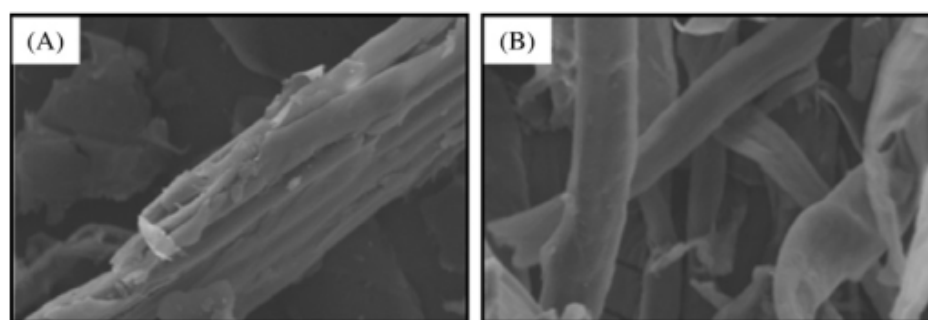


Figure 3.4 Scanning electron micrograph of morphological bagasse fiber: (A) raw material; (B) fibers after combined hydrothermal and alkaline pretreatment.

Source: From Guilherme A, Dantas PVF, Santos ES, Fernandes FAN, Macedo GR.

Evaluation of composition, characterization and enzymatic hydrolysis of pretreated sugar cane bagasse. *Braz J Chem Eng* 2015;32(01):23–33 [54].

is reported to range from 4.85 to 5.64 μm . The cross-sections show fiber forms, with length of fibers ranging from 1.54 to 5.84 mm.

The percentage of chemical composition in bagasse fibers indicated a cellulose content of 32.33%–48.49%, which was higher than hemicellulose content of 19.25%–24.44%, while the whole bagasse contained lignin and ash at 17.3%–26.5% and 1.54%–5.35%, respectively [54,55].

In the longitudinal sections, the fiber bundles of rice straw have clean surface after the alkali and enzyme treatments [56]. There is still a great variety in shape and size of the bundles, as shown in the cross-sectional views. The fiber length ranges from 0.55 to 0.57 mm [57]. Fiber width and cell wall thickness range from 6.75 to 9.45 μm and 4.55 to 5.64 μm , respectively [58].

Rice straw ranges from 38.72% to 40.74% cellulose, 25.34% to 26.20% hemicellulose, 12.62% to 14.24% lignin, and about 16.33% to 16.99% ash [59,60]. Reddy and Yang [58] investigated fiber potential of rice straw, and reported that the cellulosic fiber formed by using alkali and enzyme treatment produced about 50% high-quality fibers.

Fig. 3.5 shows that pineapple fiber cross-section has a rougher structure, compact surface, and many fiber matrices [61]. Mishra et al. [62] investigated the microstructure of pineapple fiber through surface modifications by alkali treatment. They showed that these form fibers irregular cross section. Moya et al. [63] reported fiber diameter of 4.38–7.56 μm and a fiber length of 3.34–4.64 mm. Fig. 3.6 shows cell wall thickness in a range of ca. 1.46–2.30 μm [61,64].

Chemical constituents of pineapple fiber are composed of three main categories: cellulose (66.2%–74.3%), hemicellulose (19.5%–21.22%), and lignin (4.2%–10.5%), with some other small quantities (ash) at 2.0%–4.73% [61,65,66].

Fig. 3.6 shows coir fibers extracted from a coconut's outermost husk. These fibers have length ranging from 0.30 to 1.00 mm. The SEM image cross-sections reveal that the diameters and the wall thickness of the coir fiber cells exhibited variations from 8.90 to 19.33 μm and from 4.24 to 12.63 μm , respectively [35,52,67]. Based on Fig. 3.7,

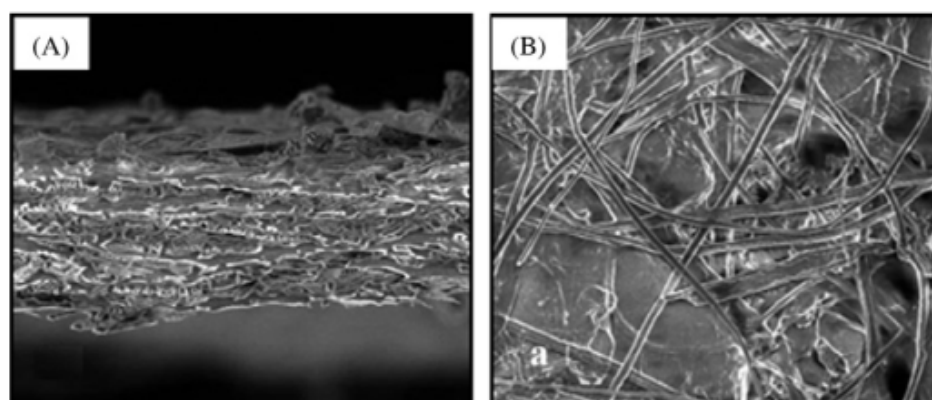


Figure 3.5 Scanning electron micrograph of morphological pineapple fiber: (A) cross-section image; (b) surface morphology.

Source: From Daud Z, Mohd Hatta MZ, Mohd Kassim AS, Awang H, Mohd Aripin A. Exploring of agro waste (pineapple leaf, corn stalk, and napier grass) by chemical composition and morphological study. *BioResources* 2014;9(1):872–80 [61].

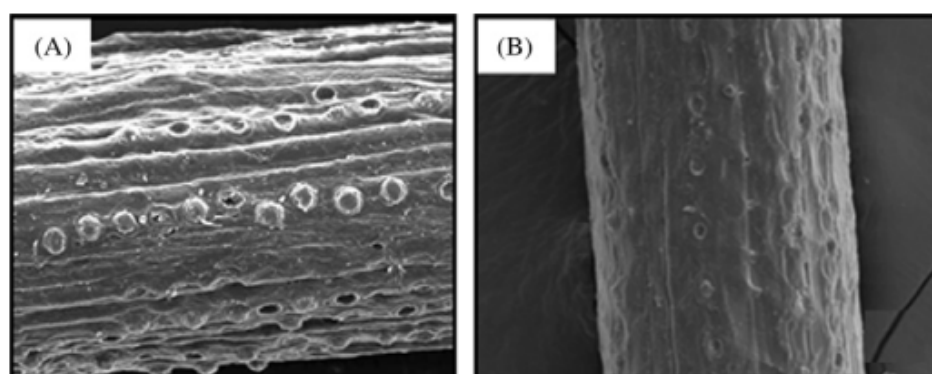


Figure 3.6 Scanning electron micrograph of morphological coir fiber: (A) raw material; (B) coir fiber–NaClO₂ treated fiber.

Source: From Muensri P, Kunanopparat T, Menut P, Siri wattanayotin S. Effect of lignin removal on the properties of coconut coir fiber/wheat gluten biocomposite. *Composites Part A* 2011;42:173–9 [72].

Arsène et al. [68] suggested that coir has a high lignin content, which helps make it resistant to burning [69], microbial attack [70], and moisture uptake/swelling [71].

Amount of cellulose in the coir was about 20.02%–22.90%, while hemicelluloses, lignin, and ash content were about 10.02%–14.70%, 44.75%–48.21%, and 1.00%–1.103%, respectively [68,73].

Banar² fiber is a multiple-celled structure (Fig. 3.7). These fibers has large lumens, rare and fiber tips pointed and flat, ribbon like individual. In Fig. 3.8, banana fibers appeared to be quite parallel, with cell wall thickness whose size ranges from 1.12 to 1.57 μm [74]. The banana fibers were embedded in each bundle (Fig. 3.7); the diameter of those fibers was approximately 20.70–23.70 μm and fiber length ranged from 1.26 to 2.54 mm [52,58,75].

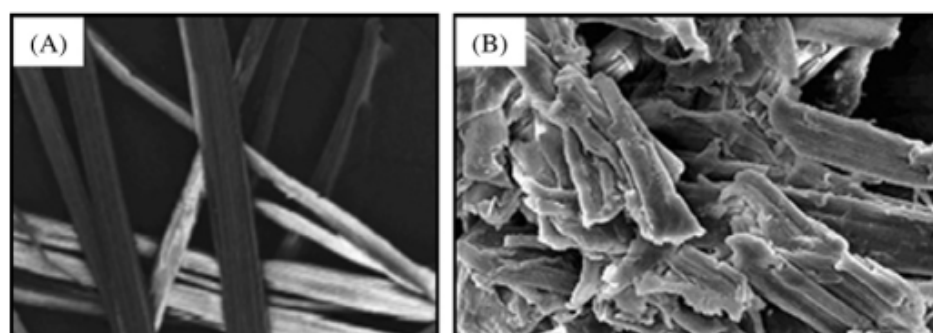


Figure 3.7 Scanning electron micrograph of morphological banana fiber: (A) raw material; (B) bleached banana fiber.

Source: From Deepa B, Abraham E, Cherian BM, Bismarck A, Blaker JJ, Pothan LA, et al. Structure, morphology and thermal characteristics of banana nano fibers obtained by steam explosion. *Bioresour Technol* 2011;102:1988–97 [77].

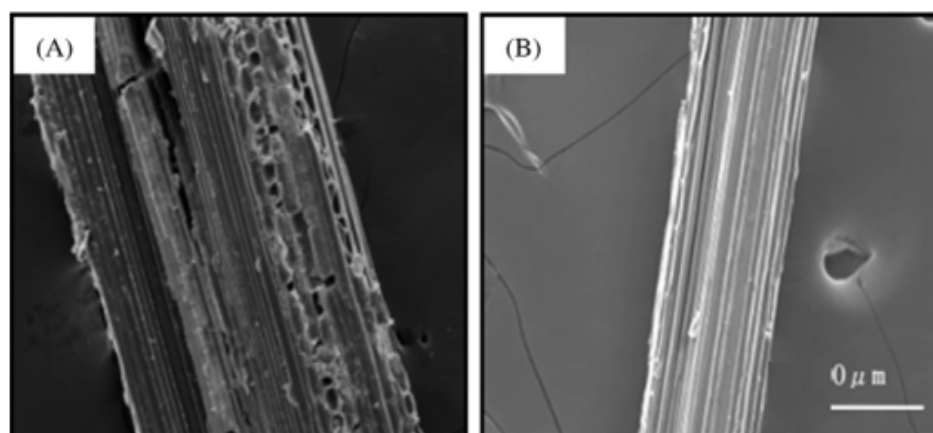


Figure 3.8 Scanning electron micrograph of morphological bamboo fiber: (A) raw material; (B) alkaline-treated fiber.

Source: From Phong NT, Fujii T, Chuong B, Okubo K. Study on how to effectively extract bamboo fibers from raw bamboo and wastewater treatment. *J Mater Sci Res* 2012;1(1): 144–55 [83].

Bilba et al. [76] characterized the chemical composition of banana. They reported that cellulose showed the highest value (27.87%–35.09%), followed by hemicellulose (12.95%–17.01%) and lignin (14.41%–15.73%). Ash content showed that the lowest value was about 8.62%–8.68% [68].

Fig. 3.8 shows a cross-sectional micrograph of a phloem fiber cap in a vascular bundle of a bamboo culm. It can be seen that the outer culm wall has high bending stiffness and strength [78]. Fig. 3.8 shows that these fibers are approximately 12.91–42.32 μm in diameter [79]. The length value of the fibers is 2.98–5.63 mm and cell wall thickness was obtained from 2.41 to 13.32 μm [80–82].

The investigations by Li et al. [84], Wang et al. [85], and Shibata [79] showed that the chemical composition of vascular bundles of a bamboo culm with cellulose,

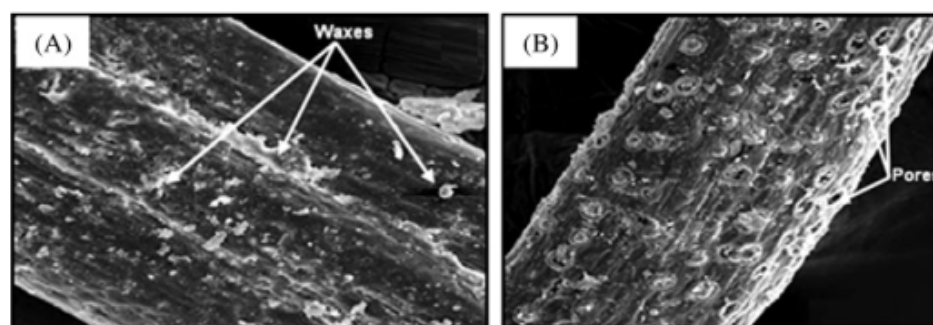


Figure 3.9 Scanning electron micrograph of morphological oil palm fiber: (A) raw material; (B) NaOH-treated.

Source: From Then YY, Ibrahim NA, Zainuddin N, Ariffin H, Md. Zin Wan Yunus W, Chieng BW. Static mechanical, interfacial, and water absorption behaviors of alkali treated oil palm mesocarp fiber reinforced poly(butylene succinate) biocomposite. *BioResources* 2015;10(1):123–36 [89].

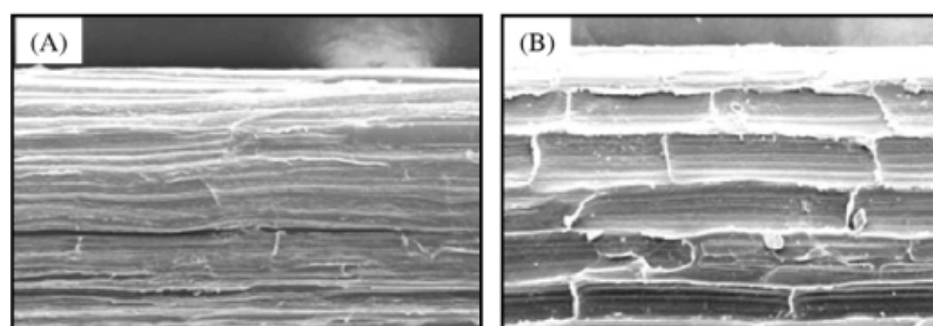


Figure 3.10 Scanning electron micrograph of morphological sisal fiber: (A) fiber surface images; (B) acetylated sisal fibers.

Source: From Fávoro SL, Ganzerli TA, de Carvalho Neto AGV, da Silva ORRF, Radovanovic E. Chemical, morphological and mechanical analysis of sisal fiber-reinforced recycled high-density polyethylene composites. *eXPRESS Polym Lett* 2010;4(8):465–73 [92].

hemicellulose, and lignin as the major components comprising about 20.3%–61.5%, 19.3%–21.4%, and 11.1%–32.2%, respectively. They also mentioned that ash content was 1.7%–5.1%.

As can be seen in Fig. 3.9, the cross-section of oil palm fiber is oval and fairly uniform in dimension. It contains various sizes of dimension such as length fiber of range from 0.33 to 50.31 mm, with fiber diameter and wall thickness of fiber cells varying between 8.30 and 20.50 μm and 2.83 and 4.35 μm , respectively [63,86,87]. The surface of oil palm fiber, shown in Fig. 3.10B, was relatively porous and rough; these fibers have silica-like bodies with rounded shape [88]. Abdul Khalil et al. [75] and Law et al. [88] suggested that the chemical composition of the oil palm varied. Cellulose, hemicellulose, and lignin contents were 14.3%–65.2%, 12.5%–38.7%, and 17.3%–26.5%, respectively.

The length of sisal fiber is between 0.85 and 1.00 mm and the diameter is about 100–300 μm , with wall thickness of fiber cells between 11.25 and 12.50 μm [90,91].

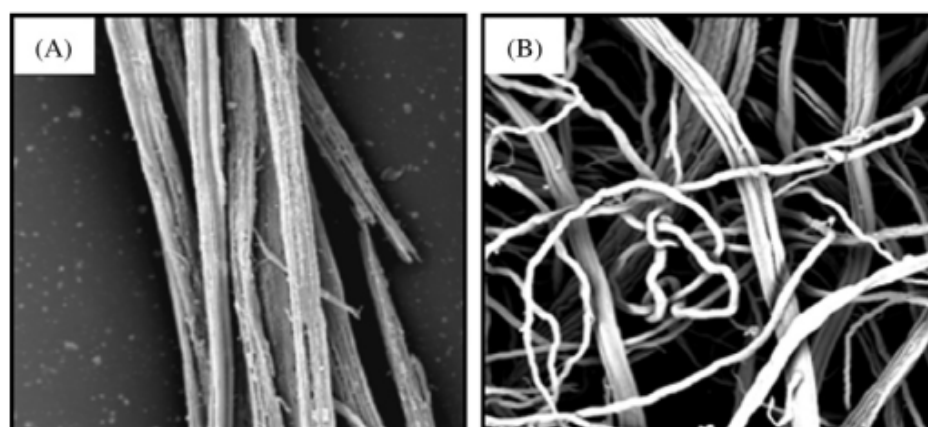


Figure 3.11 Scanning electron micrograph of morphological jute fiber: (A) raw material; (B) alkali-treated.

Source: From Baheti VK, Abbasi R, Militky J. Ball milling of jute fibre wastes to prepare nanocellulose. *World J Eng* 2012;9(1):45–50 [94].

In principle, sisal fibers have considerable surface roughness (Fig. 3.10) and are microstructurally heterogeneous. The sisal showed the presence of cellulose, hemicellulose, and lignin with 43.85%–63%, 21.12%–24.53%, and 7.21%–9.20%, respectively. This, to a great extent, is in agreement with investigation reported by Fávora et al. [92].

The surface morphology of jute fibers depended on their thickness, which was due to variation in fiber maturity [93]. The pores and voids could be decreased in number on the top portion of the fiber surface as compared to the surfaces of the middle and cutting portions. Jute fibers presented few fiber cells; cell wall thickness was 2.5 μm [42], diameter of lumens 60.00–110.00 μm ; and fiber length 3.00–3.50 mm [90] (Fig. 3.11).

According Mwaikambo [95], the presence of cellulose and hemicellulose in the raw jute was 69.21%–72.35% and 12.55%–13.65%, respectively. Lignin, the major element present, was quite higher, at 12.67%–13.21% [94].

Fig. 3.12 shows abaca fibers. In the cross-section of the fiber bundle shown in Fig. 3.12A, there is a large lumen in the center of every cell. Fig. 3.12B shows that the surface of abaca fiber bundles is composed of polygonal cells of 18.56–21.69 μm in diameter with a cell wall thickness of 4.07–5.11 μm [96]. The fiber length as shown in Fig. 3.14B is 4.14–5.05 mm [97].

Cellulose and hemicellulose are the most essential chemical components found in lignocellulosic materials such as abaca. This was demonstrated by Del Rio and Gutierrez [99] using energy-dispersive X-ray spectroscopy, which showed cellulose and hemicellulose contents as 69.23%–70.64% and 21.22%–21.97%, respectively. Other researchers reported that abaca contains lignin up to 5.87% [99,100].

The morphology of kapok fibers shows a hollow structure with a thin fiber wall and large lumen (Fig. 3.13A). These fibers have width, lumen diameter, cell wall thickness, and fiber length of 8.14–10.90, 12.10–16.90, 0.80–1.00, and 20–30 μm , respectively [101,102]. In their application, these fibers are good for stuffing beds,

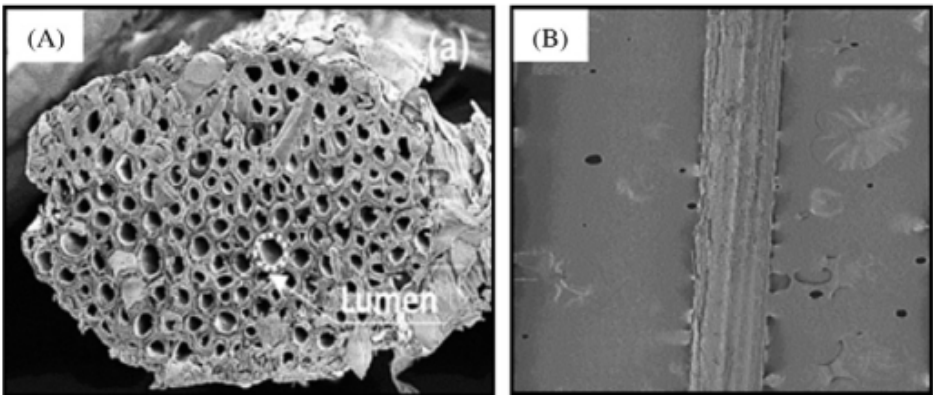


Figure 3.12 Scanning electron micrograph of morphological abaca fiber: (A) surfaces of abaca fiber bundles; (B) longitudinal sections. 22
Source: From Cai M, Takagi H, Nakagaito AN, Katoh M, Ueki T, Waterhouse GIN, et al. *Influence of alkali treatment on internal microstructure and tensile properties of abaca fibers.* Ind Crops Prod 2015;65:27–35 [98].

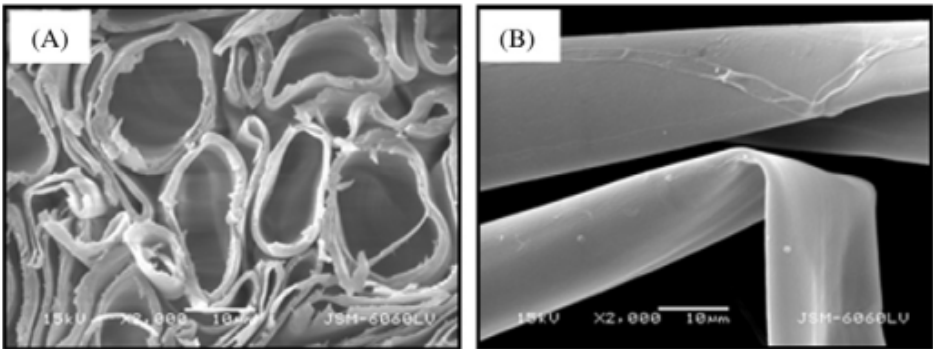


Figure 3.13 Scanning electron micrograph of morphological kapok fiber: (A) cross-section; (B) longitudinal view. 42
Source: From Rijavec T. Kapok in technical textiles. Tekstilec 2008;51(10–12):319–31 [105].

due to their light weight and the fact that they are too inelastic to be spun (Fig. 3.13B). Kapok normally consists of about 65.63%–69.87% cellulose and 5.46%–5.63% lignin [103]. According to Anigo et al. [104], kapok also contains 6.66%–10.49% hemicellulose, and 2% ash.

Fig. 3.14B shows the structure of kenaf fibers is coarse morphology, where fibers are not uniform, and are round polygonal in shape. Meanwhile, the presence of lignin and impurities (silica nodules) is shown in Fig. 3.14B [106]. Single fibers of bast kenaf were bound in a bundle of approximately 5.74–26.59 μm diameter and 2.27–2.51 mm length fiber. The mean vessel diameter and cell wall thickness are 284 and 6.39 μm , respectively [17]. The cellulose content (37.50%–63.00%) is higher in the bast part than in the core of kenaf. The lignin varies on average from 18.00% to 24.30%, while hemicellulose content is 15.10%–21.40% [75,107]. Most wax is deposited in the epidermis, where wax content affects the fiber properties of kenaf [108].

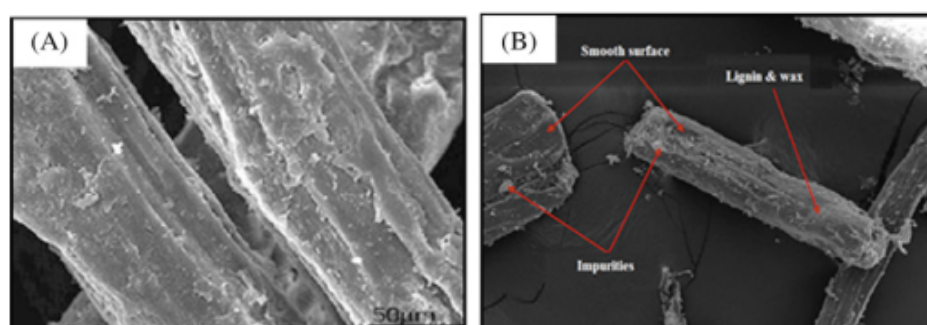


Figure 3.14 Scanning electron micrograph of morphological kenaf fiber: (A) transverse section of bast fiber [14] (B) the raw kenaf fiber bundles.

Source of A: From Jonoobi M, Harun J, Shakeri A, Misra M, Oksman K. Chemical composition, crystallinity, and thermal degradation of bleached and unbleached kenaf bast (*Hibiscus cannabinus*) pulp and nanofibrils. *BioResources* 2009;4(2):626–39 [109]. Source of B: From Safinas A, Saad Md, Bakar AA, Ismail H. Properties of kenaf bast powder-filled high density polyethylene/ethylene propylene diene monomer composites. *BioResources* 2013;8(2):2386–97 [108].

21

3.3.3 Physical and mechanical properties

The physical and mechanical properties of biomass fibers are important and closely related to the structure of the biomass fibers themselves. The biomass fibers are basically natural organic fibers, and show high variability in their various properties. This poses different problems in characterizing the quality of fibers' physical and mechanical properties. The most important physical property is density, while the mechanical properties of single fibers are measured using value of modulus and tensile strength. It is important to mention biomass fibers as biomaterials for development and fabrication of polymer composites [110,111].

Finally, it is seen from literature that biomass fibers have the best potential for filler/reinforcement in polymer composites. A comparison of physical and mechanical properties of selected biomass fiber is given in Table 3.3.

3.4 Bionanomaterial from agricultural waste

Bionanomaterial from lignocellulosic biomass is rapidly growing with production of cellulose nanofibrils or nanoparticles. Both types of nanocellulose materials are used in various applications due to their low density, optical transparency, high mechanical properties, large surface area (aspect ratio), flexibility, specific barrier properties, low thermal expansion, biodegradability, and environmentally friendly nature [123–125]. The technique for the production of nanocellulose can be through mechanical, chemical, and chemomechanical treatment process [8] [126–132]. With the appropriate modification and characterization, nanocellulose could broaden the applications of biobased polymers to the great benefit of many industries, such as transparent films [133], strength enhancers in paper [134], reinforcements for polymer composite [135],

Table 3.3 Physical and mechanical properties of selected agricultural waste fibers

Fiber source	Density (g/m ³)	Tensile strength (MPa)	Young's modulus (GPa)	References
Oil palm	0.7–1.55	227.5–278.4	2.7–3.2	[86,51]
Bagasse	0.31–1.25	257.3–290.5	15–18	[53]
Banana	0.65–1.36	51.6–55.2	3.00–3.78	[64,112,113]
Coconut (coir)	0.67–1.15	173.5–175.0	4.0–6.0	[64,113]
Pineapple	1.25–1.60	166–175	5.51–6.76	[64]
Rice straw	0.86–0.87	435–450	24.67–26.33	[114,58]
Jute	1.3–1.45	300–700	20–50	[115,116,91]
Kenaf	0.15–0.55	295–955	23.1–27.1	[117,118,119]
Bamboo	0.6–1.1	360.5–590.3	22.2–54.2	[120]
Sisal	1.45–1.5	300–500	10–30	[115,116,91]
Abaca	1.42–1.65	879–980	38–45	[91]
Kapok	0.68–1.47	80.3–111.5	4.56–5.12	[103,121,122]

4

Source: From Hemmasi AH, Khademi-Eslam H, Pourabbasi S, Ghasemi I, Talaiepour M. Cell morphology and physico-mechanical properties of HDPE/EVA/Rice hull hybrid foamed composites. *BioResources* 2011; 6(3): 2291–308 [51]; Driemeier C, Santos WD, Buckeridge MS. Cellulose crystals in fibrovascular bundles of sugarcane culms: Orientation, size, distortion and variability. *Cellulose* 2012; 19: 1507–15 [53]; Reddy N, Yang Y. Properties of High-Quality Long Natural Cellulose Fibers from Rice Straw. *J Agric Food Chem* 2006; 54(21): 8077–81 [58]; Alwani MS, Abdul Khalil HPS, Islam MN, Sulaiman O, Zaidon A, Dungani R. Microstructural study, tensile properties, and scanning electron microscopy fractography failure analysis of various agricultural residue fibers. *J Nat Fibers* 2015; 12: 154–68 [64]; Vijayalakshmi K, Neeraja CYK, Kavitha A, Hayavadana J. Abaca fibre. *Trans Eng Sci* 2014; 2: 16–9 [91]; Chaiarekij S, Apirakchaikul A, Suvarnakich K, Kiatkamjornwong S. Kapok fibre. *Trans Eng Sci* 2014; 2: 16–9 [91]; Sumaila M, Amber I, Bawa M. Effect of fiber length on the physical and mechanical properties of random oriented, woven short banana (*Musa balbisiana*) fibre/epoxy composite. *Asian J Nat Applied Sci* 2013; 2: 39–49 [112]; Sakthivel M, Ramesh S. Mechanical properties of natural fiber (banana, coir, sisal) polymer composites. *Sci Park* 2013; 1: 1–6 [113]; Bouasker M, Belayachi N, Hoxha D, Al-Mukhtar M. Physical characterization of natural straw fibers as aggregates for construction materials applications. *Materials* 2014; 7: 3034–48 [114]; Alves C, Ferrao PMC, Freitas M, Silva AJ, Luz SM, Alves DE. Sustainable design procedure: The role of composite materials to combine mechanical and environmental features for agricultural machines. *Mater. Design* 2009; 30: 4060–8 [115]; Bongarde US, Shinde VD. Review on natural fiber reinforcement polymer composites. *Int J Eng Sci Innovat Technol* 2014; 3: 431–6 [116]; Wambua P, Ivens J, Verpoest I. Natural fibres: can they replace glass in fibre reinforced plastics? *Compos Sci Technol* 2003; 63(9): 1259–64 [117]; Munawar SS, Umemura K, Kawai S. Characterization of the morphological, physical, and mechanical properties of seven non-wood plant fibre bundles. *J Wood Sci* 2007; 53(2): 108–13 [118]; Paridah M, Khalina A. 2009. Effects of soda retting on the tensile strength of kenaf (*Hibiscus cannabinus* L.) bast fibres. Project Report Kenaf EPU 14 (Suppl. 1), 2009: 21–28 [119]; Rathod A, Kulkarni A. Analysis of physical characteristics of bamboo fabrics. *Int J Res Eng Technol* 2014; 03(08): 21–25 [120]; Mwaikambo LY, Ansell MP. The determination of porosity and cellulose content of plant fibers by density methods. *J Mater Sci Lett* 2001; 20: 2095–6 [121]; Mojica ERE, Merca FE, Micor JRL. Fiber of kapok (*Ceiba pentandra*) as component of a metal sensor for lead in water samples. *Philippine J Crop Sci* 2002; 27: 37–42 [122].

emulsions and oxygen barrier films for plastics packaging [136,137], and many others [138].

There are various studies on lignocellulosic biomass as filler or reinforcement in polymer composites, such as coir fiber in PP composite [139], bagasse fiber in thermoplastic composites [140], nanocellulose sisal fiber-reinforced polyolefin composites [141], carbonized jatropha seed shell as filler in vinyl ester biocomposites [142],

nanocellulose fiber char in poly(vinyl acetate) formed composites [143], oil palm shell (OPS) nanoparticles as filler in polyester hybrid composites [15], etc. When incorporated in polymer matrices, nanosized cellulose could impart higher stiffness to the nanocomposites. It is an ideal reinforcement agent in polymer composites due to its large aspect ratio resulting from interconnected network structures through hydrogen bonding.

The morphology, dimension, crystallinity, and surface chemistry are key properties of nanocellulose for end use. A variety of cellulosic biomass other than wood fiber, such as oil palm, kenaf, rice straw, bamboo, bagasse, and pineapple have been utilized for the extraction of nanocellulose [77,144]. Selecting the cellulosic biomass depends on the availability of the fiber in a country, the chemical components for its application, and economic considerations [37]. In spite of being the most abundant cellulose biomaterial on earth, the processing of cellulose into types of nanostructures has only recently received considerable attention. Over the past few decades, lignocellulosic biomass has attracted a great deal of scientists and researchers using biomaterials to isolate nanocellulose to fabricate diverse functional materials.

3.4.1 *Properties and characterization of CNFs from agricultural waste*

Many studies have been done on isolation from biomass and allowing different kinds of nanoscaled cellulosic fillers to be obtained. However, the biomass structure of agricultural waste consists of inherent properties, such as strong lignin layers, low cellulose accessibility to chemicals, and high cellulose crystallinity, which inhibit the digestibility of the biomass for cellulose extraction. Some biorefinery processes are necessary to deconstruct noncellulosic content in lignocellulosic biomass, while maintaining cellulose product for further hydrolysis into nanocellulose material [145,146]. Lignocellulosic plants first require the breakdown of the supramolecular cell wall structure, thus increasing accessibility to the polysaccharide components of the raw lignocellulose. The next step is to break down the cross-linked elements in the raw material (lignin, cellulose, pectin, and hemicellulose) to increase the accessibility to the cellulose microfibrils [147]. Nanocellulose extracted by processing conditions and different cellulosic source can be classified into nanofibrillated cellulose (NFC) and nanocrystalline cellulose (Fig. 3.15).

Generally there are two main families of CNFs, differing in size and crystallinity, which are cellulose nanocrystal (CNC) and nanocellulose [127,148]. CNC is also known as nanowhiskers [150,151], nanorods [152], and rod-like cellulose crystals [152]. CNC is usually isolated from cellulose fibers through acid hydrolysis, using sulfuric acid, hydrochloric acid, etc. [153,154].

The nanoscale structure of nanocellulose was revealed by transmission electron microscopy (TEM). TEM images of the nanocellulose (CNC and NFC) suggest transverse cleavage of microfibril fibers into free and individualized nanocellulose (Fig. 3.16). Furthermore, diameter of nanocellulose had a gradual decrease due to the progressive removal of the amorphous portion of cellulose fiber with increase in process time [155]. Surface morphology from SEM analysis shows the form of the

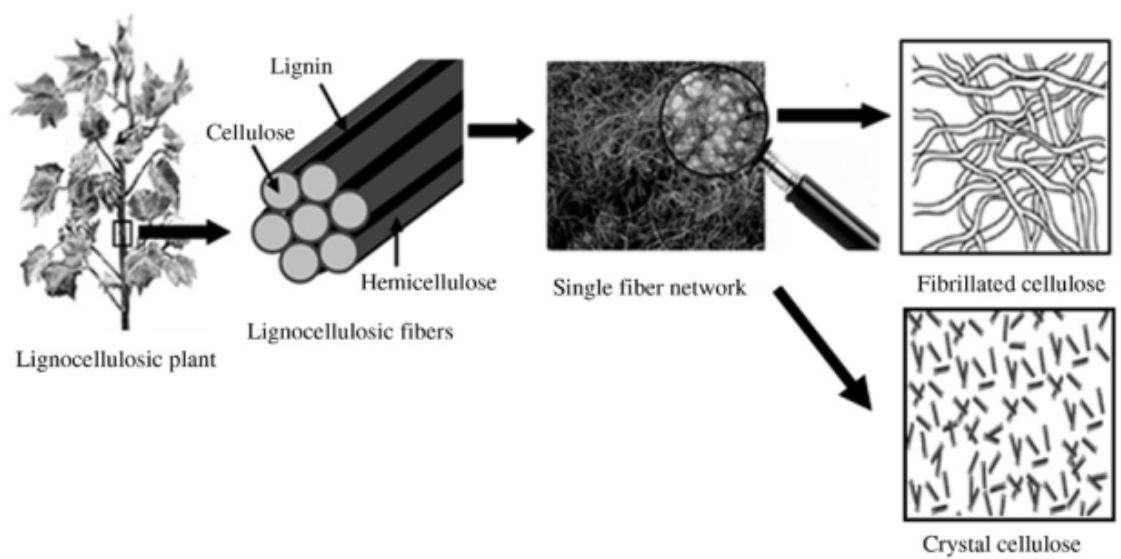


Figure 3.15 The schematic principle of isolating noncellulosic content in lignocellulosic biomass into CNFs.

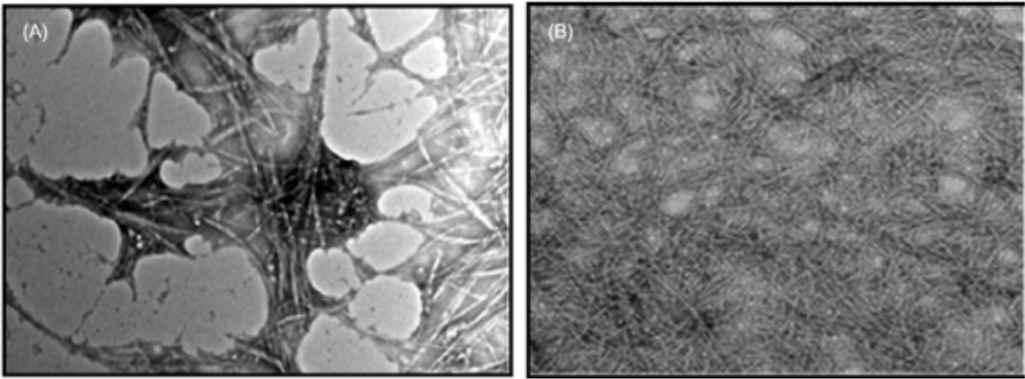


Figure 3.16 TEM image of nanocellulose from agricultural waste: (A) TEM image of nanocrystal/nanowhiskers; (B) TEM image of NFC.
Source of A: From Saurabh CK, Dungani R, Owolabi AF, Atiqah NS, Zaidon A, Aprilia NAS, et al. Effect of hydrolysis treatment on cellulose nanowhiskers from oil palm (*Elaeis guineensis*) fronds: morphology, chemical, crystallinity, and thermal characteristics. BioResources 2016;11(3):6742–55 [158]. Source of B: From Fatah IYA, Abdul Khalil HPS, Hossain MdS, Aziz AA, Davoudpour Y, Dungani R, et al. Exploration of a chemo-mechanical technique for the isolation of nanofibrillated cellulosic fiber from oil palm empty fruit bunch as a reinforcing agent in composites materials. Polymers 2014;6:2611–24 [159].

smooth surface of the fiber and the individual in a bundle [156,157]. TEM images of the nanowhiskers suggest that amorphous regions from fiber are removed through transverse cleavage of microfibril fibers (Fig. 3.16A). On the other hand, NFC is flexible and has an entangled network structure, matted and not individualized, therefore the total length cannot be determined, as seen in Fig. 3.16B.

A NFC is a fiber resulting from isolation process of lignocellulosic biomass with a diameter of 100 nm or less and length of several micrometers. Reported by Chao et al.

[160], the treated cellulose nanofibril has diameter distribution in the range 15–35 nm, which was similar to that of the untreated CNF (about 15–40 nm). Processing this biomass presents a large crystalline region with 150 m²/g on specific surface area, also called microfibrillated CNFs. CNC has a perfect crystalline structure and high modulus, close to the theoretical modulus of cellulose [148].

There are various reports on isolation of nanocellulose from nonconventional agricultural waste, including pineapple leaf fibers [161], grass [162], rice husk [163,164], rice straw [165], empty fruit bunches [129,166], etc. In these types of nanocellulose, after applying various pretreatments, tailor-made nanofibrils with specific morphology and surface chemistry are produced. Different properties of these two types of nanocellulose will result in varying reinforcement of nanocomposites to the thermoplastic and thermoset of polymer matrices. As well as being completely renewable, safer to handle, and cheaper to produce, nanocellulose materials also possess exceptional physical and chemical properties.

Applications being developed for nanofibers include stimulating the production of carbon nanofibers, which can improve the performance of flame retardant in furniture [167]. Many methods have been made to isolate the cellulose fibers. Alemdar and Sain [168] imply that cellulose chains are packed in an ordered manner to form compact microfibrils, which are stabilized by both inter- and intramolecular hydrogen bonding. CNC are very polar and attract each other by H bonding, so that treatment by acid hydrolysis formed separating individual crystals. Isolating the CNFs can be done by steam explosion method [16,69], high-intensity ultrasonication combined with chemical pretreatments [170], 2,2,6,6-tetramethylpiperidine-1-oxyl radical (TEMPO) method [10], acid treatment, ultrasonication method [171], and enzymatic hydrolysis [172].

In recent years, biological pretreatment using microorganisms has been strongly beneficial. The formation of CNF with microorganisms as tools gives various advantages, such as nontoxicity, biodegradability, and low inhibitory factors. Some fungi, bacteria, and yeast have the ability to degrade cellulosic contents in plants using their enzymatic mechanism, and the resulting products can be used for nanofiber materials [173–177]. In the near future, the optimized use of microorganisms as pretreatment agents is expected to be an efficient method for cellulose degradation and will contribute to the production of CNF.

The mechanical properties of CNC contain a small number of defects [178]. The axial elastic modulus is close to that derived from theoretical chemistry and is potentially stronger than steel and similar to Kevlar [179]. The first report showed that Young's modulus of CNC is 130 GPa [180], and then Zimmerman et al. [181] reported this value as 250 GPa. However, Eichhorn [182] showed that the modulus of tunicate cellulose nanowhiskers was 143 GPa. Menezes et al. [179] imply that experimentally the elastic modulus is around 137–167.5 GPa. CNC has higher strength than steel and higher stiffness than aluminum. It has elastic modulus and bending strength of 138–167 and 10 GPa [183,184]. CNC has high availability, light weight, and high mechanical properties. It consists of slender parallelepiped rods, depending on its origin, and the lateral dimensions range from about 2 to 50 nm in diameter for length than can reach several tens of micrometers [185].

Iwamoto et al. [186] evaluated the elastic modulus of single NFC using TEMPO oxidation and acid hydrolysis treatment. They showed elastic modulus values of

145.2 ± 31.3 and 150.7 ± 28.8 GPa, respectively. They considered that NFC has large surface area that increases its interaction with secondary materials at the nanolevel. Thus it can be concluded that crystalline domains of nanocellulose resulted in an increase in mechanical properties of nanocellulose-incorporated composites.

The thermal characterization of NFC was conducted using thermogravimetric and derivative thermogravimetric curves analysis. These were used to determine its potential use in high temperature applications. Thermal analysis showed that the weight loss of NFC was observed from 50 to 150°C; at this range of temperature, the moisture content evaporates [187]. The degradation behavior of agriculture waste started at 290°C [128] and 300°C [187]. The degradation temperature of CNFs of agriculture waste started at 300°C and continued up to 400°C [188]. Nuruddin et al. [187] [12] wed that the degradation temperature for the microbrils extracted from rice straw started at 332°C and continued up to 370°C, where all cellulose was pyrolyzed, the solid residues being of about 20%. In general, the sulfate groups, smaller fiber dimensions, and crystal structure of CNC prepared by sulfuric acid hydrolysis on the surface could promote the thermal degradation [189,190].

The physical characterization of NFC based on the morphology and dimension has been conducted with TEM and AFM analysis by different methods. Many studies have found a difference in characterization of NFC, from 1 to 50 nm in thickness and by several μm in length [146]. The results of TEM show that the NF7 from agricultural waste obtained after the chemomechanical treatment typically are 100–300 nm in length and 44–20 nm in width [191]. The dimensions of CNC depend on the sources; they depend strongly on the processing techniques and the prepared samples exhibited distinct features. With acid hydrolysis method, stronger acidity, higher temperature, and longer reaction time might yield shorter CNC [192]. 24

The structure of CNC was studied using X-ray diffraction (XRD). XRD is used to investigate the effect of chemical and mechanical treatments on the crystallinity and crystal type of the NFC. In all cases, the cellulose crystal structure of nanocellulose fiber indicated that the native cellulose crystal structure was preserved [77,188]. With sulfuric acid hydrolysis method, strong acid hydrolysis usually resulted in removal of amorphous areas and a higher crystallinity during hydrolysis [78,193]. However, TEMPO-mediated oxidation did not influence the crystalline structure of isolated cellulose [194–196]. Furthermore, several researchers have reported the diffraction peak of CNFs at the 110, 200, 004 crystallographic plane [138,197] and the crystallinity index of CNFs between 70% and 80% [198].

3.4.2 Properties and characterization of nanoparticles from agricultural waste

Nanoparticles have one dimension that measures 100 nm or less. In other words, we can say that they are the collection of atoms bonded together with a structural radius of less than 100 nm. The properties of many conventional materials change when formed from nanoparticles. This is typically because nanoparticles have a greater surface area per weight than larger particles, which causes them to be more reactive to some other molecules. Nanoparticles are very ordinary in nature, for instance,

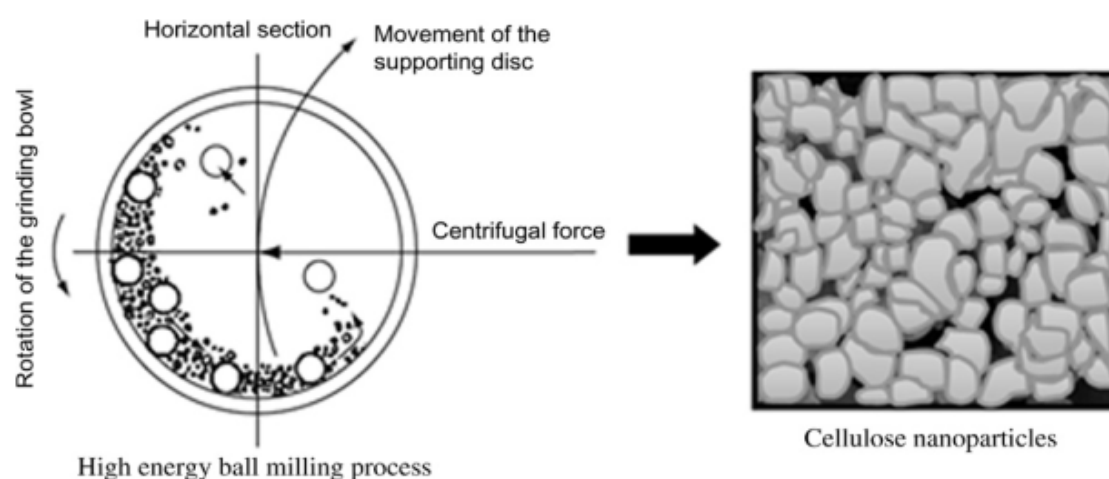


Figure 3.17 The schematic principle of pulverization of lignocellulosic biomass by high grinding energy to produce cellulose nanoparticles.

proteins exist in almost all biological systems. These can include, e.g., fullerenes, metal clusters, large molecules such as proteins, and even hydrogen-bonded assemblies of water molecules, which exist in water at ambient temperatures.

Until recently, metallic nanoparticles, especially silver nanoparticles, were considered as the most promising due to their large surface-area-to-volume ratio. The use of renewable plant material on synthetics of silver nanoparticles offers enormous benefits as a viable alternative for the development of metal nanoparticles because of their wide range of applications [199]. Agricultural wastes such as sesame husk [200], OPS [14], oil palm ash [201], and coconut shell (CS) [202] have been used to generate cellulose nanoparticles.

Many attempts have been made to use agricultural wastes to produce nanoparticles by a variety of chemical and physical methods. The combined action of chemical treatment and high-energy planetary ball-milling process is another effective method of nanoparticles synthesis [94]. The principle of this combined method is that chemical treatment removes lignin and hemicelluloses from cellulosic materials and then the ball-milling process further grinds the material into powder form, which is nothing but cellulose nanoparticles. The principal properties of nanoparticles include size, shape, and surface structure, and processing tends to introduce surface imperfections (Fig. 3.17). These surface imperfections can significantly impact on the overall nanoparticle surface physicochemical properties [203,204].

Lignocellulosic biomass consists of polymeric materials that contain different amounts of oil. The presence of remaining oil within the lignocellulosic biomass such as oil palm, coconut, and jatropha is one challenge. The second challenge that was discovered was irreversible adsorption and aggregation of nanoparticles when solvents were removed during purification, which led to significant loss of material and created a problem afterward [205]. Any impurity and contamination on the particle will lower the effect of this biomass for advanced applications such as composites [206], pulp and paper production, etc. The oil removal process is crucial to eliminate this problem, and could also benefit further applications. Several methods can be

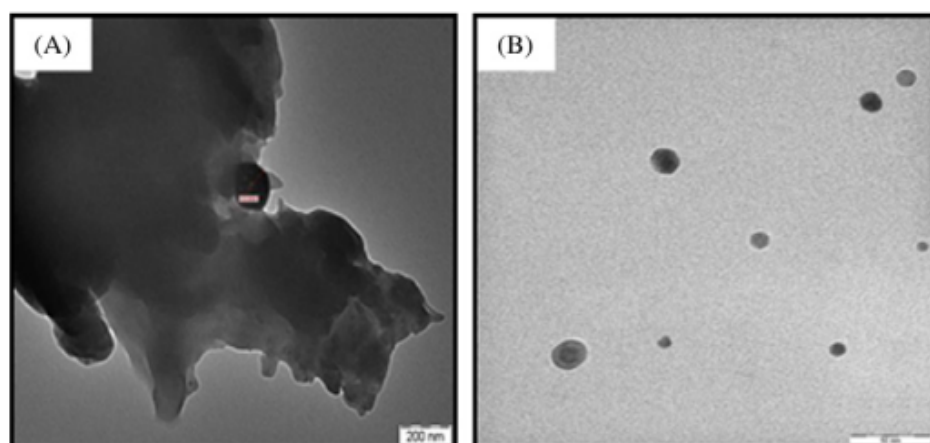


Figure 3.18 TEM images of nanoparticle CS. (A) Before extraction; (B) after extraction.

used to separate oil from the lignocellulosic biomass; these include mechanical pressing, supercritical fluid extraction, and solvent extraction [207,208]. The successful extraction of oil removal of lignocellulosic biomass nanoparticles was reported by Sulaeman et al. [202]. Using an soxhlet extraction unit (Soxtec 2043, Foss, Hillerød, Denmark), which connected to a reaction flask containing 250 mL of *n*-hexane, the resulting nanoparticles showed a clear increase in size and the elimination of the remaining oil within the nanoparticle samples (Fig. 3.18).

As a filler, nanoparticles from agriculture waste could be made in the form of flour, carbon, fiber, etc. When the three dimensions of particulates are in the order of nanometers, they are called isodimensional nanoparticles. They include spherical nanoparticles, nanogranules, and nanocrystals [209]. The filler may be selected such as flours from CS [202], OPS [14], olive stone and pecan shell [210], wood bark [211], wood flour such as soft wood, hard wood, and free bark flours [212], and other cellulosic fillers.

The particle size and size distribution play a crucial role in property characterization of nanoparticles. These properties are chemical, physical, electronic, thermal, magnetic, and mechanical. For example, a study on thermal properties of CS showed that CS nanoparticles had more thermal stability when the size reached to the nanometer scale compared with raw CS [202]. Hence, the novel properties of nanoparticles do not prevail until the size has been reduced to the nanometer scale [213]. In other words, the functional properties of nanoparticles are significantly different from the properties of the bulk material having the same chemical composition. The particle size and size distribution of nanoparticles can be determined with microscopic techniques and utilizing the relationship between particle behavior and size. There are numerous commercially available instruments that can be used for determining particle size and size distribution of nanoparticles, such as TEM, SEM, dynamic light scattering (DLS), X-ray diffraction (XRD), photon correlation spectroscopy (PCS), AFM, Brunauer–Emmett–Teller (BET), etc. Many studies have been made on particle sizing of nanoparticles using different instruments. For example, Dungani et al. [214] investigated the particle size of OPS by TEM. They showed that OPS particle

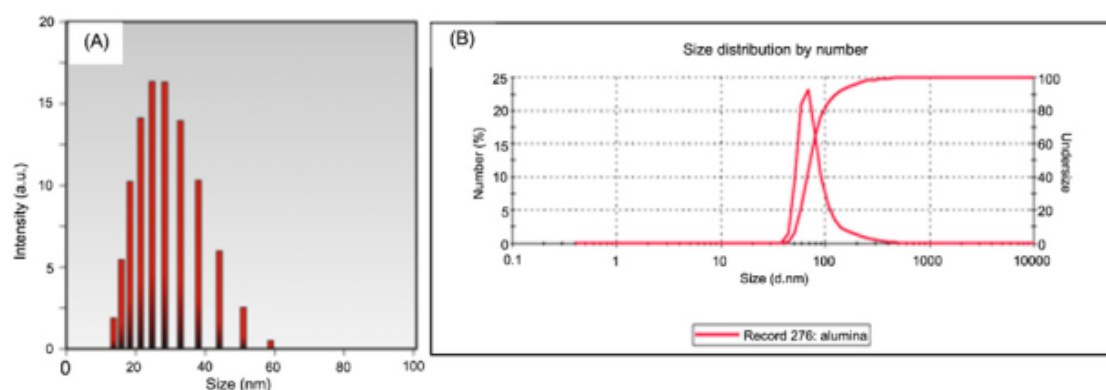


Figure 3.19 Particle size distribution of the nanoparticles. (A) DLS image; (B) PCS image.

Source of A: From Mollick MdMR, Rana D, Dash SK, Chattopadhyay S, Bhowmick B, Maity D, et al. Studies on green synthesized silver nanoparticles using *Abelmoschus esculentus* (L.) pulp extract having anticancer (in vitro) and antimicrobial applications. *Arabian J Chem* 2015;doi: 10.1016/j.arabjc.2015.04.033 [215]. *Source of B:* From Akbari B, Tavandashti MP, Zandrahimi M. Particle size characterization of nanoparticles—a practical approach. *Iran J Mater Sci Eng* 2011;8(2):48–56 [213].

34

size ranged from 10 to 50 nm with average of particle size close to 50 nm. They also reported that the average particle size was determined from X-ray diffraction peaks using XRD images, with the average size of OPS nanoparticles calculated to be 31.75 nm. By comparing the results from different instruments, one can obtain extra information about the system. Fig. 3.19 shows the DLS and PCS techniques used to determine the average size and particle size distribution of nanoparticles.

Nanoparticles possess a variety of morphologies and their names are characterized by their different shapes. These morphologies sometimes arise spontaneously as an effect of a templating or directing agent during synthesis. Ghaedi et al. [216] investigated the surface morphology of the activated carbon-derived nanoparticles from medlar wood. They showed that a surface morphology could be achieved that is homogeneous and relatively smooth and dense with a large number of pores and cavities in different sizes and shapes. They also observed that the adsorbent exhibited nearly narrow pore size distribution in the mesoporous domain with average pore diameter lower than 10 nm. The functional properties of nanoparticles highly depend on the surface morphology of the particles, so precise measurements of a particle's morphology enable reliable characterization of the nanoparticle's properties. Controlling the morphology of nanoparticles is of key importance for exploiting their properties. For example, surface functionalization of silica nanoparticles with coating polymer by brushes [217] and a thin polymer film [218] is very important as the polymer coating alters the interfacial properties, and thus the mechanical and thermal properties of the matrix polymers can be altered by the compatibility of the nanoparticles within the matrix.

SEM analysis was employed to visualize the size and shape of nanoparticles. From the SEM analysis, it was found that silica nanoparticles from agricultural waste have their own shape and size arrangement [219]. These results suggested that the waste

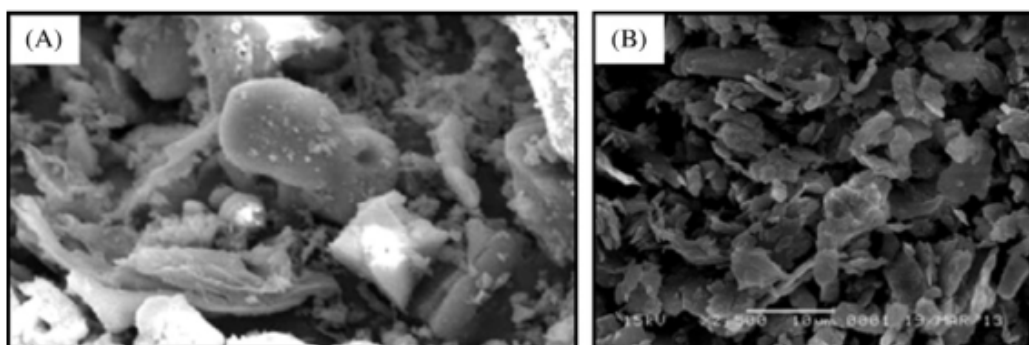


Figure 3.20 SEM micrographs of ground silica powder (A) bagasse ash; (B) CS.

Source of A: From Hariharan V, Sivakumar G. Studies on synthesized nanosilica obtained from bagasse ash. *Int J ChemTech Res* 2013;5(3):1263–6 [220]. Source of B: [25]m Sulaeman A, Dungani R, Islam MN, Abdul Khalil HPS, Sumardi I, Hermawan D, et al. Preliminary study of characterization of nanoparticles from coconut shell as filler agent in composites materials. *MAYFEB J Mater Sci* 2016;1(2016):1–9 [202].

materials are converted to ash by sintering at 900°C and silica powders characterized by SEM showed bamboo leaf-like particles. However, the groundnut shell ash shows uniform spherical particles. They also observed that rice husk ash has a fiber-like appearance, whereas, sugarcane bagasse ash was highly porous on its structure. Hariharan and Sivakumar [220] studied the waste material bagasse ash as a material from which to obtain nanosilica. They reported nanosilica with various sizes and prismatic and spherical geometry (Fig. 3.20A). SEM imaging on CS nanoparticles found a structure with angular, irregular, and crushed shapes [202]; the authors also reported that these structures broke down after high-energy ball milling (Fig. 3.20B).

TEM is employed to determine the morphology, shape, and size of nanoparticles. Fig. 3.21 shows the TEM images of silica nanoparticles of rice husk ash. Fig. 3.21A shows that the particles are dispersed (heterogeneity). Fig. 3.21B shows that the majority of particles are in the 60–70 nm size range and there are some larger particles in [38] 105–112 nm range [221].

Fourier transform infrared spectroscopy (FTIR) is used to examine the surface chemistry as the organic functional groups that are attached to the surface of nanoparticles. Ghorbani et al. [222] and Chen et al. [223] investigated the organic functional group of silica nanoparticles of extracted rice husk at combustion temperatures of 600°C and 700°C, respectively. FTIR analysis has detected that the vibration signals at 1075, 780, and 665 cm^{-1} are typical of Si–O–Si bands, which confirms the presence of silica nanoparticles [224]. These three peaks are the main indices of silica materials, which represent successful production [222]. Synthesis of nanoparticles has been developed from banana peel [225], which show characterization of FTIR was a shift in the 2930–2924, 2353–2344, 1732–1726, 1640–1630, 1532–1533 and 1445–1451 cm^{-1} . They also reported that the main surface function groups present as amide group; amino group; and methyl, methylene, and methoxy groups. The main surface functional groups in CS nanoparticles obtained by ball milling process present as a combination of hydroxyl (OH), methylene groups (C–H), carbonyl groups (C=O), and ethers (C–O–C) [202].

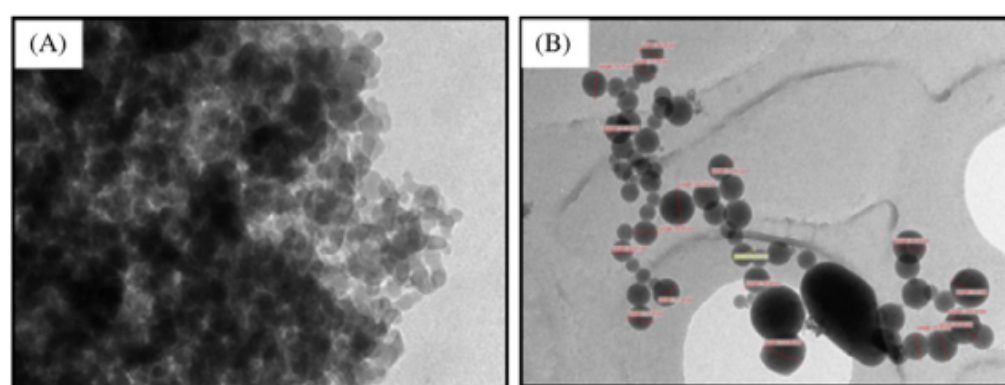


Figure 3.21 TEM image of silica nanoparticles of rice husk ash. (A) The particles are dispersed; (B) a heterogeneity in size.

Source: From Djangang CN, Mlowe S, Njopwouo D, Revaprasadu N. One-step synthesis of silica nanoparticles by thermolysis of rice husk ash using non toxic chemicals ethanol and polyethylene glycol. *J Appl Chem* 2015;4(4):1218–26 [221].

3.5 Various applications of bionanomaterial

Nanotechnology represents a major opportunity for wood and plant-based materials to improve their performance and functionality, develop new generations of products, and open new market segments in the coming decades. Research on nanocellulose and commercial development for sustainable utilization of biomass is ongoing, mainly in Japan, North America, and Europe. The current market situation continues to grow as the worldwide demand for new products on the market. As the worldwide demand for fiber grows, so does the demand for sustainable resource management and efficient industrial utilization. This means that nanocellulose is a prime candidate for use as sustainable and recycling-based material in industries such as packaging, automotive components, biocomposites, etc.

With improvement techniques of the selected biomass fibers and extraction technologies, as well as modification and characterization, nanocellulose can be applied to composite-based products. Applications of surface-modified nanofibrillar cellulose are for advanced materials such as high-performance nanocomposite materials and films, medical, pharmaceutical, cosmetics, automotive, electronic industries, aircraft manufacturers, and paper and printing industries. Numerous works are underway regarding nanocellulose-based products from various cellulosic sources and their applications [226].

The market for nanomaterials in various products such as structural components continues to grow, mainly driven by the demand for materials that have a high strength-to-weight ratio. Researchers have found that adding natural cellulosic to polymer composites may result in stronger/stiffer components than polymer composites using a similar weight of carbon nanocellulose [182,227–231]. This property could result in the manufacture of components with higher strength-to-weight ratios for such uses as aircraft components.

In the last decade, considerable efforts have been made to develop bionanomaterials. In addition bionanomaterials play an important role in many recent applications. Novel bionanomaterials are leading to new, multifunctionalities for packaging, fillers to improve mechanical and barrier properties of biocomposites, automotive components, medical devices, and other applications. The next section shows that bionanomaterials from agriculture waste have applications in several sectors.

3.5.1 As a reinforcing agent in composites materials

Over the past two decades, there has been a growing interest in the use of bionanomaterials as a reinforcement for polymer composite materials [25,232]. These materials include cellulose fibers and particles that possess desirable specific properties. Cellulose fibers for use as reinforcing elements in composite materials are an interesting alternative to synthetic fibers, such as glass fibers, because of their competitiveness in terms of weight and mechanical properties [117].

However, certain drawbacks such as incompatibility with the hydrophobic polymer matrix, a tendency to form aggregates during processing, and poor resistance to moisture absorption reduce the potential of these fibers for use as a reinforcement of thermoplastic matrices. Several strategies have been reported based on physical treatments in order to improve fiber/polymer compatibility and interfacial adhesion [233,234] and chemical modification of fibers to reduce their polarity and hydrophilicity [235,227].

There is a wide variety of different biomaterials that can be applied as reinforcing agents or fillers. A nanocomposite is a matrix to which nanoparticles have been added to improve a particular property of the material. Reinforcement is a simple method to reduce defects. The reinforcement of polymer composite materials depends on reinforcing agents such as fibers and nanoparticles [237]. Nanoscale additives, such as carbon black and silica nanoparticles, have been commonly used as polymer reinforcing agents [238]. The properties of nanocomposites have caused researchers and companies to consider using this material in several fields [25,127,159,239].

There has been wide application of bionanomaterial from agriculture waste in industrial applications. Bionanomaterials in reinforcement in polymers, such as in thermoset and thermoplastic polymers, have been used in many applications such as electronics, thermal insulators, aerospace, automotive, building materials, construction, and sports [168,240,241]. In terms of electronic devices, CNFs have low density, high specific modulus, high electrical conductivity, and large surface area, and are highly valuable in the field of super capacitors, nanooptoelectronic components, etc. [242].

Silica-reinforced polymer composite prepared via various processes is promising and has been widely used. Masoodi et al. [241] has studied how CNFs are used as reinforcing agents in the form of layered films in a bioderived resin. Silica nanoparticles have been developed for several applications such as electronic substrates, thin film substrates, electrical insulators, thermal insulators, and humidity sensors [243]. The quality of some of these products is highly dependent on the size and size distribution of the silica particles.

3.5.2 Packaging applications

In line with development of research in the nanotechnology field and concern for reducing environmental impact, cellulose-based materials have gained much more consideration for the development of alternative packaging materials. Studies by several researchers, such as Singh et al. [244], De Moura et al. [245], Youssef et al. [246], and Kalia et al. [247], have reported the use of natural cellulose-based nanocomposites for packaging applications.

Lignocellulose packaging has been used for a wide range of food categories, such as dry food products, frozen or liquid foods, beverages, and even fresh foods [246]; furthermore, it can be used in packaging of nonfood materials, such as medical and pharmaceutical packaging [248,249].

Packaging is being designed as a health system to provide positive impact on consumer health by integrating functional ingredients in the structure of the packaging [250]. Applications being developed for packaging material are durable, can be continuously recycled and reused, and do not contaminate [251]. Researchers have found that the adding nanocellulose to polymeric composites may result enhancement in gas barrier properties and heat stability on polymer composites nanocellulose-based materials [125,127,247,252–254]. Efforts have been made to reduce poor mechanical and barrier properties of food packaging biobased materials with incorporation of reinforcing structures and matrices such as nanocellulose [255–257].

Studies have reported that the use of cellulosic materials may maximize the mechanical and barrier properties of product packaging materials [37]. Active food packaging systems include the concept of sustainable packaging, which must contain several properties such as protecting food products, enhancing food quality (stability), and releasing active compounds onto food surface [256,258]. According to Kumar and Münstedt [259], antimicrobial could be used for a variety of applications, which include fabrication of food packaging materials. The use of antimicrobial agents is its have broad antimicrobial spectrum, good processability and high temperature stability.

3.5.3 Medical application

Recent advances in biocomposites have been supported by producing biofibers, microfibrillated, or nanosize fibers. Reinforcing cellulosic nanofibers offer potential advantages such as high performance of biofiber-based biocomposites [260]. John and Thomas [23] reported that CNFs combined with biodegradable polymers as biofiber-based nanocomposites proved to be very versatile in wide range of medical applications such as cardiac devices, scaffolds for tissue engineering, repair of articular cartilage, vascular grafts, urethral catheters, mammary prostheses, blood bags, penile prostheses, adhesion barriers, and artificial skin. The development of composites from these biofibers has increased commercial prospects for medical applications.

Many studies have been made on the development of biomaterials from agricultural waste to fabricate various versatile medical implants, such as pineapple leaf fibers and polyurethane [169]. In these studies, addition of 5 wt% of cellulose

nanofibrils to polyurethane increased the strength and stiffness. Millon and Wan [261] report that the polyvinyl alcohol reinforced bacterial cellulose fibers will form biocompatible nanocomposites similar to that of cardiovascular tissues. Development of nanocellulose polyurethane vascular grafts [262], and micro- and nanofiller in polyurethane composites [263] have been reported. There have been various uses of bionanomaterials reported for the cosmetics and medical product industries, including pharmaceutical [187,264,265], medical [266], veterinary medicine [267], and dental [268] applications; furthermore, they can be used in drug delivery [175], medical implants [269–271], wound healing dressings [242,272,273], tissue engineering, and cellular culture [171,274,275].

3.5.4 Automotive industry application

Improvement in the performance of automobiles is of great importance for meeting both consumer needs and regulatory requirements in the automotive industry. Nanotechnology and nanomaterials have received great attention in the automobile industry to meet their performance needs [276]. Nanocellulose based materials are increasingly being used in thermoplastics matrix in the automotive industry over the last several years [277]. These plastic composites reinforced with cellulose fiber being used in automotive applications for front-ends, bumper beams, dashboards, and underbody shields.

Cellulose-based materials such as natural fiber are emerging as a realistic alternative to glass-reinforced composites for application in automotive components. Natural fiber composites can deliver high-performance, nonbrittle fracture. Moreover, they are considerably cheaper to produce. The use of nanofiber-reinforced plastic composites in the automotive industry has grown significantly in recent years because of their low weight, design flexibility, corrosion resistance, and cost effectiveness [277]. The most common composites in automotive application are in the exterior body panel and are also an important requirement in the passenger compartment [139,278].

Natural fiber like hemp, jute, abaca, banana, kenaf, flax, and sisal have had success as reinforcing fibers in polymer composite from PP, polyethylene, nylon, or thermoplastic polymers for other automotive applications [278–282]. Furthermore, automakers now have been using natural fiber composite thermoset matrices for automotive components (seat backs, package trays, door panels, dashboards, headliners, and interior parts). Many auto companies have been utilizing cellulose fibers composites in their automobile products. Shinoj et al. [283] suggested that Mercedes Benz utilize coconut fiber-based rubber latex composites for seat parts. They also reported that flax/sisal fiber mat-reinforced epoxy have been utilized for door panels. Suddell and Evans [284] reported that Audi uses flax/sisal mat-reinforced polyurethane composite as door trim panels. Ford has been utilizing kenaf-reinforced PP composites for producing door panels [285].

3.5.5 Other applications

Several studies reported other applications of nanobiocomposites such as sporting goods, industrial rubber applications, aerospace components, etc. Most materials used for the sporting goods market are still glass and wooden materials. Efforts have been made to produce biocomposites in their manufacture, including development of

biobased materials from agricultural waste. Some cellulose fiber materials like hemp, flax, coir, jute, etc., have been used effectively in sporting goods application. The carbon-reinforced composites have been used successfully to replace wood, glass, and metal in various applications for sporting goods such as fishing rods, ski equipment, tennis racquets, golf clubs, spars/shafts for kayak paddles, windsurfing masts, and bicycle handlebars [286,287].

Many researchers are concerned with the production of carbon black, activated carbon, and silica from biomass and agriculture-based residues, as they can be used for many applications. Nanoscale additives have been studied for the use in both natural and synthetic polymer reinforcing [288]. Silica-reinforced natural rubber prepared via a sol-gel process is promising and has been widely used [289]. Other researchers have focused on carbon black-reinforced elastomer composites to manufacture automotive components such as tires [290], as well as gloves [291] and nanobioceramic composites [292,293].

Polymer composites are widely used in the aerospace industry. Plants and crops from agricultural waste-reinforced composites have been used in polymer composites for making aerospace components. Wu and Radovic [294] reported that reinforced nanoparticles of carbon in epoxy matrix have found use in applications such as nose cones of the space shuttle, rocket nozzles, and aircraft brake discs. They also considered that additional these fillers have been improve the thermal, mechanical, chemical and physical properties.

3.6 Conclusion

Agriculture-based residues are of notable economic and cultural significance all over the world, especially in South Asia, Southeast Asia, and East Asia, being used for various applications such as building materials, as a decorative product, and as a versatile raw product. Agriculture-based residues also have significant potential in composite making due to their high strength, environmentally friendly nature, low cost, availability, and sustainability. Development of basic science and novel technologies for effective utilization of agriculture-based residues is the most significant aim of collaboration between research, development, and commercialization. Bionanocomposites are a fairly new idea in high-strength composite production, with extensive applications utilizing biomaterial in nanometer dimensions as reinforcement. Typical examples of CNF-reinforced nanocomposites can be seen in packaging, automotive components, medical, aircraft components, and other applications.

The properties of natural fiber as reinforcement in polymer composites influence their composites' performance, hence, it is essential to understand the properties of natural fiber, including their physical, mechanical, and morphological properties, as well as their chemical composition. These biomaterials offer many of the advantages associated with nanosized materials, such as larger interface, flexibility in surface, and reduction in flammability. Furthermore, bionanocomposite production has superior mechanical performance. Overall, it can be concluded that isolated CNF from pineapple leaf, bagasse, kenaf, oil palm, jute, bamboo, banana, etc can be a suitable alternative reinforcing agent or filler in functional composite for various engineering applications.

References

- [1] Pardo M, Cassellis M, Escobedo R, García E. Chemical characterisation of the industrial residues of the pineapple (*Ananas comosus*). *J Agric Chem Environ* 2014;3(4):53–6.
- [2] Ioelovich M. Cellulose as a nanostructured polymer: a short review. *BioResources* 2008;3:1403–18.
- [3] Alila S, Besbes I, Vilar MR, Mutjé P, Boufi S. Mon-woody plants as raw materials for production of microfibrillated cellulose (MFC): a comparative study. *Ind Crop Prod* 2013;41:250–9.
- [4] Madsen B, Gamstedt EK. Review article wood versus plant fibers: similarities and differences in composite applications. *Adv Mater Sci Eng* 2013 2013:1–14.
- [5] United Nations Environment Programme (UNEP). Oil palm plantation: threats and opportunities for tropical ecosystem, <http://www.unep.org/GEAS>; 2011 [accessed 22.06.16].
- [6] Robles E, Urruzola I, Labidi J, Serrano L. Surface modified nano-cellulose as reinforcement 390 in poly(lactic acid) to conform new composites. *Ind Crops Prod* 2015;71:44–53.
- [7] Sumanthi S, Chai SP, Mohamed AR. Utilization of oil palm as a source of renewable energy in Malaysia. *Renew Sustain Energy Rev* 2008;12(9):2404–21.
- [8] Jawaid M, Abdul Khalil HPS. Cellulosic/synthetic fibre reinforced polymer hybrid composites: a review. *Carbohydr Polym* 2011;86(1):1–18.
- [9] Changsarn S, Mendez JD, Shanmuganathan E, Foster J, Weder C, Supaphol P. Biologically inspired hierarchical design of nanocomposites based on poly (ethylene oxide) and cellulose nanofibers. *Macromol Rapid Commun* 2011;32:1367–72.
- [10] Lavoine N, Desloges I, Dufresne A, Bras J. Microfibrillated cellulose-its barrier properties and applications in cellulosic materials: a review. *Carbohydr Polym* 2012;90(2):735–64.
- [11] Durán N, Lemes AP, Seabra AB. Review of cellulose nanocrystals patents: preparation, composites and general applications. *Recent Pat Nanotechnol* 2012;6:16–28.
- [12] Adam F, Chew TS, Andas J. A simple template-free sol-gel synthesis of spherical nanosilica from agricultural biomass. *J Sol-Gel Sci Technol* 2011;59:580–3.
- [13] Hata M, Chomanee J, Thongyen T, Bao L, Tekasakul S, Tekasakul P, et al. Characteristics of nanoparticles emitted from burning of biomass fuels. *J Environ Sci* 2014;26:1913–20.
- [14] Dungani R, Abdul Khalil HPS, Islam MdN, Davoudpour Y, Rumidatul A. Modification of the inner part of the oil palm trunk lumber (OPTL) with oil palm shell (OPS) nanoparticles and phenol formaldehyde (PF) resin: physical, mechanical and thermal properties. *BioResources* 2014;9(1):455–71.
- [15] Rosamah E, Hossain MdS, Abdul Khalil HPS, Wan Nadirah WO, Dungani R, Nur Amiranajwa AS, et al. Properties enhancement using oil palm shell nanoparticles of fibers reinforced polyester hybrid composites. *Advanc Compos Mater* 2016;23:1–14.
- [16] Dungani R, Karina M, Subyakto Sulaeman A, Hermawan D, Hadiyane A. Agricultural waste fibers towards sustainability and advanced utilization: a review. *Asian J Plant Sci* 2016;15:42–55.
- [17] Abdul Khalil HPS, Ireana Yusra AF, Bhat AH, Jawaid M. Cell wall ultrastructure, anatomy, lignin distribution and chemical composition of Malaysian cultivated kenaf fiber. *Ind Crops Prod* 2010;31:113–21.
- [18] Abba HA, Nur IZ, Salit SM. Review of agro waste plastic composites production. *J Miner Mater Charact Eng* 2013;1:271–9.
- [19] Namvar F, Jawaid M, Tanir PM, Mohamad R, Azizi S, Khodavandi A, et al. Potential use of plant fibres and their composites for biomedical applications. *BioResources* 2014;9(3):5688–706.

- [20] Ogah AO, Afiukwa JN, Nduji AA. Characterization and comparison of rheological properties of agro fiber filled high-density polyethylene bio-composites. *Open J Polym Chem* 2014;4:12–19.
- [21] Lau KT, Ho MP, Au-Yeung CT, Cheung HY. Biocomposites: their multifunctionality. *Int J Smart Nano Mater* 2010;1(13):13–27.
- [22] Taj SM, Munawar A, Khan SU. Natural fiber-reinforced polymer composites. *Proc Pak Acad Sci* 2007;44(2):129–44.
- [23] John MJ, Thomas S. Biofibres and biocomposites. *Carbohydr Polym* 2008;71(3):343–64.
- [24] Hambali E, Thahar E, Komarudin A. The potential of oil palm and rice biomass as bioenergy feedstock. In: *17th Biomass Asia workshop*; 2010.
- [25] Faruk O, Bledzki AK, Fink HP, Sain M. Biocomposites reinforced with natural fibers: 2000–2010. *Prog Polym Sci* 2012;37(11):1552–96.
- [26] Alwani MS, Abdul Khalil HPS, Sulaiman O, Islam MN, Dungani R. An approach to using agricultural waste fibres in biocomposites application: thermogravimetric analysis and activation energy study. *BioResources* 2014;9(1):218–30.
- [27] Adekunle KF. Surface treatments of natural fibres—a review: Part 1. *J Polym Chem* 2015;5:41–6.
- [28] Abdul Khalil HPS, Aprilia NAS, Bhat AH, Jawaid M, Paridah MT, Dungani R. A *Jatropha* biomass as renewable materials for biocomposites and its applications. *Renew Sustain Energy Rev* 2013;2013(22):667–85.
- [29] Dipti P. Bioenergy crop as alternative energy. *Int J Environ Eng Manage* 2013;4(3):265–72.
- [30] Agunbiade SO, John-Dewole OO, Adelegan O. Characterization of prime starches from some plant food crops for industrial exploitations. *Afr J Food Sci* 2011;5(10):574–9.
- [31] Ververis C, Georghiou K, Christodoulakis N, Santas P, Santas R. Fiber dimensions, lignin and cellulose content of various plant materials and their suitability for paper production. *Ind Crops Prod* 2004;19:245–54.
- [32] Bushman BS, Scholte AA, Cornish K, Scott DJ, Brichta JL, Vederas JC, et al. Identification and comparison of natural rubber from two *Lactuca* species. *Phytochemistry* 2006;67:2590–6.
- [33] Wang S, Zhang Y, Xing C. Effects of strand drying methods on wood surface wettability. *Holz Roh Werkst* 2007;65(6):437–42.
- [34] Pan M, Zhou X, Chen M. Cellulose nanowhiskers isolation and properties from acid hydrolysis combined with high pressure homogenization. *BioResources* 2013;8:933–43.
- [35] Van Dam JEG, de Klerk-Engels B, Struik PC, Rabbinge R. Securing renewable resources supplies for changing market demands in a biobased economy. *Ind Crop Prod* 2005;21:129–44.
- [36] Akil HM, Omar MF, Mazuki AAM, Safiee S, Ishak ZAM, Bakar AA. Kenaf fiber reinforced composites: a review. *Mater Design* 2011;32:4107–21.
- [37] Kalia S, Dufresne A, Cherian BM, Kaith BS, Averous L, Njuguna J, et al. Cellulose-based bio- and nanocomposites: a review. *Inter J Polym Sci* 2011;2011:1–35.
- [38] Somboon P, Nieminen K, Paulapuro H. Finite element analysis of the fatigue behavior of wood fiber cell walls. *BioResources* 2008;3(4):983–94.
- [39] Thomas S, Paul SA, Pothan LA, Deepa B. Natural fibres: structure, properties and applications Kalia S, Kaith BS, Kaur I, editors. *Cellulose fibers: bio-and nano-polymer composites*. Berlin: Springer; 2011. p. 3–42.
- [40] Basiji F, Safdari F, Nourbakhsh A, Pilla S. The effects of fiber length and fiber loading on the mechanical properties of wood-plastic (polypropylene) composites. *Turk J Agric For* 2010;34:191–6.

- [41] Singh TJ, Samanta S. Characterization of natural fiber reinforced composites-bamboo and sisal: a review. *Int J Res Eng Technol* 2014;3(7):187–95.
- [42] Fidelis MEA, Pereira TVC, Gomes OFM, Silva FA, Filho RDT. The effect of fiber morphology on the tensile strength of natural fibers. *J Mater Res Technol* 2013;2(2):149–57.
- [43] Ghasemi I, Azizi H, Naeimian N. Rheological behaviour of polypropylene/kenaf fibre/wood flour hybrid composite. *Iranian Polym J* 2008;17(3):191–8.
- [44] Abdul Khalil HPS, Hossain S, Rosamah E, Azli NA, Saddon N, Davoudpour Y, et al. The role of soil properties and it's interaction towards quality plant fiber: a review. *Renew Sustain Energy Rev* 2015;43:1006–15.
- [45] Dittenber DB, Gangarao H. Critical review of recent publications on use of natural composites in infrastructure. *Compos Part A* 2012;43(8):1419–29.
- [46] Norton AJ, Bennett SJ, Hughes M, Dimmock JPRE, Wright D, Newman G, et al. Determining the physical properties of flax fibre for industrial applications: the influence of agronomic practice. *Ann Appl Biol* 2006;149:15–25.
- [47] Rowell RM, Han JS, Rowell JS. Characterization and factors effecting fiber properties. Frollini E, Leao AL, Mattoso LHC, editors. *Natural polymers and agrofibers composites*. San Carlos Brazil: Embrapa Agricultural Instrumentation; 2000. p. 115–34.
- [48] Guzmán P, Fernández F, Graça J, Cabral V, Kayali N, Khayet M, et al. Chemical and structural analysis of *Eucalyptus globulus* and *E. camaldulensis* leaf cuticles: a lipidized cell wall region. *Front Plant Sci* 2014;5:21–30.
- [49] Ping JL, Green CJ, Bronson KF, Zartman RE, Dobermann A. Identification of relationships between cotton yield, quality and soil properties. *Agro J* 2004;96:1588–97.
- [50] Jahan MS, Sabina R, Tasmin B, Chowdhury DAN, Noori A, Al-Maruf A. Effect of harvesting age on the chemical and morphological properties of dhaincha (*Sesbania aculeata*) and its pulp ability and bleachability. *BioResources* 2009;4:471–81.
- [51] Hemmasi AH, Khademi-Eslam H, Pourabbasi S, Ghasemi I, Talaiepour M. Cell morphology and physico-mechanical properties of HDPE/EVA/rice hull hybrid foamed composites. *BioResources* 2011;6(3):2291–308.
- [52] Satyanarayana KG, Wypych F, Woehl MA, Ramos LP, Marangoni R. Nanocomposites based on starch and fibers of natural origin. Pilla S, editor. *Bioplastics and biocomposites engineering applications*. New York: John Wiley & Sons, Inc; 2011. p. 471–509.
- [53] Driemeier C, Santos WD, Buckeridge MS. Cellulose crystals in fibrovascular bundles of sugarcane culms: orientation, size, distortion and variability. *Cellulose* 2012;19:1507–15.
- [54] Guilherme A, Dantas PVF, Santos ES, Fernandes FAN, Macedo GR. Evaluation of composition, characterization and enzymatic hydrolysis of pretreated sugar cane bagasse. *Braz J Chem Eng* 2015;32(01):23–33.
- [55] Wahlang B, Nath K, Ravindra U, Chandu R, Vijayalaxmi K. Processing and utilization of sugarcane bagasse for functional food formulations. In: *Proceedings of the international conference and exhibition on food processing and technology*; 2012.
- [56] Reddy N, Yang Y. Biofibers from agricultural byproducts for industrial applications. *TRENDS Biotechnol* 2005;23(1):22–7.
- [57] Lim SK, Son TW, Lee DW, Park BK, Cho KM. Novel regenerated cellulose fibers from rice straw. *J Appl Polym Sci* 2001;82:1705–8.
- [58] Reddy N, Yang Y. Properties of high-quality long natural cellulose fibers from rice straw. *J Agric Food Chem* 2006;54(21):8077–81.
- [59] Helal GA. Bioconversion of straw into improved fodder: mycoprotein production and cellulolytic activity of rice straw decomposing fungi. *Mycobiology* 2005;33(2):90–6.
- [60] El-Tayeb TS, Abdelhafez AA, Ali SH, Ramadan EM. Effect of acid hydrolysis and fungal biotreatment on agro-industrial wastes for obtainment of free sugars for bioethanol production. *Braz J Microbiol* 2012;43(4):1523–35.

- [61] Daud Z, Mohd Hatta MZ, Mohd Kassim AS, Awang H, Mohd Aripin A. Exploring of agro waste (pineapple leaf, corn stalk, and napier grass) by chemical composition and morphological study. *BioResources* 2014;9(1):872–80.
- [62] Mishra S, Misra M, Tripathy SS, Nayak SK, Mohanty AK. Potentiality of pineapple leaf fibre as reinforcement in PALF-polyester composite: Surface modification and mechanical performance. *J Reinf Plast Compos* 2001;20(4):321–34.
- [63] Moya R, Muñoz F, Mata JS, Soto RF. An anatomical comparison between bunch and fruit of oil palm with pineapple leaf and three woods from plantations in Costa Rica. *J Oil Palm Res* 2013;25(1):138–48.
- [64] Alwani MS, Abdul Khalil HPS, Islam MN, Sulaiman O, Zaidon A, Dungani R. Microstructural study, tensile properties, and scanning electron microscopy fractography failure analysis of various agricultural residue fibers. *J Nat Fibers* 2015;12:154–68.
- [65] Leao AL, Sartor SM, Caraschi JC. Natural fibers based composites-technical and social issues. *Mol Cryst Liquid Cryst* 2007;448(1):161–77.
- [66] Wan Nadirah WO, Jawaid M, Al Masri AA, Abdul Khalil HPS, Suhaily SS, Mohamed AR. Cell wall morphology, chemical and thermal analysis of cultivated pineapple leaf fibres for industrial applications. *J Polym Environ* 2012;20:404–11.
- [67] Setyanto RH, Diharjo K, Setyono P, Miasa IM. A preliminary study: the influence of alkali treatment on physical and mechanical properties of coir fiber. *J Mater Sci Res* 2013;2:80–8.
- [68] Arsène MA, Bilba K, Junior HS, Ghavami K. Treatments of non-wood plant fibres used as reinforcement in composite materials. *Mater Res* 2013;16(4):903–23.
- [69] Ganesan S, Mydin MdAO, Mohd Yunus MY. Fire resistance performance of coir fiber-reinforced foamed concrete wall panel. *Adv Environ Biol* 2015;9(4):117–20.
- [70] John VM, Cincotto MA, Sjostrom C, Agopyan V, Oliveira CTA. Durability of slag mortar reinforced with coconut fibre. *Cem Concr Compos* 2005;27(5):565–74.
- [71] Li Z, Wang L, Wang X. Flexural characteristics of coir fiber reinforced cementitious composites. *Fibers Polym* 2006;7(3):286–94.
- [72] Muensri P, Kunanopparat T, Menut P, Siri wattanayotin S. Effect of lignin removal on the properties of coconut coir fiber/wheat gluten biocomposite. *Compos Part A* 2011;42:173–9.
- [73] Satyanarayana KG, Arizaga GGC, Wypych F. Biodegradable composites based on ligno-cellulosic fibers—an overview. *Progr Polym Sci* 2009;34:982–1021.
- [74] Rahman MM, Nayeema TIJ, Jahan MS. Variation of chemical and morphological properties of different parts of banana plant (*Musa paradisiaca*) and their effects on pulping. *Int J Lignocellulosic Prod* 2014;1(2):93–103.
- [75] Abdul Khalil HPS, Alwani MS, Mohd Omar AK. Chemical composition, anatomy, lignin distribution and cell wall structure of Malaysian plant waste fibers. *BioResources* 2006;2:220–32.
- [76] Bilba K, Arsene MA, Ouensanga A. Study of banana and coconut fibers botanical composition, thermal degradation and textural observations. *Bioresour Technol* 2007;98:58–68.
- [77] Deepa B, Abraham E, Cherian BM, Bismarck A, Blaker JJ, Pothan LA, et al. Structure, morphology and thermal characteristics of banana nano fibers obtained by steam explosion. *Bioresour Technol* 2011;102:1988–97.
- [78] Yu G, Li B, Liu C, Zhang Y, Wang H, Mu X. Fractionation of the main components of corn stover by formic acid and enzymatic saccharification of solid residue. *Ind Crops Prod* 2013;50:750–7.
- [79] Shibata S. Effects of forming processing condition on the flexural properties of bagasse and bamboo plastic composite. *BioResources* 2012;7(4):5381–90.
- [80] He J, Tang Y, Wang SY. Differences in morphological characteristics of bamboo fibres and other natural cellulose fibres: studies on X-ray diffraction, solid state ¹³C-CP/MAS NMR, and second derivative FTIR spectroscopy data. *Iran Polym J* 2007;16(12):807–18.

- [81] Murali K, Mohana K. Extraction and tensile properties of natural fibers: Vakka, date and bamboo. *Compos Struct* 2007;77:288–95.
- [82] Ghasemi I, Mirbagheri J, Tajvidi M, Hermanson JC. Prediction of the elastic modulus of wood flour/kenaf fibre/polypropylene hybrid composites. *Iran Polym J* 2007;16:271–8.
- [83] Phong NT, Fujii T, Chuong B, Okubo K. Study on how to effectively extract bamboo fibers from raw bamboo and wastewater treatment. *J Mater Sci Res* 2012;1(1):144–55.
- [84] Li X, Tabil LG, Panigrahi S. Chemical treatments of natural fiber for use in natural fiber-reinforced composites: a review. *J Polym Environ* 2007;15(1):25–33.
- [85] Wang YP, Wang G, Cheng HT. Structures of bamboo fiber for textiles. *Text Res J* 2010;84(4):334–43.
- [86] Abdul Khalil HPS, Alwani MS, Ridzuan R, Kamarudin H, Khairul A. Chemical composition, morphological characteristics and cell wall structure of Malaysian oil palm fibers. *Polymer-Plastics Technol Eng* 2008;47:273–80.
- [87] Ewulonu CM, Igwe IO. Properties of oil palm empty fruit bunch fibre filled high density polyethylene. *Int J Eng Technol* 2012;3(6):458–71.
- [88] Law KN, Wan Rosli WD, Arniza G. Morphological and chemical nature of fiber strands of oil palm empty-fruit-bunch (OPEFB). *BioResources* 2007;2(3):351–60.
- [89] Then YY, Ibrahim NA, Zainuddin N, Ariffin H, W Md Zin Wan Yunus, Chieng BW. Static mechanical, interfacial, and water absorption behaviors of alkali treated oil palm mesocarp fiber reinforced poly(butylene succinate) biocomposite. *BioResources* 2015;10(1):123–36.
- [90] Gassan J, Chate A, Bledzki AK. Calculation of elastic properties of natural fibers. *J Mater Sci* 2001;36:3715–20.
- [91] Vijayalakshmi K, Neeraja CYK, Kavitha A, Hayavadana J. Abaca fibre. *Trans Eng Sci* 2014;2:16–19.
- [92] Fávaro SL, Ganzerli TA, de Carvalho Neto AGV, da Silva ORRF, Radovanovic E. Chemical, morphological and mechanical analysis of sisal fiber-reinforced recycled high-density polyethylene composites. *EXPRESS Polym Lett* 2010;4(8):465–73.
- [93] Shahinur S, Hasan M, Ahsan Q, Saha DK, Islam MdS. Characterization on the properties of jute fiber at different portions. *Int J Polym Sci* 2015 2015:1–6.
- [94] Baheti VK, Abbasi R, Militky J. Ball milling of jute fibre wastes to prepare nanocellulose. *World J Eng* 2012;9(1):45–50.
- [95] Mwaikambo LY. Tensile properties of alkalised jute fibres. *BioResources* 2009;4(2):566–88.
- [96] Shibata M, Ozawa K, Teramoto N, Yosomiya R, Takeishi H. Biocomposites made from short abaca fiber and biodegradable polyesters. *Macromol Mater Eng* 2003;288:35–43.
- [97] Shibata M, Takachiyo KI, Ozawa K, Yosomiya R, Takeishi H. Biodegradable polyester composites reinforced with short abaca fiber. *J Appl Polym Sci* 2002;85:129–38.
- [98] Cai M, Takagi H, Nakagaito AN, Katoh M, Ueki T, Waterhouse GIN, et al. Influence of alkali treatment on internal microstructure and tensile properties of abaca fibers. *Ind Crops Prod* 2015;65:27–35.
- [99] Del Rio JC, Gutierrez A. Chemical composition of abaca (*Musa textilis*) leaf fibers used for manufacturing of high quality paper pulps. *J Agric Food Chem* 2006;54:4600–10.
- [100] Pai AR, Jagtap RN. Surface morphology and mechanical properties of some unique natural fiber reinforced polymer composites—a review. *J Mater Environ Sci* 2015;6(4):902–17.
- [101] Huang X, Lim TT. Performance and mechanism of a hydrophobic-oleophilic kapok filter for oil/water separation. *Desalination* 2006;190:295–307.

- [102] Chung BY, Cho JY, Lee MH, Wi SG, Kim JH, Kim JS, et al. Adsorption of heavy metal ions onto chemically oxidized *Ceiba pentandra* (L.) Gaertn. (Kapok) Fibers. *J Appl Biol Chem* 2008;51:28–35.
- [103] Chaiarrekij S, Apirakchaiskul A, Suvarnakich K, Kiatkamjornwong S, Kapok I. Characteristics of kapok fiber as a potential pulp source for papermaking. *BioResources* 2011;7:475–88.
- [104] Anigo KM, Dauda BMD, Sallau AB, Chindo IE. Chemical composition of kapok (*Ceibapentandra*) seed and physicochemical properties of its oil. *Niger J Basic Appl Sci* 2013;21:105–8.
- [105] Rijavec T. Kapok in technical textiles. *Tekstilec* 2008;51(10–12):319–31.
- [106] Abdul Khalil HPS, Suraya NL. Anhydride modification of cultivated kenaf bast fibers: morphological, spectroscopic and thermal studies. *BioResources* 2011;6(2): 1122–35.
- [107] Thiruchitrabalam M, Alavudeen A, Venkateshwaran N. Review on kenaf fiber composites. *Rev Adv Mater Sci* 2012;32:106–12.
- [108] Safinas A, Saad Md, Bakar AA, Ismail H. Properties of kenaf bast powder-filled high density polyethylene/ethylene propylene diene monomer composites. *BioResources* 2013;8(2):2386–97.
- [109] Jonoobi M, Harun J, Shakeri A, Misra M, Oksman K. Chemical composition, crystallinity, and thermal degradation of bleached and unbleached kenaf bast (*Hibiscus cannabinus*) pulp and nanofibers. *BioResources* 2009;4(2):626–39.
- [110] Biagiotti J, Fiori S, Torre L, Lopez-Manchado MA, Kenny JM. Mechanical properties of polypropylene matrix composites reinforced with natural fibers: a statistical approach. *Polym Compos* 2004;25(1):26–36.
- [111] Puglia D, Biagiotti J, Kenny JM. A review on natural fibre-based composites—part II. *J Nat Fibres* 2005;1:23–65.
- [112] Sumaila M, Amber I, Bawa M. Effect of fiber length on the physical and mechanical properties of random oriented, nonwoven short banana (*Musa balbisiana*) fibre/epoxy composite. *Asian J Nat Applied Sci* 2013;2:39–49.
- [113] Sakthivel M, Ramesh S. Mechanical properties of natural fiber (banana, coir, sisal) polymer composites. *Sci Park* 2013;1:1–6.
- [114] Bouasker M, Belayachi N, Hoxha D, Al-Mukhtar M. Physical characterization of natural straw fibers as aggregates for construction materials applications. *Materials* 2014;7:3034–48.
- [115] Alves C, Ferrao PMC, Freitas M, Silva AJ, Luz SM, Alves DE. Sustainable design procedure: the role of composite materials to combine mechanical and environmental features for agricultural machines. *Mater Design* 2009;30:4060–8.
- [116] Bongarde US, Shinde VD. Review on natural fiber reinforcement polymer composites. *Int J Eng Sci Innovat Technol* 2014;3:431–6.
- [117] Wambua P, Ivens J, Verpoest I. Natural fibres: can they replace glass in fibre reinforced plastics? *Compos Sci Technol* 2003;63(9):1259–64.
- [118] Munawar SS, Umemura K, Kawai S. Characterization of the morphological, physical, and mechanical properties of seven non-wood plant fibre bundles. *J Wood Sci* 2007;53(2):108–13.
- [119] Paridah M, Khalina A. Effects of soda retting on the tensile strength of kenaf (*Hibiscus cannobnius* L.) bast fibres. *Project Report Kenaf EPU* 2009;14(Suppl. 1):21–8.
- [120] Rathod A, Kolhatkar A. Analysis of physical characteristics of bamboo fabrics. *Int J Res Eng Technol* 2014;03(08):21–5.

- [121] Mwaikambo LY, Ansell MP. The determination of porosity and cellulose content of plant fibers by density methods. *J Mater Sci Lett* 2001;20:2095–6.
- [122] Mojica ERE, Merca FE, Micor JRL. Fiber of kapok (*Ceiba pentandra*) as component of a metal sensor for lead in water samples. *Philippine J Crop Sci* 2002;27:37–42.
- [123] Mariano M, El Kissi N, Dufresne A. Cellulose nanocrystals and related nanocomposites: review of some properties and challenges. *J Polym Sci Part B: Polym Phys* 2014;52(12):791–806.
- [124] Liu D, Chen X, Yue Y, Chen M, Wu Q. Structure and rheology of nanocrystalline cellulose. *Carbohydr Polym* 2011;84:316–22.
- [125] Moon RJ, Martini A, Nairn J, Simonsen J, Youngblood J. Cellulose nanomaterials review: structure, properties and nanocomposites. *Chem Soc Rev* 2011;40(7):3941–94.
- [126] Abdul Khalil HPS, Bhat AH, Ireana Yusra AF. Green composites from sustainable cellulose nanofibrils: a review. *Carbohydr Polym* 2012;87:963–79.
- [127] Abdul Khalil HPS, Davoudpour Y, Islam MN, Mustapha A, Sudesh K, Dungani R, et al. Production and modification of nanofibrillated cellulose using various mechanical processes: a review. *Carbohydr Polym* 2014;99:649–65.
- [128] Jonoobi M, Khazaeian A, Tahir PM, Azry SS, Oksman K. Characteristics of cellulose nanofibers isolated from rubberwood and empty fruit bunches of oil palm using chemo-mechanical process. *Cellulose* 2011;18:1085–95.
- [129] Fahma F, Iwamoto S, Hori N, Iwata T, Takemura A. Isolation, preparation, and characterization of nanofibers from oil palm empty-fruit-bunch (OPEFB). *Cellulose* 2010;17:977–85.
- [130] Fahma F, Iwamoto S, Hori N, Iwata T, Takemura A. Effect of pre-acid-hydrolysis treatment on morphology and properties of cellulose nanowhiskers from coconut husk. *Cellulose* 2011;18:443–50.
- [131] Nazir MS, Wahjoedi BA, Yusof AW, Abdullah MA. Eco-friendly extraction and characterization of cellulose from oil palm empty fruit bunches. *BioResources* 2013;8:2161–72.
- [132] Brinchi L, Cotana F, Fortunati E, Kenny JM. Production of nanocrystalline cellulose from lignocellulosic biomass: technology and applications. *Carbohydr Polym* 2013;94:154–69.
- [133] Zhu H, Fang Z, Preston C, Li Y, Hu L. Transparent paper: fabrications, properties, and device applications. *Energy Environ Sci* 2014;7(1):269–87.
- [134] Tang Y, He Z, Mosseler JA, Ni Y. Production of highly electro-conductive cellulosic paper via surface coating of carbon nanotube/graphene oxide nanocomposites using nanocrystalline cellulose as a binder. *Cellulose* 2014;21(6):4569–81.
- [135] Miao C, Hamad WY. Cellulose reinforced polymer composites and nanocomposites: a critical review. *Cellulose* 2013;20(5):2221–62.
- [136] Metreveli G, Wagberg L, Emmoth E, Belak S, Stromme M, Mihranyan A. A size-exclusion nanocellulose filter paper for virus removal. *Adv Healthcare Mater* 2014;3(10):1546–50.
- [137] Lin N, Dufresne A. Nanocellulose in biomedicine: current status and future prospect. *Eur Polym J* 2014;59:302–25.
- [138] Chen W, Li Q, Cao J, Liu Y, Li J, Zhang J, et al. Revealing the structures of cellulose nanofiber bundles obtained by mechanical nanofibrillation via TEM observation. *Carbohydr Polym* 2015;117:950–6.
- [139] Ayrimis N, Jarusombuti S, Fueangvivat V, Bauchongkol P, White R. Coir fiber reinforced polypropylene composite panel for automotive interior applications. *Fibers Polym* 2011;12(7):919–26.
- [140] Bajwa SG, Bajwa DS, Holt G, Coffelt T, Nakayama F. Properties of thermoplastic composites with cotton and guayule biomass residues as fiber fillers. *Ind Crops Prod* 2011;33:747–55.

- [141] Chand N, Prajapati SC, Singh RK. Development and characterization of sisal nano fibre reinforced polyolefin composites. *J Sci Res Rev* 2012;1(3):026–32.
- [142] Aprilia NAS, Abdul Khalil HPS, Bath AH, Dungani R, Hossain SMd. Exploring material properties of vinyl ester biocomposites filled carbonized jatropha seed shell. *BioResources* 2014;9(3):4888–98.
- [143] Li W, Wu Q, Zhao X, Huang Z, Cao J, Li J, et al. Enhanced thermal and mechanical properties of PVA composites formed with filamentous nanocellulose fibrils. *Carbohydr Polym* 2014;113:403–10.
- [144] Chaker A, Mutjé P, Vilar MR, Boufi S. Agriculture crop residues as a source for the production of nanofibrillated cellulose with low energy demand. *Cellulose* 2014;21(6):4247–59.
- [145] Pääkkö M, Ankerfors M, Kosonen H, Nykänen A, Ahola S, Österberg M, et al. Enzymatic hydrolysis combined with mechanical shearing and high-pressure homogenization for nanoscale cellulose fibrils and strong gels. *Biomacromolecules* 2007;8(6):1934–41.
- [146] Stenstad P, Andresen M, Tanem BS, Stenius P. Chemical surface modifications of microfibrillated cellulose. *Cellulose* 2008;15(1):35–45.
- [147] Siro I, Placket D. Microfibrillated cellulose and new nanocomposite materials: a review. *Cellulose* 2010;17:459–94.
- [148] Li W, Zhao X, Liu S. Preparation of entangled nanocellulose fibers from APMP and its magnetic functional property as matrix. *Carbohydr Polym* 2013;94:278–85.
- [149] Zoppe JO, Ruottinen V, Ruotsalainen J, Rönkkö S, Johansson LS, Hinkkanen A, et al. Synthesis of cellulose nanocrystals carrying tyrosine sulfate mimetic ligands and inhibition of alphavirus infection. *Biomacromolecules* 2014;15(4):1534–42.
- [150] Brioude MM, Roucoules V, Haidara H, Vonna L, Laborie MP. Role of cellulose nanocrystals on the microstructure of maleic anhydride plasma polymer thin films. *ACS Appl Mater Interfaces* 2015;7(25):14079–88.
- [151] Azizi Samir MAS, Alloin F, Dufrene A. Review of recent research into cellulosic whiskers, their properties and their application in nanocomposite field. *Biomacromolecules* 2005;6(2):612–26.
- [152] Iwamoto S, Nakagaito AN, Yano H. Nano-fibrillation of pulp fibers for the processing of transparent nanocomposites. *Appl Phys A Mater Sci Process* 2007;89:461–6.
- [153] Bhatnagar A, Sain M. Processing of cellulose nanofiber-reinforced composites. *J Reinf Plast Compos* 2005;24:1259–68.
- [154] Cranston ED, Gray DG. Morphological and optical characterization of polyelectrolyte multilayers incorporating nanocrystalline cellulose. *Biomacromolecules* 2006;7:2522–30.
- [155] Lamaming J, Hashim R, Sulaiman O, Leh CP, Sugimoto T, Nordin NA. Cellulose nanocrystals isolated from oil palm trunk. *Carbohydr Polym* 2015;127:202–8.
- [156] Haafiz MKM, Eichhorn SJ, Hassana A, Jawaid M. Isolation and characterization of microcrystalline cellulose from oil palm biomass residue. *Carbohydr Polym* 2013;93:628–34.
- [157] Krishnan VN, Ramesh A. Synthesis and characterization of cellulose nanofibers from coconut coir fibers. *IOSR J Appl Chem* 2013;6(3):18–23.
- [158] Saurabh CK, Dungani R, Owolabi AF, Atiqah NS, Zaidon A, Aprilia NAS, et al. Effect of hydrolysis treatment on cellulose nanowhiskers from oil palm (*Elaeis guineensis*) fronds: morphology, chemical, crystallinity, and thermal characteristics. *BioResources* 2016;11(3):6742–55.
- [159] Fatah IYA, Abdul Khalil HPS, Hossain MdS, Aziz AA, Davoudpour Y, Dungani R, et al. Exploration of a chemo-mechanical technique for the isolation of nanofibrillated cellulosic fiber from oil palm empty fruit bunch as a reinforcing agent in composites materials. *Polymers* 2014;6:2611–24.

- [160] Chao D, Liu M, Li B, Li H, Meng Q, Zhan H. Cellulose nano crystals prepared by per-sulfate one-step oxidation of bleached bagasse pulp. *BioResources* 2016;11(2):4017–24.
- [161] Sheltami RM, Abdullah I, Ahmad I, Dufresne A, Kargarzadeh H. Extraction of cellulose nanocrystals from mengkuang leaves (*Pandanus tectorius*). *Carbohydr Polym* 2012;88(2):772–9.
- [162] Saritha S, Nair SM, Kumar NC. Nano-ordered cellulose containing I α crystalline domains derived from the algae chaetomorpha antennina. *BioNano Sci* 2013;3(4):423–7.
- [163] Johar N, Ahmad I, Dufresne A. Extraction, preparation and characterization of cellulose fibres and nanocrystals from rice husk. *Ind Crop Prod* 2012;37(1):93–9.
- [164] Dufresne A. Processing of polymer nanocomposites reinforced with cellulose nanocrystals: a challenge. *Int Polym Proc* 2012;27(5):557–64.
- [165] Jan JS, Chen PS, Hsieh PL, Chen BY. Silicification of genipin-cross-linked polypeptide hydrogels toward biohybrid materials and mesoporous oxides. *ACS Appl Mater Interfaces* 2012;4(12):6865–74.
- [166] Jonoobi M, Mathew AP, Oksman K. Producing low-cost cellulose nanofiber from sludge as new source of raw materials. *Ind Crop Prod* 2012;40:232–8.
- [167] Seo HJ, Kim S, Huh W, Park KW, Lee DR, Son DW, et al. Enhancing the flame-retardant performance of wood-based materials using carbon-based materials. *J Therm Anal Calorim* 2015;123(3):1935–42.
- [168] Alemdar A, Sain M. Isolation and characterization of nanofibers from agricultural residues -wheat straw and soy hulls. *Bioresour Technol* 2008;99:1664–71.
- [169] Cherian BM, Leão AL, de Souza SF, Thomas S, Pothan LA, Kottaisamy M. Isolation of nanocellulose from pineapple leaf fibres by steam explosion. *Carbohydr Polym* 2010;81(3):720–5.
- [170] Chen WS, Yu HP, Liu YX, Chen P, Zhang MX, Hai YF. Individualization of cellulose nanofibers from wood using high-intensity ultrasonication combined with chemical pretreatments. *Carbohydr Polym* 2011;83(4):1804–11.
- [171] He X, Xiao Q, Lu C, Wang Y, Zhang X, Zhao J, et al. Uniaxially aligned electrospun all-cellulose nanocomposite nanofibers reinforced with cellulose nanocrystals: scaffold for tissue engineering. *Biomacromolecules* 2014;15:618–27.
- [172] Aprilia NAS, Hosain MdS, Musthapha A, Suhaily SS, Noruliani NAN, Peng LC, et al. Optimizing the isolation of microfibrillated bamboo in high pressure enzymatic hydrolysis. *BioResources* 2015;10(3):5305–16.
- [173] Lynd LR, Weimer PJ, van Zyl WH, Pretorius IS. Microbial cellulose utilization: fundamentals and biotechnology. *Microbiol Mol Biol Rev* 2002;66(3):506–77.
- [174] Bai S, Ravi kumar M, Mukesh kumar DJ, Balashanmugam P, Bala kumaran MD, Kalaichelvan PT. Cellulase production by *Bacillus subtilis* isolated from Cow Dung. *Arch Appl Sci Res* 2012;4(1):269–79.
- [175] Ahmed S, Saiqa Ikram S. Synthesis of gold nanoparticles using plant extract: an overview. *Nano Res Appl* 2015;1:1–5.
- [176] Sethi S, Datta A, Lal Gupta B, Gupta S. Optimization of cellulase production from bacteria isolated from soil. *ISRN Biotechnol* 2013;2013:1–7.
- [177] Patagundi BI, Shivasharan CT, Kaliwal BB. Isolation and characterization of cellulase producing bacteria from soil. *Int J Curr Microbiol App Sci* 2014;3(5):59–69.
- [178] Siqueira G, Bras J, Dufresne A. Cellulosic bionanocomposites: a review of preparation, properties and applications. *Polymers* 2010;2:728–65.
- [179] Menezes AJ, Siqueira G, Curvelo AAS, Dufresne A. Extrusion and characterization of functionalized cellulose whiskers reinforced polyethylene nanocomposites. *Polymer* 2009;50:4552–63.

- [180] Sakurada I, Nukushina Y, Ito T. Experimental determination of the elastic modulus of crystalline regions in oriented polymers. *J Polym Sci* 1962;57(165):651–60.
- [181] Zimmerman T, Poehler E, Geiger T. Cellulose fibrils for polymer reinforcement. *Adv Eng Mater* 2004;6:754–61.
- [182] Eichhorn SJ. Cellulose nanowhiskers: promising materials for advanced applications. *Soft Matter* 2011;7:303–15.
- [183] Eichhorn SJ, Baillie C, Zafereiropoulos N, Mwaikambo L, Ansell M, Dufresne A, et al. Current international research into cellulosic fibres and composites. *J Mater Sci* 2001;36(9):2107–31.
- [184] Lee SY, Chun SJ, Kang IA, Park JY. Preparation of cellulose nanofibrils by high-pressure homogenizer and cellulose-based composite films. *J Ind Eng Chem* 2009;15(1):50–5.
- [185] Gardner DJ, Oporto GS, Mills R, Samir ASA. Adhesion and surface issue in cellulose and nanocellulose. *J Adhes Sci Technol* 2008;22:545–67.
- [186] Iwamoto S, Kai W, Isogai A, Iwata T. Elastic modulus of single cellulose microfibrils from tunicate measured by atomic force microscopy. *Biomacromolecules* 2009;10:2571–6.
- [187] Nuruddin M, Chowdhury A, Haque SA, Rahman M, Farhad F, Jahan S, et al. Extraction and characterization of cellulose microfibrils from agriculture waste in an integrated biorefinery initiative. *Cellulose Chem Technol* 2011;45(5–6):347–54.
- [188] Qing Y, Sabo R, Zhu JY, Agarwal U, Cai Z, Wu Y. A comparative study of cellulose nanofibrils disintegrated via multiple processing approaches. *Carbohydr Polym* 2013;97(1):226–34.
- [189] Liu ZT, Yang Y, Zhang L, Liu ZW, Xiong H. Study on the cationic modification and dyeing of ramie fiber. *Cellulose* 2007;14(4):337–45.
- [190] Roman M, Winter WT. Effect of sulfate groups from sulfuric acid hydrolysis on the thermal degradation behavior of bacterial cellulose. *Biomacromolecules* 2004;5:1671–7.
- [191] Elazzouzi-Hafraoui S, Nishiyama Y, Putaux JL, Heux L, Dubreuil F, Rochas C. The shape and size distribution of crystalline nanoparticles prepared by acid hydrolysis of native cellulose. *Biomacromolecules* 2008;9(1):57–65.
- [192] Martínez-Sanz M, Lopez-Rubio A, Lagaron JM. Optimization of the nanofabrication by acid hydrolysis of bacterial cellulose nanowhiskers. *Carbohydr Polym* 2011;85(1):228–36.
- [193] Chen W, Li Q, Wang Y, Yi X, Zeng J, Yu H, et al. Comparative study of aerogels obtained from differently prepared nanocellulose fibers. *Chem Sus Chem* 2014;7(1):154–61.
- [194] Isogai T, Saito T, Isogai A. Wood cellulose nanofibrils prepared by TEMPO electro-mediated oxidation. *Cellulose* 2010;18(2):421–31.
- [195] Saito T, Hirota M, Tamura N, Kimura S, Fukuzumi H, Heux L, et al. Individualization of nano-sized plant cellulose fibrils by direct surface carboxylation using TEMPO catalyst under neutral conditions. *Biomacromolecules* 2009;10(7):1992–6.
- [196] Sun X, Wu Q, Ren S, Lei T. Comparison of highly transparent all-cellulose nanopaper prepared using sulfuric acid and TEMPO-mediated oxidation methods. *Cellulose* 2015;22(2):1123–33.
- [197] Mariño M, Da Silva LP, Durán N, Tasic L. Enhanced materials from nature: nanocellulose from citrus waste. *Molecules* 2015;20:5908–23.
- [198] Haafiz MK, Hassan A, Zakaria Z, Inuwa IM. Isolation and characterization of cellulose nanowhiskers from oil palm biomass microcrystalline cellulose. *Carbohydr Polym* 2014;103:119–25.
- [199] Nisha SN, Aysha OS, Rahaman JSN, Kumar PV, Valli S, Nirmala P, et al. Lemon peels mediated synthesis of silver nanoparticles and its antidermatophytic activity. *Spectrochim Acta Part A Mol Biomol Spectros* 2014;124(24):194–8.

- [200] Purkait BS, Ray D, Sengupta S, Kar T, Mohanty A, Misra M. Isolation of cellulose nanoparticles from sesame husk. *Ind Eng Chem Res* 2011;50:871–6.
- [201] Abdul Khalil HPS, Fizree HM, Jawaid M, Alattas OS. Preparation and characterization of nano-structured materials from oil palm ash: a bio-agricultural waste from oil palm mill. *BioResources* 2011;6(4):4537–46.
- [202] Sulaeman A, Dungani R, Islam MN, Abdul Khalil HPS, Sumardi I, Hermawan D, et al. Preliminary study of characterization of nanoparticles from coconut shell as filler agent in composites materials. *MAYFEB J Mater Sci* 2016 2016;1:1–9.
- [203] Jiang J, Oberdorster G, Biswas P. Characterization of size, surface charge and agglomeration state of nanoparticle dispersions for toxicological studies. *Nanopart Res* 2009;11:77–89.
- [204] Paul K, Satpathy S, Manna I, Chakraborty K, Nando G. Preparation and characterization of nano structured materials from fly ash: a waste from thermal power stations, by high energy ball milling. *Nanosc Res Lett* 2007;2:397–404.
- [205] Andersen TR, Yan Q, Larsen-Olsen TT, Søndergaard R, Li Q, Andreasen B, et al. A nanoparticle approach towards morphology controlled organic photovoltaics (OPV). *Polymers* 2012;4:1242–58.
- [206] Bi Y, Luo R, Li J, Feng Z, Jin Z. The effects of the hydraulic oil on mechanical and tribological properties of C/C composites. *Mater Sci Eng A* 2008;483–484:274–6.
- [207] Yahaya S, Giwa SO, Ibrahim M, Giwa A. Extraction of oil from jatropa seed kernels: optimization and characterization. *Int J ChemTech Res* 2016;9(05):758–70.
- [208] Liauw MY, Natan F, Widiyanti P, Ikasari D, Indraswati N, Soetaredjo F. Extraction of neem oil (*Azadirachta indica* A. Juss) using n-hexane and ethanol: studies of oil quality, kinetic and thermodynamic. *ARNP J Eng Appl Sci* 2008;3:49–54.
- [209] Damien MM, Éric G, Carine CJ. Properties of nanofillers in polymer. In: John C, editor. *Nanocomposites and polymers with analytical methods*. France: InTech. p. 281–304.
- [210] Bhat IH, Abdul Khalil HPS. Exploring “nano filler” based on oil palm ash in polypropylene composites. *Bioresources* 2011;6(2):1286–97.
- [211] Sutrisno Syamsudin TS, Alamsyah EM, Purwasasmita BS. Synthesis and characterization of bio-based nanomaterials from jabon (*Anthocephalus cadamba* (Roxb.) Miq) wood bark: an organic waste material from community forest. *J Math Fundam Sci* 2015;47(2):205–18.
- [212] Eberhardt TL, Reed KG. Strategies for improving the performance of plywood adhesive mix fillers from Southern yellow pine bark. *For Prod J* 2006;56(10):64–8.
- [213] Akbari B, Tavandashti MP, Zandrahimi M. Particle size characterization of nanoparticles—a practical approach. *Iran J Mater Sci Eng* 2011;8(2):48–56.
- [214] Dungani R, Islam N, Abdul Khalil HPS, Hartati S, Abdullah CK, Dewi M, et al. Termite resistance study of oil palm trunk lumber (OPTL) impregnated with oil palm shell meal and phenol-formaldehyde resin. *BioResources* 2013;8(4):4937–50.
- [215] Mollick MdMR, Rana D, Dash SK, Chattopadhyay S, Bhowmick B, Maity D, et al. Studies on green synthesized silver nanoparticles using *Abelmoschus esculentus* (L.) pulp extract having anticancer (in vitro) and antimicrobial applications. *Arab J Chem* 2015. doi:10.1016/j.arabjc.2015.04.033.
- [216] Ghaedi M, Jahromi MN, Sajedi M, Mousavi H. Comparison of modified palladium nanoparticles and homemade activated carbon derived from medlar for solid phase extraction of metal ions prior to their flame atomic absorption spectrometry determination. *Environ Stud Persian Gulf* 2015;2(1):1–14.
- [217] Savin DA, Pyun J, Patterson GD, Kowalewski T, Matyjaszewski KJ. Synthesis and characterization of silica-graft-polystyrene hybrid nanoparticles: effect of constraint on

- the glass-transition temperature of spherical polymer brushes. *Polym Sci Part B: Polym Phys* 2002;40:2667–76.
- [218] Liu L, Ding X, Li J, Luo Z, Hu Y, Liu J, et al. Enzyme responsive drug delivery system based on mesoporous silica nanoparticles for tumor therapy *in vivo*. *Nanotechnology* 2015;26(14):15–24.
- [219] Vaibhav V, Vijayalakshmi U, Mohana Roopan S. Agricultural waste as a source for the production of silica nanoparticles. *Spectrochim Acta Part A* 2015;139:515–20.
- [220] Hariharan V, Sivakumar G. Studies on synthesized nanosilica obtained from bagasse ash. *Int J ChemTech Res* 2013;5(3):1263–6.
- [221] Djangang CN, Mlowe S, Njopwouo D, Revaprasadu N. One-step synthesis of silica nanoparticles by thermolysis of rice husk ash using non toxic chemicals ethanol and polyethylene glycol. *J Appl Chem* 2015;4(4):1218–26.
- [222] Ghorbani F, Sanati AM, Maleki M. Production of silica nanoparticles from rice husk as agricultural waste by environmental friendly technique. *Environ Stud Persian Gulf* 2015;2(1):56–65.
- [223] Chen H, Wang W, Martin JC, Oliphant AJ, Doerr PA, Xu JF, et al. Extraction of ligno-cellulose and synthesis of porous silica nanoparticles from rice husks: a comprehensive utilization of rice husk biomass. *ACS Sustain Chem Eng* 2013;1:254–9.
- [224] Vaccaro L, Spallino L, Agnello S, Buscarino G, Cannas M. Defect-related visible luminescence of silica nanoparticles. *Phys Status Solidi C* 2013;10(4):658–61.
- [225] Bankar A, Joshi B, Kumar AR, Zinjarde S. Banana peel extract mediated novel route for the synthesis of AgNPs. *Colloids Surf A* 2010;368(1):58–63.
- [226] Regan BC, Aloni S, Jensen K, Ritchie RO, Zettl A. Nanocrystal-powered nanomotor. *Nano Lett* 2005;5(9):1730–3.
- [227] Gojny F, Nastalczyk J, Roslaniec Z, Schulte K. Surface modified multi-walled carbon nanotubes in CNT/epoxy-composites. *Chem Phys Lett* 2003;370(5–6):820–4.
- [228] Fukushima H, Drzal LT, Rook BP, Rich MJ. Thermal conductivity of exfoliated graphite nanocomposites. *J Therm Anal Calorim* 2006;85:235–8.
- [229] Kalaitzidou K, Fukushima H, Drzal LT. Mechanical properties and morphological characterization of exfoliated graphite–polypropylene nanocomposites. *Compos Part A* 2007;38(7):1675–82.
- [230] Ramya R, Sudha PN, Mahalakshmi J. Preparation and characterization of chitosan binary blend. *Int J Scientif Res Publ* 2012;2:1–9.
- [231] Khan A, Vu KD, Chauve G, Bouchard J, Riedl B, Lacroix M. Optimization of microfluidization for the homogeneous distribution of cellulose nanocrystals (CNCs) in biopolymeric matrix. *Cellulose* 2014;21:3457–68.
- [232] Shalwan A, Yousif BF. In state of art: mechanical and tribological behaviour of polymeric composites based on natural fibres. *Mater Des* 2013;48:14–24.
- [233] Gassan J, Gutowski VS. Effects of corona discharge and UV treatment on the properties of jute-fibre epoxy composites. *Compos Sci Technol* 2000;60(15):2857–63.
- [234] Ragoubi M, Bienaimé D, Molina S, George B, Merlin A. Impact of corona treated hemp fibres onto mechanical properties of polypropylene composites made thereof. *Ind Crops Prod* 2010;31(2):344–9.
- [235] Li Z, Wang L, Wang X. Cement composites reinforced with surface modified coir fibers. *J Compos Mater* 2007;41(12):1445–57.
- [236] Belgacem MN, Gandini A. The surface modification of cellulose fibres for use as reinforcing elements in composite materials. *Compos Interfaces* 2005;12(1–2):41–75.
- [237] Leblanc JL. Rubber–filler interactions and rheological properties in filled compounds. *Prog Polym Sci* 2002;27(4):627–87.

- [238] Ooi ZX, Ismail H, Bakar AA. Optimisation of oil palm ash as reinforcement in natural rubber vulcanisation: a comparison between silica and carbon black fillers. *Polym Test* 2013;32(4):625–30.
- [239] Cao Y, Shibata S, Fukumoto I. Mechanical properties of biodegradable composite reinforced with bagasse fibre before and after alkali treatments. *Compos Part A* 2006;37:423–9.
- [240] Kondawar SB, Pethe SM. Synthesis and characterization of nanofibers of conducting polyaniline and its substitute derivatives. *Adv Mater Lett* 2014;5(7):414–20.
- [241] Masoodi R, El-Hajjar RF, Pillai KM, Sabo R. Mechanical characterization of cellulose nanofiber and bio-based epoxy composite. *Mater Des* 2012;36:570–6.
- [242] Liu H, Bai J, Wang Q, Li C, Wang S, Sun W, et al. Preparation and characterization of silver nanoparticles/carbon nanofibers via electrospinning with research on their catalytic properties. *NANO Brief Rep Rev* 2014;9(3): 145004-1–145004-7.
- [243] Tabatabaei S, Shukohfar A, Aghababazadeh R, Mirhabibi A. Experimental study of the synthesis and characterisation of silica nanoparticles via the sol-gel method. *J Phys Conf Ser* 2006;26:371–4.
- [244] Singh A, Sharma PK, Malviya R. Eco friendly pharmaceutical packaging material. *World Appl Sci J* 2011;14:1703–16.
- [245] De Moura MR, Mattoso LHC, Zucolotto V. Development of cellulose-based bactericidal nanocomposites containing silver nanoparticles and their use as active food packaging. *J Food Eng* 2012;109:520–4.
- [246] Youssef AM, El-Samahy MA, Abdel Rehim MH. Preparation of conductive paper composites based on natural cellulosic fibers for packaging applications. *Carbohydr Polym* 2012;89:1027–32.
- [247] Kalia S, Boufi S, Celli A, Kango S. Nanofibrillated cellulose: surface modification and potential applications. *Colloid Polym Sci* 2014;292:5–31.
- [248] Nafchi AM, Alias AK, Mahmud S, Robal M. Antimicrobial, rheological, and physico-chemical properties of sago starch films filled with nanorod-rich zinc oxide. *J Food Eng* 2012;113:511–9.
- [249] Zadbuke N, Shahi S, Gulecha B, Padalkar A, Thube M. Recent trends and future of pharmaceutical packaging technology. *J Pharm Bioallied Sci* 2013;5:98–110.
- [250] Chen H. Chemical composition and structure of natural lignocellulose. Chen H, editor. *Biotechnology of lignocellulose*. Dordrecht: Springer; 2014. p. 25–71.
- [251] Marsh K, Bugusu B. Food packaging-roles, materials, and environmental issues. *J Food Sci* 2007;72:39–55.
- [252] Lewis H, Verghese K, Fitzpatrick L. Evaluating the sustainability impacts of packaging: the plastic carry bag dilemma. *Pack Technol Sci* 2010;23:145–60.
- [253] Freire MG, Teles ARR, Ferreira RAS, Carlos LD, Lopes-da-Silva JA, Coutinho JAP. Electrospun nanosized cellulose fibers using ionic liquids at room temperature. *Green Chem* 2011;13:3173–80.
- [254] Zhang X, Tu M, Paice M. Routes to potential bioproducts from lignocellulosic biomass lignin and hemicelluloses. *BioEnergy Res* 2011;4:246–57.
- [255] Ul-Islam M, Khan T, Park JK. Nanoreinforced bacterial cellulose-montmorillonite composites for biomedical applications. *Carbohydr Polym* 2012;89:1189–97.
- [256] Azeredo HMC. Antimicrobial nanostructures in food packaging. *Trends Food Sci Technol* 2013;30:56–69.
- [257] Sirviö JA, Liimatainen H, Niinimäki J, Hormi O. Sustainable packaging materials based on wood cellulose. *RSC Adv* 2013;3:16590–6.

- [258] Ghaderi M, Mousavi M, Yousevi H, Labbafi M. All-cellulose nanocomposites film made from bagasse cellulose nanofibers for food packaging applications. *Carbohydr Polym* 2014;104:59–65.
- [259] Kumar R, Münstedt H. Silver ion release from antimicrobial polyamide/silver composites. *Biomaterials* 2005;26:2081–8.
- [260] Chakraborty A, Sain M, Kortschot M. Cellulose microfibrils as reinforcing agents for structural materials Oksman K, Sain M, editors. *Cellulose nanocomposites: processing, characterization, and properties*. Washington, DC: ACS Symposium Series; 2006. p. 169–86.
- [261] Millon E, Wan WK. The polyvinyl alcohol-bacterial cellulose system as a new nanocomposite for biomedical applications. *J Biomed Mater Res B Appl Biomater* 2006;79(2):245–53.
- [262] Costa LMM, de Olyveira GM, Cherian BM, Leão AL, de Souza SF, Ferreira M. Bionanocomposites from electrospun PVA/pineapple nanofibers/*Stryphnodendron adstringens* bark extract for medical applications. *Ind Crops Prod* 2013;41:198–202.
- [263] Auad ML, Contos VS, Nutt S, Aranguren MI, Marcovich NE. Polyurethane reinforced with nano/micro sized cellulose fibers *Proceedings of the third international conference on science and technology of composite materials*. : COMAT; 2005.
- [264] Baumann MD, Kang CE, Stanwick JC, Wang Y, Kim H, Lapitsky Y, et al. An injectable drug delivery platform for sustained combination therapy. *J Control Release* 2009;138(3):205–13.
- [265] Nadagouda MN, Varma RS. Green synthesis of silver and palladium nanoparticles at room temperature using coffee and tea extract. *Green Chem* 2008;10:859–62.
- [266] Czaja WK, Young DJ, Kawecki M, Brown Jr RM. The future prospects of microbial cellulose in biomedical applications. *Biomacromolecules* 2007;8(1):1–20.
- [267] Iamaguti LS, Brandao CVS, Minto BW, Mamprim MJ, Ranzani JJT, Gomes DC. Utilização de membrana biossintética de celulose na troclectomia experimental em cães. *Avaliações clínica, radiográfica e macroscópica*. *Vet e Zootec* 2008;15: 160–218.
- [268] Macedo NL, Matuda FS, Macedo LGS, Monteiro ASF, Valera MC, Carvalho YR. Evaluation of two membranes in guided bone tissue regeneration: histological study in rabbits. *Braz J Oral Sci* 2004;3:395–400.
- [269] Klemm D, Schumann D, Udhardt U, Marsch S. Bacterial synthesized cellulose-artificial blood vessels for microsurgery. *Prog Polym Sci* 2001;26:1561–603.
- [270] Ikada Y. Challenges in tissue engineering. *J R Soc Interface* 2006;3(10):589–601.
- [271] Kumar R, Roopan SM, Prabhakar A, Khanna VG, Chakraborty S. Agricultural waste *Annona squamosa* peel extract: biosynthesis of silver nanoparticles. *Spectrochim Acta Part A* 2012;90:173–6.
- [272] Seal BL, Otero TC, Panitch A. Polymeric biomaterials for tissue and organ regeneration. *Mater Sci Eng Rep* 2001;34:147–230.
- [273] Capes JS, Ando HY, Cameron REJ. Fabrication of polymeric scaffolds with a controlled distribution of pores. *Mater Sci Mater Med* 2005;16:1069–75.
- [274] Bhattacharya M, Malinen MM, Lauren P, Lou YR, Kuusisto SW, Kanninen L, et al. Nanofibrillar cellulose hydrogel promotes three-dimensional liver cell culture. *J Control Release* 2012;164(3):291–8.
- [275] Hua K, Carlsson DO, Ålander E, Lindström T, Strømme M, Mihranyan A, et al. Translational study between structure and biological response of nanocellulose from wood and green algae. *RSC Adv* 2014;4:2892–903.

- [276] Kiziltas A, Nazari B, Gardner DJ, Bousfield DW. Polyamide 6-cellulose composites: effect of cellulose composition on melt rheology and crystallization behaviour. *Polym Eng Sci* 2013;54(4):739–46.
- [277] Hill K, Swiecki B, Cregger J. The bio-based materials automotive value chain. *Center Automot Res* 2012;2012(Suppl. 20585):S23–7.
- [278] Bartus SD, Vaidya UK, Ulven CA. Design and development of a long fiber thermoplastic bus seat. *Compos Struct* 2005;67:263–77.
- [279] Jeyanthi S, Rani JJ. Improving mechanical properties by kenaf natural long fiber reinforced composite for automotive structures. *J Appl Sci Eng* 2012;15(3):275–80.
- [280] Cicero JA, Dorgan JR, Dec SF, Knauss DM. Phosphite stabilization effects on two step melt-spun fibers of polyactide. *Polym Degrad Stab* 2002;78:95–105.
- [281] Mohanty AK, Misra M, Hinrichsen G. Biofibers, biodegradable polymers and biocomposites: an overview. *Macromol Mater Eng* 2000;276/277:1–24.
- [282] Brouwer WD. Natural fiber composites: where flax compete with glass? *SAMPE J* 2000;36(6):18–23.
- [283] Shinoj S, Visvanathan R, Panigrahi S, Kochubabu M. Oil palm fiber (OPF) and its composites: a review. *Ind Crops Prod* 2011;33(1):7–22.
- [284] Suddell BC, Evans WJ. Natural fiber composites in automotive applications in natural fibers in biopolymers & their biocomposites Mohanty AK, Misra M, Drzal LT, editors. *Natural fibers, biopolymers and biocomposites*. Boca Raton, FL: CRC Press; 2005. p. 231–59.
- [285] Pickering K. *Properties and performance of natural-fibre composites*, 1st ed Cambridge: Woodhead Publishing; 2008.
- [286] Lee S. 2010. An overview of advanced composite material and their industrial applications. <https://www.industryhk.org/upload/media/file/9f0bdc4a82f044576a49a559d4b233fc.pdf>. [accessed 17.07.16].
- [287] François V. 2013. Lineo-flax fibres impregnation. <http://www.lineo.eu>. [accessed 17.07.16].
- [288] Zhou Y, Fan M, Chen L, Zhuang J. Lignocellulosic fibre mediated rubber composites: an overview. *Compos Part B* 2015;76:180–91.
- [289] Watcharakul N, Poompradub S, Prasassarakich P. In situ silica reinforcement of methyl methacrylate grafted natural rubber by sol–gel process. *J Sol-Gel Sci Technol* 2011;58(2):407–18.
- [290] Suhaily SS, Jawaid M, Abdul HPS, Khalil AR, Mohamed IF. A review of oil palm biocomposites for furniture design and applications: potential and challenges. *BioResources* 2012;7(3):4400–23.
- [291] Ismail H, Tan BK, Suharty NS, Husseinayah S. Comparison of the effects of palm oil ash, carbon black and halloysite nanotubes on the properties of polypropylene/recycled natural rubber glove composites. *J Phys Sci* 2015;26(2):89–99.
- [292] Sasthriyar S, Abdul Khalil HPS, Bhat AH, Ahmad ZA, Islam MdZ, Zaidon A, et al. Nanobioceramic composites: a study of mechanical, morphological and thermal properties. *BioResources* 2014;9(1):861–71.
- [293] Sasthriyar S, Abdul Khalil HPS, Ahmad ZA, Islam MdN, Dungani R, Fizree HM. Carbon nanofiller-enhanced ceramic composites: thermal and electrical studies. *BioResources* 2014;9(2):3143–51.
- [294] Wu X, Radovic LR. Inhibition of catalytic oxidation of carbon/carbon composites by phosphorus. *Carbon* 2006;44(1):141–51.

Bionanomaterial from agricultural waste and its application

ORIGINALITY REPORT

8%

SIMILARITY INDEX

5%

INTERNET SOURCES

6%

PUBLICATIONS

2%

STUDENT PAPERS

PRIMARY SOURCES

1	www.springerprofessional.de Internet Source	1 %
2	journals.sagepub.com Internet Source	1 %
3	www.eurelectric.org Internet Source	1 %
4	Submitted to Universiti Kebangsaan Malaysia Student Paper	1 %
5	www.omicsonline.org Internet Source	<1 %
6	www.purevisiontechnology.com Internet Source	<1 %
7	www.tandfonline.com Internet Source	<1 %
8	"Eco-friendly Polymer Nanocomposites", Springer Nature, 2015 Publication	<1 %
9	Submitted to Caledonian College of Engineering Student Paper	<1 %
10	Submitted to School of Business and Management ITB Student Paper	<1 %
11	Ana Carolina Corrêa, Eliangela de Moraes Teixeira, Luiz Antonio Pessan, Luiz Henrique Capparelli Mattoso. "Cellulose nanofibers from curaua fibers", Cellulose, 2010	<1 %

12	M. Sarwar Jahan, Abrar Saeed, Zhibin He, Yonghao Ni. "Jute as raw material for the preparation of microcrystalline cellulose", Cellulose, 2010	<1 %
Publication		
13	M.K. Mohamad Haafiz, Azman Hassan, Abdul Khalil H.P.S., Abdulwahab F. Owolabi et al. "Cellulose nanowhiskers from oil palm empty fruit bunch biomass as green fillers", Elsevier BV, 2017	<1 %
Publication		
14	Paschoal, Giovanni B., Carmen M. O. Muller, Gizilene M. Carvalho, Cesar A. Tischer, and Suzana Mali. "ISOLATION AND CHARACTERIZATION OF NANOFIBRILLATED CELLULOSE FROM OAT HULLS", Química Nova, 2015.	<1 %
Publication		
15	Supitcha Tomyangkul, Pornlada Pongmuksuwan, Wanlop Harnnarongchai, Kantima Chaochanchaikul. "Enhancing sound absorption properties of open-cell natural rubber foams with treated bagasse and oil palm fibers", Journal of Reinforced Plastics and Composites, 2016	<1 %
Publication		
16	tel.archives-ouvertes.fr	<1 %
Internet Source		
17	Rui M. A. Domingues, Manuela E. Gomes, Rui L. Reis. "The Potential of Cellulose Nanocrystals in Tissue Engineering Strategies", Biomacromolecules, 2014	<1 %
Publication		
18	Submitted to Silver Oaks International School, Bangalore	<1 %

19	www.compositestech.com Internet Source	<1 %
20	"Fiber Plants", Springer Science and Business Media LLC, 2016 Publication	<1 %
21	Da Zhao, Zhou Zhou. "Applications of Lightweight Composites in Automotive Industries", American Chemical Society (ACS), 2014 Publication	<1 %
22	Karen S. Prado, Asaph A. Jacinto, Márcia A. S. Spinacé. "Chapter 10 Cellulose Nanostructures Extracted from Pineapple Fibres", Springer Science and Business Media LLC, 2020 Publication	<1 %
23	digital.csic.es Internet Source	<1 %
24	journals.plos.org Internet Source	<1 %
25	fmipa.itb.ac.id Internet Source	<1 %
26	herkules.oulu.fi Internet Source	<1 %
27	idoc.pub Internet Source	<1 %
28	www.insightsociety.org Internet Source	<1 %
29	Hongli Zhu, Wei Luo, Peter N. Ciesielski, Zhiqiang Fang, J. Y. Zhu, Gunnar Henriksson, Michael E. Himmel, Liangbing Hu. "Wood-Derived Materials for Green Electronics,	<1 %

Biological Devices, and Energy Applications",
Chemical Reviews, 2016

Publication

30	Chuanwei Miao, Wadood Y. Hamad. "Cellulose reinforced polymer composites and nanocomposites: a critical review", Cellulose, 2013	<1 %
31	Keat Teong Lee, Cynthia Ofori-Boateng. "Sustainability of Biofuel Production from Oil Palm Biomass", Springer Science and Business Media LLC, 2013	<1 %
32	"Bio - based Packaging", Wiley, 2021	<1 %
33	J. Tarique, S.M. Sapuan, A. Khalina, S.F.K. Sherwani, J. Yusuf, R.A. Ilyas. "Recent developments in sustainable arrowroot (Maranta arundinacea Linn) starch biopolymers, fibres, biopolymer composites and their potential industrial applications: A review", Journal of Materials Research and Technology, 2021	<1 %
34	ncsu.edu	<1 %
35	Chao Liu, Haishun Du, Lv Dong, Xin Wang, Yuedong Zhang, Guang Yu, Bin Li, Xindong Mu, Hui Peng, Huizhou Liu. "Properties of Nanocelluloses and Their Application as Rheology Modifier in Paper Coating", Industrial & Engineering Chemistry Research, 2017	<1 %
36	Rudi Dungani, Abdulwahab F. Owolabi, Chaturbhuj K. Saurabh, H. P. S. Abdul Khalil et	<1 %

al. "Preparation and Fundamental Characterization of Cellulose Nanocrystal from Oil Palm Fronds Biomass", Journal of Polymers and the Environment, 2016

Publication

37	Submitted to University Tun Hussein Onn Malaysia	<1 %
Student Paper		
38	repository.lib.ncsu.edu	<1 %
Internet Source		
39	vdocuments.site	<1 %
Internet Source		
40	Soeta, Hiroto, Shuji Fujisawa, Tsuguyuki Saito, Lars A. Berglund, and Akira Isogai. "Low-Birefringent and Highly Tough Nanocellulose-Reinforced Cellulose Triacetate", ACS Applied Materials & Interfaces	<1 %
Publication		
41	www.grandviewresearch.com	<1 %
Internet Source		
42	www.scribd.com	<1 %
Internet Source		
43	api.intechopen.com	<1 %
Internet Source		
44	ir.qibebt.ac.cn	<1 %
Internet Source		
45	link.springer.com	<1 %
Internet Source		
46	www.eurekaselect.com	<1 %
Internet Source		
47	www.jddtonline.info	<1 %
Internet Source		
48	www.scipress.com	
Internet Source		

Exclude quotes On

Exclude matches < 10 words

Exclude bibliography On